

PHOTOCATALYTIC OXIDATION OF GAS PHASE VOLATILE ORGANIC  
COMPOUNDS USING UNDOPED AND METAL IONS DOPED TITANIUM  
DIOXIDE THIN FILMS.

NOOR KHAIDA WATI BTE MOHD SAIYUDI

A thesis submitted in fulfilment of the  
requirements for the award of the degree of  
Master of Science (Chemistry)

Faculty of Science  
Universiti Teknologi Malaysia

JUNE 2006

*Dedicated in love and gratitude to,*

*My late parents, Mohd Saiyudi bin Othman and Nora bt Md Taib*

*and*

*My husband, Mohd Khir bin Muhammad*

## ACKNOWLEDGEMENTS

I thank ALLAH for giving me the strength, patience, courage and maturity to face and undergo one of the most challenging events of my life. I would like to thank my supervisors Associate Professor Dr Mohd Yusuf Othman and Professor Dr Wan Azelee Wan Abu Bakar for their guidance and encouragement. To another wonderful person, Dr Keiichi Tanaka, I wished to express my sincere gratitude for his guidance, support and constant sharing of knowledge throughout this work. To Mr. Teruaki Hisanaga and Mr. Shariq Vohra, a special thanks for helping me during my early work at NIMC, Tsukuba, Japan. Thank you also for making my stay at Tsukuba an extremely enjoyable and unforgettable one.

I wish to thank Associate Professor Dr Ambar Yarmo and the staff from Department of Chemistry, Universiti Kebangsaan Malaysia for their assistance on the XPS analysis. I also thank Associate Professor Dr Karim Deraman, Associate Professor Dr. Mohd Khairi Zaidin, Dr. Zuhairi Ibrahim, Dr. Agus and Dr. Putut from the Physics Department, UTM for their valuable advice and comments. To all individuals who have helped and contributed to the accomplishment of this work, in particular, Mr. Ayub and Mr. Jeffri from the Faculty of Mechanical, Mr. Abdul Kadir, Mr. Zaki Rahman, Mr. Zaki Hassan, Mr. Abdul Hanan, Mr Ayob Jabal and Mr. Fuaad Omar from the Department of Chemistry, Mr. Jaafar, Mrs. Wani and Mrs. Norhaya from the Physics Department, Faculty of Science, UTM. Finally, to my fellow colleague in the Science Faculty, UTM, whose names are too numerous to mention, thank you for your help, support and encouragement during my critical period.

I wish to thank Universiti Teknologi Malaysia for granting me the study leave and Jabatan Perkhidmatan Awam Malaysia for the financial support.

Lastly to my husband and family for the love, patience, praying and support that went above and beyond.

## ABSTRACT

Heterogeneous photocatalytic oxidation allows the oxidation of airborne volatile organic compounds (VOCs) into carbon dioxide and water in the presence of a semiconductor catalyst and UV light source. Titanium dioxide ( $\text{TiO}_2$ ), due to its chemical stability, non-toxicity and low cost represents one of the most efficient photocatalyst. However, only the ultraviolet fraction of the solar irradiation is active in the photoexcitation processes using pure  $\text{TiO}_2$  and although,  $\text{TiO}_2$  can treat a wide range of VOCs, the effectiveness of the process for pollution abatement is still low. A more effective and efficient catalyst therefore must be formulated. Doping  $\text{TiO}_2$  with metal ions was considered with the aim of improving  $\text{TiO}_2$  photocatalytic properties. In this study transparent  $\text{TiO}_2$  thin films were prepared using the sol-gel and dip-coating method. Various ratios of doped  $\text{TiO}_2$  thin films were also prepared using  $\text{Cr}^{3+}$ ,  $\text{Fe}^{3+}$ ,  $\text{Cu}^{2+}$ ,  $\text{Ni}^{2+}$ ,  $\text{Co}^{2+}$ ,  $\text{Zn}^{2+}$ ,  $\text{Mn}^{2+}$  and  $\text{Ag}^+$  ions. The photoactivity of the catalyst was evaluated by the photodegradation of VOCs, conducted in a home built glass reactor. Photocatalytic oxidation of benzene using various ratios of metal-doped  $\text{TiO}_2$  showed an optimum dopant to metal ion ratio that indicates the dependency of  $\text{TiO}_2$  photocatalytic reactivity on dopant concentration. Photocatalytic oxidation of benzene, toluene, *m*-xylene, acetone and tetrachloroethylene was conducted using the catalyst with the optimum ratio. It was observed that the photoactivity of doped  $\text{TiO}_2$  substantially depends on the type and concentration of dopant and VOCs. Dopants affect the photoreactivity of  $\text{TiO}_2$  by acting either as electron/hole trap or electron-hole recombination center. High photocatalytic degradation of all the VOCs was observed with pure  $\text{TiO}_2$ . However adding  $\text{Fe}^{3+}$  and  $\text{Ag}^+$  into  $\text{TiO}_2$  increased the photodegradation of benzene and acetone while  $\text{Zn}^{2+}$  in toluene and *m*-xylene degradation. Dopants such as  $\text{Cr}^{3+}$ ,  $\text{Co}^{2+}$ ,  $\text{Cu}^{2+}$ ,  $\text{Ni}^{2+}$  and  $\text{Mn}^{2+}$  decreased the photoreactivity of  $\text{TiO}_2$  in the photodegradation of all VOCs under studied. Dopants have no effect in TeCE degradation. However, TeCE shows highest degradation compared to the non-chlorinated hydrocarbon. This observation was attributed to the participation of chlorine radical, which induced a chain reaction mechanism. Preliminary studies on the mineralization of VOCs showed that  $\text{CO}_2$  was formed during the photooxidation process using pure or doped photocatalyst. The formation of new compounds, however, was not detected. The experimental ratio of VOCs degraded against the amount of  $\text{CO}_2$  formed showed that the photodegradation of VOCs is a partial oxidation process. Structural and optical properties of the thin films were characterized using XRD, SEM/EDAX, XPS, UV-Vis and PL spectroscopy. All thin films showed primarily the anatase phase. However, the presence of rutile in doped  $\text{TiO}_2$  contributed to the reduced photoreactivity of  $\text{TiO}_2$ . Surface species such as  $\text{Ti}^{4+}$ , surface hydroxyl and physically adsorbed water increased the photoreactivity of  $\text{TiO}_2$  but  $\text{Ti}^{3+}$  reduced its activity. Dopants such as  $\text{Zn}^{2+}$ ,  $\text{Mn}^{2+}$  and  $\text{Ag}^+$  shift the absorption edge of  $\text{TiO}_2$  into the visible region indicating the possibility of photocatalytic process using visible light.

## ABSTRAK

Pengoksidaan fotopemangkinan heterogen melibatkan pengoksidaan bahan mudah meruap (VOCs) kepada karbon dioksida dan air dengan menggunakan mangkin semikonduktor dan cahaya UL. Titanium dioksida merupakan fotomangkin yang sangat berkesan kerana kestabilan kimia, tidak toksik dan murah. Bagaimanapun, dalam pancaran solar, hanya kawasan UL adalah aktif dalam proses fotopengujaan TiO<sub>2</sub> tulen. Walaupun TiO<sub>2</sub> boleh merawat sejumlah besar VOCs, keberkesanan proses ini dalam mengawal pencemaran udara masih rendah. Oleh itu mangkin yang lebih berkesan dan cekap perlu disediakan. Kaedah mendop TiO<sub>2</sub> dengan ion logam telah dipertimbangkan untuk meningkatkan sifat mangkinfoto TiO<sub>2</sub>. Dalam kajian ini sapat tipis TiO<sub>2</sub> telah disediakan dengan menggunakan kaedah sol-gel dan celup angkat. Sapat tipis dengan berbagai nisbah bahan dop juga disediakan menggunakan ion Cr<sup>3+</sup>, Fe<sup>3+</sup>, Cu<sup>2+</sup>, Ni<sup>2+</sup>, Co<sup>2+</sup>, Zn<sup>2+</sup>, Mn<sup>2+</sup> dan Ag<sup>+</sup>. Aktiviti fotomangkin telah dinilai melalui foto degradasi sebatian mudah meruap di dalam reaktor kaca. Pengoksidaan fotomangkin benzena menggunakan semua mangkin menunjukkan satu nilai optimum bahan pendop terhadap TiO<sub>2</sub>. Nilai ini menunjukkan bahawa aktiviti fotomangkin TiO<sub>2</sub> bergantung kepada kepekatan bahan pendop. Fotodegradasi benzena, toluena, *m*-silena, aseton dan tetrakloroetilena (TeCE) telah dikaji menggunakan mangkin pada nisbah yang optimum. Diperhatikan bahawa fotoaktiviti TiO<sub>2</sub> berpendop bergantung kepada jenis dan kepekatan pendop dan VOCs. Dopan mempengaruhi fotoreaktiviti TiO<sub>2</sub> dengan bertindak sebagai perangkap e<sup>-</sup>/h<sup>+</sup> atau sebagai pusat pengabungan e<sup>-</sup>/h<sup>+</sup>. Fotodegradasi VOCs adalah tinggi menggunakan TiO<sub>2</sub> tulen. Tetapi penambahan Fe<sup>3+</sup> dan Ag<sup>+</sup> ke dalam TiO<sub>2</sub> meningkatkan fotoreaktiviti TiO<sub>2</sub> terhadap degradasi benzena dan aseton manakala Zn<sup>2+</sup> untuk toluena dan *m*-silena. Dopan seperti ion Cr<sup>3+</sup>, Cu<sup>2+</sup>, Ni<sup>2+</sup>, Co<sup>2+</sup>, dan Mn<sup>2+</sup> menurunkan aktiviti TiO<sub>2</sub>. Fotodegradasi TeCE bagaimanapun tidak dipengaruhi oleh dopan tetapi fotodegradasi TeCE adalah sangat tinggi berbanding sebatian hidrokarbon tanpa klorin. Ini adalah berpunca daripada penglibatan radikal klorin yang menyuntik penghasilan mekanisme rantai. Kajian awal mineralisasi VOCs menunjukkan bahawa CO<sub>2</sub> terbentuk semasa proses fotopengoksidaan menggunakan fotomangkin tulen atau berpendop. Pembentukan sebatian baru, bagaimanapun, tidak dapat dikesan menggunakan GC-MS. Nisbah VOCs yang terdegradasi terhadap CO<sub>2</sub> yang terbentuk menunjukkan fotodegradasi VOCs adalah pengoksidaan separa. Sifat struktur dan optik sapat tipis dicirikan menggunakan XRD, SEM/EDAX, XPS, UV-Vis dan PL. Semua mangkin menunjukkan fasa anatas. Kewujudan fasa rutil menyebabkan penurunan fotoaktiviti TiO<sub>2</sub>. Spesies permukaan seperti Ti<sup>4+</sup>, hidrosil dan air meningkatkan fotoaktiviti TiO<sub>2</sub> tetapi Ti<sup>3+</sup> di dapati menurunkan kereaktifan TiO<sub>2</sub>. Bahan pendop seperti ion Zn<sup>2+</sup>, Mn<sup>2+</sup> dan Ag<sup>+</sup> mengubah penyerapan TiO<sub>2</sub> ke kawasan nampak, menunjukkan kemungkinan foto degradasi dapat dijalankan menggunakan cahaya nampak.

## TABLE OF CONTENTS

CHAPTER	TITLE	PAGE
	<b>TITLE</b>	i
	<b>STATEMENT</b>	ii
	<b>DEDICATIONS</b>	iii
	<b>ACKNOWLEDGEMENTS</b>	iv
	<b>ABSTRACT</b>	v
	<b>ABSTRAK</b>	vi
	<b>TABLE OF CONTENTS</b>	vii
	<b>LIST OF TABLES</b>	xi
	<b>LIST OF FIGURES</b>	xii
	<b>LIST OF ABBREVIATIONS/SYMBOLS/TERMS</b>	xvi
	<b>LIST OF APPENDICES</b>	xvii
<b>1</b>	<b>INTRODUCTION</b>	
	1.0 Air Pollution	1
	1.1 Volatile Organic Compounds (VOCs)	2
	1.2 Heterogeneous Photocatalysis	5
	1.3 Titanium Dioxide (TiO <sub>2</sub> )	7
	1.3.1 Band Gap Transition	9
	1.3.2 Doping	10
	1.3.3 Reaction Pathway	13
	1.3.4 Kinetic Study	15
	1.3.5 TiO <sub>2</sub> Thin Film	17
	1.3.6 Limitations of TiO <sub>2</sub>	18
	1.4 Research Objectives	20
	1.5 Scope of Study	20

**2 REVIEW OF THE LITERATURE**

2.0	Introduction	22
2.1	Gas Phase Photocatalysis Using TiO <sub>2</sub>	23
2.2	Photocatalysis Using Doped TiO <sub>2</sub>	36
2.3	Summary	45

**3 EXPERIMENTAL**

3.0	Introduction	48
3.1	Chemicals and Reagents	48
3.2	Catalysts Preparation	49
3.2.1	Sol-gel dip coating	50
3.3	Photocatalytic Activity Measurements	51
3.3.1	Photocatalytic Testing	52
3.3.1.1	Gas Chromatograph	53
3.3.1.2	VOCs Calibration	54
3.3.2	Kinetic Study	55
3.3.3	Effect of Chlorine Radical	56
3.4	Characterization Tools	57
3.4.1	Ellipsometry	58
3.4.2	X-Ray Diffraction (XRD)	58
3.4.3	X-Ray Photoelectron Spectroscopy (XPS)	59
3.4.4	Scanning Electron Microscope (SEM)/Electron Dispersive X-Ray Analysis (EDAX)	60
3.4.5	UV-Vis Spectroscopy (Band gap Measurements)	62
3.4.6	Photoluminescence (PL) Measurements	62
3.4.7	Gas Chromatograph-Mass Spectroscopy (GC-MS)	63

<b>4</b>	<b>RESULTS AND DISCUSSION</b>	
	<b>PHOTOCATALYTIC REACTIONS</b>	
4.0	Introduction	66
4.1	Preliminary Studies	67
4.2	Optimum Ratio	69
4.3	Effect of Wavelength	72
4.4	Photocatalytic Oxidation of VOCs Using doped TiO <sub>2</sub> Thin Films	75
4.4.1	Benzene	75
4.4.2	Toluene	82
4.4.3	<i>m</i> -Xylene	87
4.4.4	Acetone	89
4.4.5	Tetrachloroethylene (TeCE)	92
4.5	Photocatalytic Oxidation of Mixtures	94
4.5.1	TeCE/Benzene Mixture	95
4.5.2	TeCE/Toluene Mixture	97
4.6	Kinetic Study	101
4.7	Mineralization Study of VOCs	106
4.8	Catalyst Deactivation	111
4.9	Summary	112
<b>5</b>	<b>RESULTS AND DISCUSSION</b>	
	<b>CHARACTERIZATION</b>	
5.1	Introduction	114
5.2	X-Ray Diffraction (XRD)	114
5.3	X-Ray Photoelectron Spectroscopy (XPS)	118
5.4	Electron Dispersive X-Ray Analysis (EDAX)	127
5.5	Scanning Electron Microscope (SEM)/	129
5.6	UV-Visible Spectrum	131
5.7	Band gap	134
5.8	Photoluminescence (PL)	138



5.9	Summary	143
<b>6</b>	<b>CONCLUSION</b>	147
<b>7</b>	<b>RECOMMENDATION</b>	151
	<b>REFERENCES</b>	153
	Appendices	171

## LIST OF TABLES

TABLE. NO.	TITLE	PAGE
1.1	National VOCs Emission in ktonnes (1995)	3
3.1	Amount of metal ion precursors (g) added to TiO <sub>2</sub>	50
4.1	The amount of TiO <sub>2</sub> coated on the hollow cylinders after calcinations at 600 °C for 1 hour	67
4.2	GC retention time of VOCs	68
4.3	Adsorption and photolysis of VOCs over TiO <sub>2</sub> after two (2) hours (photolysis using 354 nm light source).	68
4.4	Photodegradation of benzene using 254 nm, 354 nm and fluorescence light source. Thin films calcined at 600 °C for 1 hour	73
4.5	Rate of benzene degradation. Time taken for 90% of benzene to degrade. Catalysts calcined at 600 °C for 1 hour. (L: 280-430 ppm; H: 630-800 ppm)	76
4.6	Rate of toluene degradation. Time taken for 90% of toluene to degrade. Catalysts calcined at 600 °C for 1 hour. (L: 270-320 ppm; H: 580-625 ppm)	83
4.7	Amount of <i>m</i> -xylene degraded after 120 minutes illumination time. Catalysts calcined at 600 °C for 1 hour. (L: 200-280 ppm; H: 580-640 ppm)	87
4.8	Rate of acetone degradation. Time taken for 90 % of acetone to degrade. Catalyst calcined at 600 °C for 1 hour. (L: 380-480 ppm; H: 740-890 ppm).	90
4.9	Amount of TeCE degraded after 3 minutes illumination time. Catalysts calcined at 600 °C for 1 hour. (L: 250-380 ppm; H: 650-780 ppm)	93
4.10	Langmuir-Hinshelwood parameters obtained in the photocatalytic oxidation of VOCs	104
4.11	The abundance of fragments (m/z = VOCs molecular	

	ion, $m/z = 44$ and $m/z = 32$ ) during the photodegradation of VOCs	107
4.12	The theoretical ratio of VOCs degraded against the amount of $\text{CO}_2$ formed during complete oxidation	109
5.1	Binding energy (eV) for Ti 2p in undoped and doped catalysts	118
5.2	Binding energy (eV) for O 1s in undoped and doped catalysts	118
5.3	Binding energy (eV) for Ti 2p in Cr and Cu doped $\text{TiO}_2$ catalysts	122
5.4	Binding energy (eV) for O 1s in Cr and Cu doped $\text{TiO}_2$ catalysts	122
5.5	Physical and optical measurements for undoped and doped $\text{TiO}_2$ thin films	135
5.6	Energy values and intensities of PL peaks	139

## LIST OF FIGURES

FIGURE NO.	TITLE	PAGE
1.1	Illustrating the major processes occurring on a semiconductor particle following electronic excitation	6
1.2	Energy diagram for TiO <sub>2</sub> and relevant redox potentials	8
1.3	Electronic transitions in a semiconductor bands. (a), (b) direct transition and (c) indirect transition	10
1.4	Energy difference reduced due to dopant	11
1.5	Energy levels of dopant ions	12
3.1	Photocatalysis reactor scheme	52
3.2	A schematic diagram of a gas chromatograph	54
3.3	Glass container for VOCs calibration	55
3.4	Schematic diagram for a generic SEM	61
4.1	Bar chart showing amount of benzene degraded using different ratios of doped TiO <sub>2</sub>	70
4.2	Degradation of benzene using light with different wavelength for undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	74
4.3	Degradation of high concentration of benzene using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	77
4.4	Degradation of low concentration of benzene using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	77
4.5	Degradation of high concentration of toluene using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	84
4.6	Degradation of low concentration of toluene using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	84
4.7	Degradation of high concentration of <i>m</i> -xylene using	

	doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	88
4.8	Degradation of low concentration of <i>m</i> -xylene using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	88
4.9	Degradation of high concentration of acetone using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	91
4.10	Degradation of low concentration of acetone using doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	91
4.11	Degradation of benzene and TeCE in TeCE/benzene mixture using undoped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour.	95
4.12	Degradation of benzene and TeCE in TeCE/benzene mixture using Fe <sup>3+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	96
4.13	Degradation of toluene and TeCE in TeCE/toluene mixture using undoped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour.	98
4.14	Degradation of toluene and TeCE in TeCE/toluene mixture using Zn <sup>2+</sup> doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour.	99
4.15	Degradation of toluene as a single component and mixed component feed using Zn <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	100
4.16	1/ <i>r</i> versus 1/ <i>C</i> plot for benzene degradation	102
4.17	1/ <i>r</i> versus 1/ <i>C</i> plot for toluene degradation	102
4.18	1/ <i>r</i> versus 1/ <i>C</i> plot for acetone degradation	103
4.19	1/ <i>r</i> versus 1/ <i>C</i> plot for TeCE degradation	103
4.20	Deactivation of TiO <sub>2</sub> for the photocatalytic oxidation of benzene	111
5.1	XRD profile of pure and doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour	117
5.2	XPS survey spectrum for the surface of undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	119
5.3	Typical O 1s spectrum for undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	119

5.4	Typical Ti 2p spectrum for undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	121
5.5	XPS spectrum of Ti 2p for Cr doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	123
5.6	XPS spectrum of O 1s for Cr doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	123
5.7	Condensation process of oxygen bonded to Ti <sup>3+</sup>	125
5.8	XPS spectrum of Cr 2p for doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	126
5.9	EDAX spectra of glass support	128
5.10	EDAX spectra of TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	128
5.11	SEM micrograph of undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour. Magnification:10K; Scale bar: 2μ	129
5.12A	SEM micrograph of (a) Cr <sup>3+</sup> (b) Fe <sup>3+</sup> (c) Ni <sup>2+</sup> (d) Cu <sup>2+</sup> (e) Co <sup>2+</sup> and (f) Zn <sup>2+</sup> doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour. Magnification:10K; Scale bar 2μ	130
5.12B	SEM micrograph of (g) Mn <sup>2+</sup> and (h) Ag <sup>+</sup> doped TiO <sub>2</sub> thin films calcined at 600 °C for 1 hour. Magnification: 10K; Scale bar 2μ	131
5.13	UV-Vis absorption spectrum for doped and undoped thin films calcined at 600 °C for 1 hour.	132
5.14	Tauc's plot for (a) direct and (b) indirect band gap	135
5.15	Photoluminescence spectrum of undoped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour.	140

**List of Abbreviations/Symbols/Terms**

VOCs	-	Volatile Organic Compounds
CB	-	Conduction Band
VB	-	Valence Band
$E_{bg}$	-	Band Gap Energy
$E_g$	-	Optical Band Gap
RF	-	Radio Frequency
GC	-	Gas Chromatography
GC-MS	-	Gas Chromatography – Mass Spectrometer
FID	-	Flame Ionization Detector
UV-Vis	-	Ultraviolet Visible
XRD	-	X-Ray Diffraction Analysis
XPS	-	X-Ray Photoelectron Spectroscopy
SEM	-	Scanning Electron Microscope
PL	-	Photoluminescence
EDAX	-	Electron Dispersive X-Ray Analysis
L-H	-	Langmuir – Hinshelwood
$n$	-	Refractive index
$d$	-	Film Thickness
$k$	-	Reaction Rate Constant
$K$	-	Adsorption Equilibrium Constant
$\alpha$	-	Adsorption Coefficient
$r$	-	Degradation Rate of VOCs
$t$	-	Reaction Time (minutes)
C	-	Concentration of Gaseous VOCs (ppm)
R	-	Reflectivity
T	-	Transmittance

**LIST OF APPENDICES**

<b>APPENDIX</b>	<b>TITLE</b>	<b>PAGE</b>
A1	Calculation of percentage degradation	172
A2	Calculation of thin film surface area	172
B	Calculation to convert VOCs volume ( $\mu\text{L}$ ) to VOCs concentration (ppm).	173
C1	Calibration graph of benzene.	174
C2	Calibration graph of toluene.	174
C3	Calibration graph of acetone.	175
C4	Calibration graph of <i>m</i> -xylene.	175
C5	Calibration graph of tetrachloroethylene	176
D1	GC-MS spectrum of air sample in reactor	177
D2	GC-MS spectrum of pure benzene	178
D3	GC-MS spectrum of pure toluene	179
D4	GC-MS spectrum of pure acetone	180
D5	GC-MS spectrum of pure TeCE	181
D6	GC-MS data for benzene photodegradation using pure $\text{TiO}_2$	182
D7	GC-MS data for benzene photodegradation using $\text{Fe}^{3+}/\text{TiO}_2$	184
D8	GC-MS data for toluene photodegradation using pure $\text{TiO}_2$	186
D9:	GC-MS data for toluene photodegradation using	



	Zn <sup>2+</sup> /TiO <sub>2</sub>	193
D10	GC-MS data for <i>m</i> -xylene photodegradation using pure TiO <sub>2</sub>	195
D11	GC-MS data for acetone photodegradation using pure TiO <sub>2</sub>	197
D12	GC-MS data for acetone photodegradation using Fe <sup>3+</sup> /TiO <sub>2</sub>	198
D13	GC-MS data for TeCE photodegradation using pure TiO <sub>2</sub>	200
D14	GC-MS data for TeCE photodegradation using Zn <sup>2+</sup> /TiO <sub>2</sub>	203
E1	EDAX spectra for Cr <sup>3+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	207
E2	EDAX spectra for Fe <sup>3+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	207
E3	EDAX spectra for Ni <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	208
E4	EDAX spectra for Cu <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	208
E5	EDAX spectra for Co <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	209
E6	EDAX spectra for Zn <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	209
E7	EDAX spectra for Mn <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	210
E8	EDAX spectra for Ag <sup>+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	210
F1	Tauc's plot for Cr <sup>3+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	211
F2	Tauc's plot for Fe <sup>3+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	212
F3	Tauc's plot for Ni <sup>2+</sup> doped TiO <sub>2</sub> thin film calcined at 600 °C for 1 hour	213

F4	Tauc's plot for $\text{Cu}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	214
F5	Tauc's plot for $\text{Co}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	215
F6	Tauc's plot for $\text{Zn}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	216
F7	Tauc's plot for $\text{Mn}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	217
F8	Tauc's plot for $\text{Ag}^+$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	218
G1	Photoluminescence spectra for $\text{Cr}^{3+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	219
G2	Photoluminescence spectra for $\text{Fe}^{3+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	219
G3	Photoluminescence spectra for $\text{Ni}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	220
G4	Photoluminescence spectra for $\text{Cu}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	220
G5	Photoluminescence spectra for $\text{Co}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	221
G6	Photoluminescence spectra for $\text{Zn}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	221
G7	Photoluminescence spectra for $\text{Mn}^{2+}$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	222
G8	Photoluminescence spectra for $\text{Ag}^+$ doped $\text{TiO}_2$ thin film calcined at 600 °C for 1 hour	222

## CHAPTER 1

### INTRODUCTION

#### 1.0 Air Pollution

In recent years as more countries become a more developed and industrialized nation, the quality of our environment deteriorates dramatically. Increased human activities accompanied by rapid industrial expansion have become the main contributors to water and air pollution. Volatile organic compounds (VOCs) which are considered as the most important anthropogenic pollutants generated in urban and industrial areas (Avila, 1998) are emitted to the atmosphere through the use of petroleum, manufacturing of organic chemicals, polymers, petrochemical and allied industries (Papaefthimou, 1998). Solvent thinners, degreasers, cleaners, lubricants and liquid fuels are also sources of VOCs emitted from small industries such as dry cleaners, electronic and auto repair shops.

Motor vehicles, however, remained the major source of VOCs in the world (Walsh, 1999). In 1999 the world's vehicle population inches over 700 million. In Malaysia, about 8.9 million vehicles were registered in 1998 and it was estimated that 2 million tonnes of hydrocarbon, 38,000 tonnes of sulfur dioxide and 17,000 tonnes of particulate were released to the atmosphere (Department of Environment Malaysia, 1998). Through development, air pollution has become a major environmental concern not only in Malaysia but the world as well.

## 1.1 Volatile Organic Compounds (VOCs)

The term VOCs is used to identify all compounds containing carbon and present in the atmosphere, with the exception of elemental carbon, carbon monoxide and carbon dioxide (Augugliaro, 1999). VOCs are defined as having a boiling point that ranges between 50 °C and 260 °C (Jones, 1999). Their low boiling point means that they will readily emit gas vapors into the air at ambient temperatures.

VOCs include a wide range of substances with diverse effects. The most significant problem related to VOCs is the production of photochemical oxidants, for example, ozone and peroxyacetyl nitrate (PANs) (Japer, 1991) which is implicated in the formation of acid rain (Fisherman, 1991). Emission of VOCs also contributed to localized pollution problems of toxicity and odour. Many VOCs are also implicated in the depletion of the stratospheric ozone layer and may contribute to global warming (Alberici, 1997).

Many VOCs are toxic, and some are considered *carcinogenic*, *mutagenic*, or *teratogenic* (Wilkinson, 1987). Exposure to VOCs can result in both acute and chronic health effects. It is possible that asthmatics and other individuals with prior respiratory complaints may be particularly susceptible to low-dose VOCs exposures (Norback, 1995). At high concentrations, many VOCs are potent narcotics, and can depress the central nervous system (Jones, 1999). Exposures can also lead to irritation of the eyes and respiratory tract and cause sensitization reactions involving the eyes, skin and lungs. The occurrence of these compounds in the atmosphere therefore posed a greater threat to human health and the environment.

The global emission of non-methane VOCs (NMVOC) for the year 1990 is 153,244 ktone while in 1995 the amount increased to 159,634 ktone. Table 1.1 shows the national emission of VOCs for several countries in the year 1990 and 1995. Except for the US, all the other countries show an increasing emission of VOCs. Data was obtained from Emission Database for Global Atmospheric Research (EDGAR 3.2).

In this research the VOCs concerned are benzene, toluene, *m*-xylene, acetone, and tetrachloroethylene (TeCE). As these substances poses very serious health affects, the Environmental Protection Agency (EPA) of most countries considers all of these compounds priority pollutants. The concentration of single VOCs was reviewed to be generally below 15 ppb with most below 1.5 ppb (Wolkoff, 2001). However, in a given environment, the concentration of individual VOCs will be very variable and depend upon the presence or absence of potential emission source.

**Table 1.1:** National VOCs Emission in ktonnes (1995)

Country	1990	1995
Australia	2,377.01	2,390.73
Japan	5,435.64	5,851.56
Malaysia	1,636.93	1,938.23
Singapore	124.66	156.11
Thailand	898.9	1195.96
United Kingdom	3,360.80	3,567.10
United States	19,626.79	19,497.00

Benzene, toluene and xylene are monocyclic aromatic hydrocarbons associated with motor vehicle emissions arise predominantly from the evaporation and combustion of petroleum products. Exhaust emission constitute 80-90 % of the total emission of benzene, the highest level of exposure (Pang, 1996).

Benzene is a well-established human carcinogen and laboratory studies have shown that it exerts its effect by damaging the genetic materials of the cells. The most frequently reported health effect of benzene is bone marrow depression leading to *anaemia* (reduced red blood cells), *leucopenia* (reduced white cells) and *thrombocytopenia* (reduced blood plateles) (Wadge, 1997). The impact of benzene on human health and environment make it a worldwide concern as it is used widely

in many industries. There is no specific air quality goal for benzene, however it is widely accepted that exposed to benzene should be minimized.

Toluene occurs naturally in crude oil and in *tolu* tree. Toluene is used in aviation gasoline, solvent for paints, fingernail polish, lacquer, adhesive and in some printing and leather tanning processes. Although the primary sources of toluene emissions are crude petroleum and natural gas extraction, petroleum refining and household furniture manufacturing facilities, it is also emitted from tobacco smoke. Toluene affects the nervous system and high levels of toluene may affect the kidneys. The U.S EPA has established a reference concentration of 162 ppb for toluene based on neurological effects in humans and has set a limit of  $3 \times 10^{-4}$  ppm in drinking water (ATSDR, 2000). The inhalation of this concentration or less, over a lifetime, would not likely result in the occurrence of chronic non-cancer effects.

Xylene occurs naturally in petroleum and coal tar and is formed during forest fires. Chemical industries produce xylene from petroleum. It is used as solvent and in the printing, rubber and leather industries. It is also used as a cleaning agent, a thinner for paint, and in paint and varnishes. Xylene affects the brain, however, human and animal studies have not shown xylene to be carcinogenic, but these studies are not conclusive. The U.S EPA has set a limit of 10 ppm of xylene in drinking water and an exposure limit of 100 ppm in the workplace air. An exposure of 900 ppm of xylene can cause permanent health problems or death (ATSDR, 1995).

Acetone is a manufactured chemical that is also found naturally in the environment. Acetone is used to make plastic, fibers, drugs and other chemicals. It is widely used in industry as solvent for numerous organic substances and is a component of most paint and varnish removers. Although acetone is not carcinogen, exposure to it can cause health effects such as eye, nose and throat irritation. High exposures may damage the liver and kidneys. Skin contact can result in irritation and damage to the skin. A permissible exposure limits for acetone is 250 ppm in the workplace (ATSDR, 1994).

Tetrachloroethylene (TeCE), also known as perchloroethylene (PCE), is a manufactured chlorinated hydrocarbon compound, mainly used as degreaser for metal parts and as a solvent in dry cleaning operations. TeCE may be a carcinogen in humans and may damage the developing fetus. It can also damage the liver and kidneys enough to cause death. The U.S EPA maximum contaminant level for the amount of TeCE that can be in drinking water is 0.005 milligrams TeCE per liter of water. It is recommended that TeCE should be handled as a potential carcinogen and exposure of TeCE at the working place should be minimized (ATSDR, 1997).

Although public concern over the health effects of VOCs is directed to outdoor pollution, the health impacts of indoor air pollution should not be neglected. Studies showed that the concentration of indoor VOCs often exceed outdoor levels by up to 5 times (Jones, 1999). Indoors air pollutants emanate from a range of sources such as fabric of buildings, paints, varnishes, aerosol sprays, cleaners, disinfectants, automotive products, dry-cleaned clothing and tobacco smoke.


VOCs have drawn considerable attention in the last decade as the health effects of these compounds are better understood. Many countries have since put stringent regulations concerning the use and emission of VOCs. Currently there is a great deal of interest in developing processes that can destroy these compounds. Since a large number of the VOCs are oxidizable, chemical oxidation process can be looked upon as a viable method.

## **1.2 Heterogeneous Photocatalysis**

Heterogeneous photocatalysis is an emerging technique valuable for water and air purification and remediation. This method has gained significant impetus over the years as it offer the advantage of destroying a wide range of water and air pollutants. Conventional techniques such as activated carbon or air stripping are becoming unacceptable because they do not destroy the pollutants but only transfer the contaminants from one phase to another. The absolute toxicity of the pollutants, however, is not diminished.

Heterogeneous photocatalysis technique for air purification and wastewater treatment formed part of a group of processes known as *Advanced Oxidation Technologies* (AOTs). AOTs use a highly active redox reagent to bring about the complete mineralization of all atoms present in an organic pollutant (Ollis, 1988). Included among these AOTs is photocatalysis using semiconductors such as titanium dioxide. Ultraviolet light radiation on such catalysts sets in train a sequence of events that can lead to oxidation of organic (or inorganic) compounds present in water or air that is in contact with the catalyst.

In heterogeneous photocatalysis, activation of the semiconductor photocatalyst is achieved through the absorption of a photon with energy equal or higher than the catalyst band gap energy. This results in the promotion of an electron,  $e^-$  from the valence band to the conduction band, with the concomitant generation of a hole,  $h^+$  in the valence band. This electron-hole separation, characterized by a finite lifetime, allows different chemical pathways to occur as outlined in Figure 1.1.

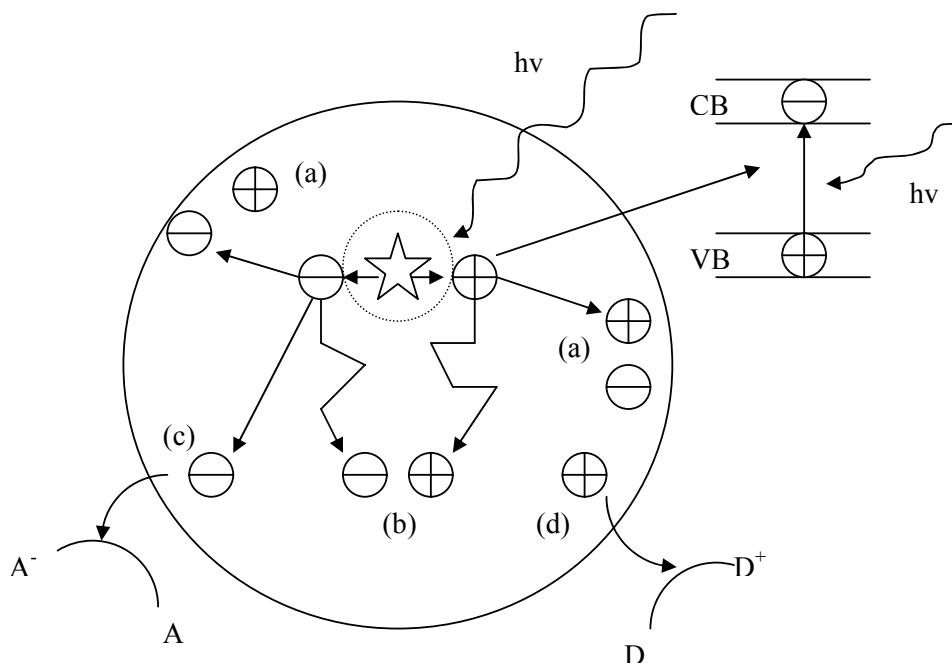

**Figure 1.1:** Illustration of the major processes occurring on a semiconductor particle following electronic excitation (Hoffman, 1995). (a) and (b) recombination of  $e^- h^+$ , (c) reduction of  $e^-$  by an electron acceptor, (d) oxidation of  $h^+$  by electron donor



This highly reactive  $e^- - h^+$  pairs can recombine and release heat (charge recombination) either on the surface of the semiconductor (Pathway a) or in the bulk volume (Pathway b) or migrate to the solid surface and undergo electron-transfer processes with adsorbates. The photogenerated electrons can reduced an electron acceptor A (Pathway c) and the photogenerated holes can oxidized an electron donor (Pathway d). For a semiconductor photocatalyst to be efficient, the different interfacial electron processes involving  $e^-$  and  $h^+$  must compete effectively with the major deactivation processes involving  $e^- - h^+$  recombination.


Once excitation occurs across the band gap there is a sufficient lifetime, in the nanosecond regime (Rothenberger, 1985) for the created electron-hole pair to undergo charge transfer to adsorbed species on the semiconductor surface from solution or gas phase contact. If the scavenger or surface defects are present to trap the electron or holes,  $e^- - h^+$  recombination can be prevented and the subsequent oxidation and reduction processes caused by electrons and holes may be enhanced (Park, 1999). Oxygen and surface-bound hydroxyl species are believed to be the most important electron acceptor and electron donor species in photocatalytic oxidation processes, respectively.

### **1.3 Titanium Dioxide**

In 1972, Fujishima and Honda (Fujishima, 1972) discovered the photocatalytic splitting of water on  $TiO_2$  electrodes. This was the starting point of a new era in heterogeneous photocatalysis. Since then heterogeneous photocatalytic oxidation, using  $TiO_2$  has been studied extensively in areas such as photovoltaic conversion and energy storage but more attention has been given in the remediation of water and air. Heterogeneous photocatalytic using  $TiO_2$  has several attractions.  $TiO_2$  is a relatively inexpensive compound as it is one of the most abundant minerals in the earth crust. It is chemically stable, resistant to acids and easy to handle, making it environmentally safe.  $TiO_2$  shows efficient destruction of toxic contaminants and reacts with organic pollutant at ambient temperature and pressure,

using oxygen as the oxidant, producing  $\text{CO}_2$  and  $\text{H}_2\text{O}$  or  $\text{HCl}$ , in the case of chlorinated organic compound.

Titanium dioxide occurs in two different crystal forms known as rutile and anatase. Both crystal forms exhibit photocatalytic activity under near-UV irradiation. However, anatase is more photoactive than rutile and is therefore more widely used. For anatase, the band gap energy of 3.2 eV corresponds to UV light (388 nm) while the band gap energy of rutile (3.0 eV) corresponds to violet light (413 nm). The band gap energy indicates the minimum energy of light necessary to produce transition of electrons from valence band (VB) to the conduction band (CB). The level of CB for anatase is 0.2 eV higher than rutile as depicted in Figure 1.2 (Fujishima, 1999).

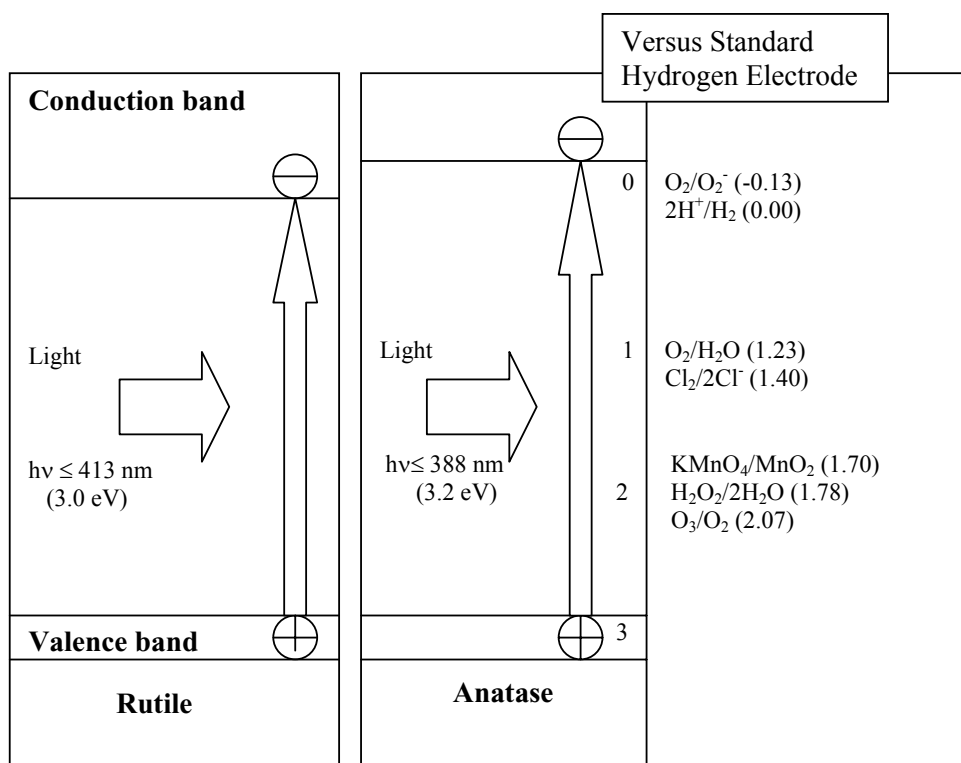

**Figure 1.2:** Energy diagram for  $\text{TiO}_2$  and relevant redox potentials

The VB energies for anatase and rutile are both similar, which is very low in the energy diagram, meaning that, for both materials, the VB holes have high oxidizing power. The CB energy for rutile is close to the potential required to electrolytically reduce water to hydrogen gas, but that of anatase is higher in the


energy diagram, meaning that it has higher reducing power. This means that it can drive the very important reaction involving the electrolytic reduction of molecular oxygen ( $O_2$ ) to superoxide ( $O_2^-$ ), which is as important as the holes and hydroxyl radicals in breaking down organic compounds.

### 1.3.1 Band Gap Transition

Unlike metals, which have a continuum of electronic states, semiconductors possess a void energy region where no energy levels are available to promote recombination of an electron and hole produced by photoactivation in the solid. The void region, which extends from the top of the filled valence band to the bottom of the vacant conduction band is called the band gap. The band gap is the most important optical characteristic of a semiconductor.

When light of sufficient energy is incident on a semiconductor, photons are absorbed and electronic excitations are created. Electrons at the ground state will be excited to a higher energy level. Eventually, these excitations relax and the electrons return to the ground state. Different processes participate in this relaxation, which can be categorized as either radiative process or non-radiative process (such as phonon emission, capture by deep centers or Auger effect). If radiative relaxation occurs, the emitted light is called photoluminescence (PL). The radiated recombination of excited individuals or coupled charge carriers that caused luminescence may be: (i) free electrons or holes occupying the energy levels in the conduction and valence bands respectively, in fact PL can be considered as the radiative recombination of conduction band electron with valence band hole in semiconductor (ii) electrons or holes bound to ionized impurities or dopants, and (iii) excitons (electron-hole pairs coupled by Coulomb interaction) which may move throughout the crystal lattice of the semiconductor (free excitons) or become localized by interaction with an active point defect of the lattice or on interfaces occurring in the semiconductor (bound excitons).

There are two kinds of transition that can occur in the band gap when a semiconductor absorbs photon as depicted in Figure 1.3.

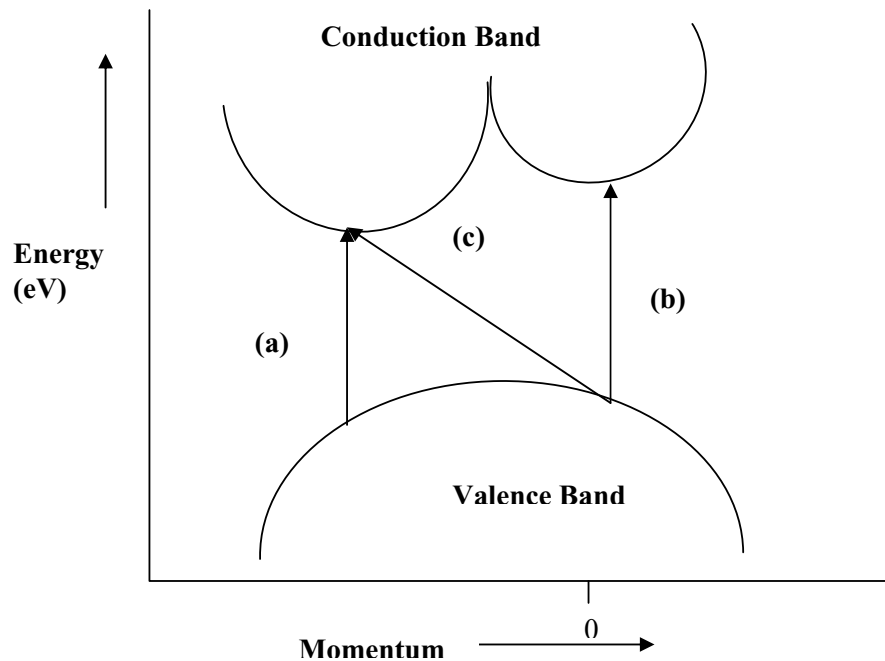

**Figure 1.3:** Electronic transitions in a semiconductor bands. (a), (b) direct transition and (c) indirect transition (Serpone, 1989)


When the lowest energy excitation of an electron from the valence band to the conduction band involves no change in momentum (Figure 1.3), the semiconductor is said to have a *direct band gap*. However, in an *indirect-band-gap* material, the momentum at the valence band maximum is different from that at the conduction band minimum (Figure 1.3).  $\text{TiO}_2$  can exhibit both indirect and direct transition but the former transition was much accepted.

### 1.3.2 Doping

It can be seen that the essence of a photocatalytic mechanism is the production of photogenerated electron and hole. The ease of production and


separation of these reactive species will consequently increase the photocatalytic activity of  $\text{TiO}_2$ . Therefore the smaller the band gap, the higher the production of the electron and hole. It can be seen from Section 1.3.1 that the transition energy of an electron from the VB to CB can change with the existence of impurities or dopant in the semiconductor. Doping implies incorporation of a foreign cation into the catalyst matrix of the parent metal oxide (Karakitsou, 1993). From a chemical point of view,  $\text{TiO}_2$  doping is equivalent to the introduction of defect sites into the semiconductor lattice (Fox, 1993). A wide range of metal ions in particular transition metal ions, have been used as dopants in the effort to increase the photocatalytic reactivity of  $\text{TiO}_2$ .

In the bulk of crystalline material, translational symmetry leads to the formation of electronic energy bands. Dopants break the periodicity of the lattice and perturb the band structure locally. The perturbation usually can be characterized by a discrete energy level that lies within the band gap. Therefore new energy levels in the band gap are created when dopants are introduced inside the semiconductor. If the new level lies between the VB and CB, the photocatalytic activity of the semiconductor is enhanced, as lower transition energy is required (Figure 1.4).

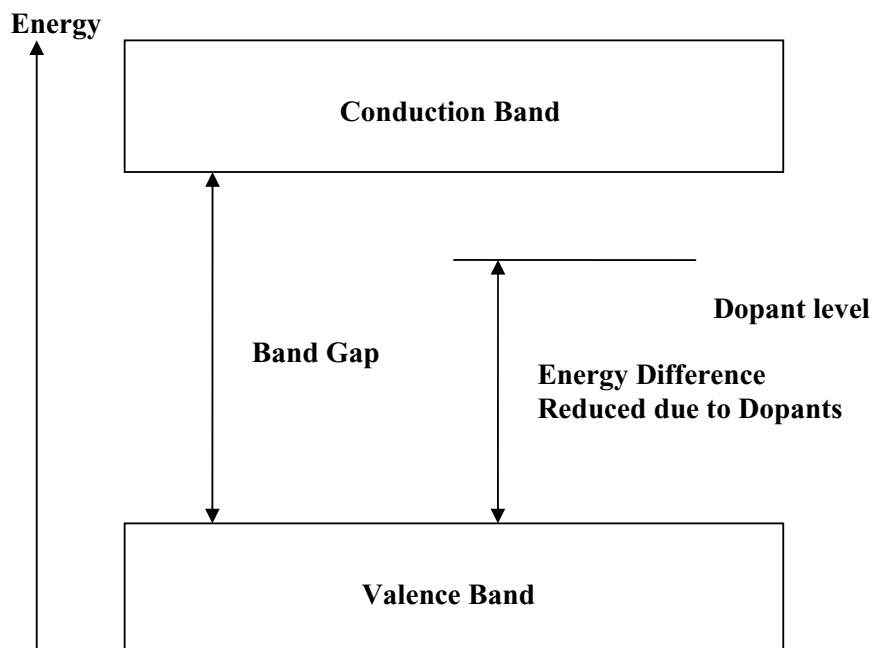


**Figure 1.4:** Energy Difference Reduced due to Dopant

Besides lowering the transition energy of electron, metal ion dopants influence the photoreactivity of TiO<sub>2</sub> by acting as electron (or hole) traps and by altering the e<sup>-</sup>/h<sup>+</sup> pair recombination rate through the following process.



Where the energy level for M<sup>n+</sup>/M<sup>(n-1)+</sup> lies below the conduction band edge (E<sub>cb</sub>) and the energy level for M<sup>n+</sup>/M<sup>(n+1)+</sup> above the valence band edge (E<sub>vb</sub>). Available energy levels of metal ion impurities in TiO<sub>2</sub> are shown in Figure 1.5 (Litter, 1996).

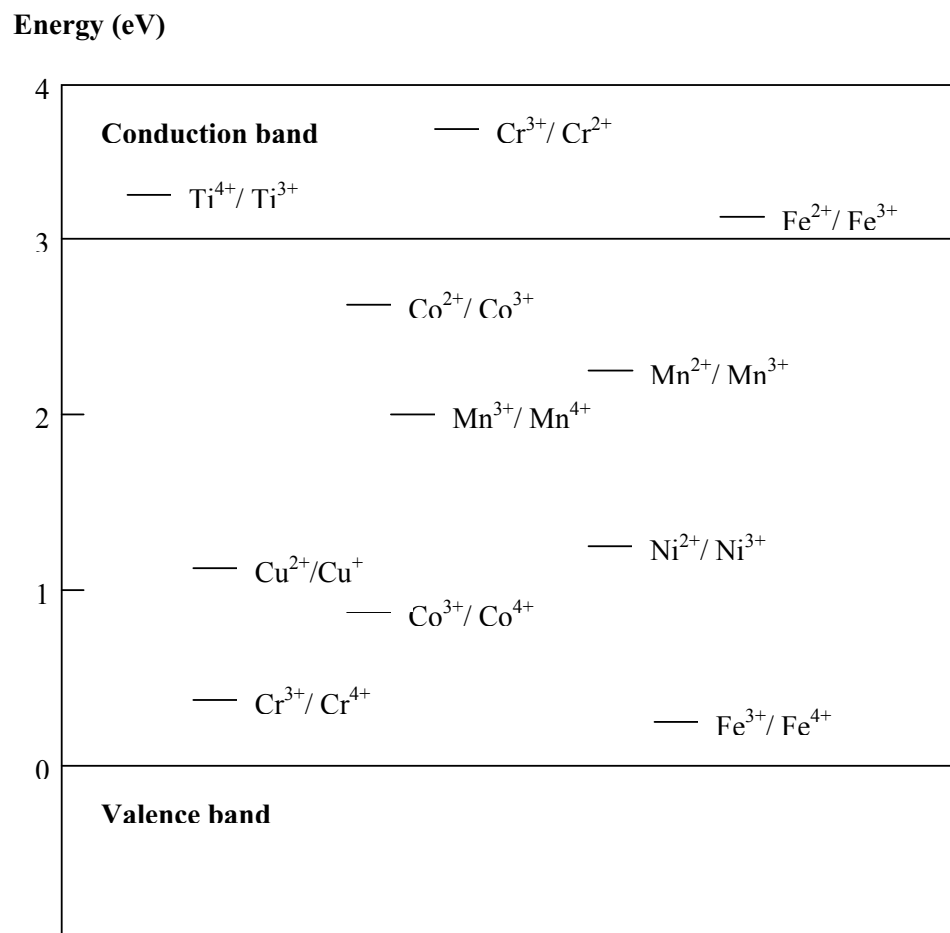

**Figure 1.5:** Energy levels of dopant ions (Litter, 1996). Energy level of Zn<sup>2+</sup> was not available.

The introduction of such energy levels in the band gap will induce a red shift (lower energy) in the band gap transition and the visible light absorption through a charge transfer between a dopant and CB (or VB) or a d-d transition in the crystal field (Choi, 1994). The incorporation of metal ions into TiO<sub>2</sub> crystal lattice, therefore, can significantly extend the absorption by the photocatalysts into the visible region.





It should be stressed that dopants should act as both electron traps and hole traps to be photoactive (Choi, 1994). Trapping either electron or hole alone is ineffective because the immobilized charge species quickly recombines with its mobile counterparts. The photoactivity of doped TiO<sub>2</sub> photocatalyst, however, substantially depends on the dopant ion nature and concentration, besides the preparation method and the thermal and reductive treatment (Malati, 1984).

### 1.3.3 Reaction Pathway





Titanium dioxide photocatalytic technology has been widely studied as a potential method for the purification of water and air contaminated with various pollutants. It is well established that hydroxyl radical implicated as the reactive species in the photocatalytic oxidation of many organic compounds in liquid-solid systems as well as in gaseous phase systems (Phillips, 1992) are formed through the capture of holes, by surface water molecules and/or hydroxyl ions or surface titanol groups (Hoffman, 1995). These reactive •OH species can readily oxidize organic substrate absorbed on the catalyst surface.

Hydroxyls are formed as a result of dissociative chemisorption of H<sub>2</sub>O onto the Ti<sup>4+</sup> sites and water can be physisorbed on the surface hydroxyl groups via hydrogen bonding (Raupp, 1985). Oxidative electron transfer occurs exclusively through these surface bound hydroxyl radical or equivalent trapped hole species. In a gas solid system, however, since water molecules are not the predominant species in contact with the catalyst in the gas phase, direct oxidation may occur via the valence band hole as the organic substrate can themselves act as adsorbed traps for the



photogenerated holes (Alberici, 1997; Shang, 2002). The role of hydroxyl groups is now established as traps for photogenerated valence band holes thereby retarding the electron-hole recombination. The reaction of hole in the heterogeneous photocatalytic can be express by the following set of equations (Hoffmann, 1995)



$\text{D}_{\text{ads}}$  is an electron donor species generally the organic compounds adsorbed on the catalyst and oxidized to  $\text{D}^+_{\text{ads}}$  when reacted with the  $h^+$  in  $\text{TiO}_2$ . In the presence of oxygen,  $\text{O}_2$ , superoxides ( $\text{O}_2^-$ ) ions are also generated. This species subsequently react with protons and adsorbed  $\text{H}_2\text{O}$  from the hydrated surface produces hydroperoxide radicals,  $\text{HO}_2\bullet$ , which is another source of OH radicals (Herrmann, 1979; Augugliaro, 1999).



Sopyan *et al.* (Sopyan, 1996) have confirmed the production of  $\text{H}_2\text{O}_2$  by the reduction of  $\text{O}_2$  using a microelectrode technique. The hydrogen peroxide production is subsequently followed by hydroxyl radical-forming reaction such as equation (1.12) and (1.13).





Or via direct photolysis (Sopyan, 1996)



These OH radicals, being deficient of one electron, are electrophiles capable of migrating and carrying out oxidative destruction of organic molecules absorbed on the catalyst surface (Linsebigler, 1995). In fact, the destruction of organic molecules via the mechanism of radical attack is the hallmark of advanced oxidation process.

### 1.3.4 Kinetic Study

Reaction kinetics gives information about the reaction rates and the mechanisms by which the reactants are converted to the products. To photocatalytic oxidation, the rate law was used to predict reaction rate. Theoretically, the reaction rate can be simply expressed as the decreasing rate of any of the reactants or the increasing rate of any of the products against time. A common way to express the reaction rate is to use the rate law:  $\text{rate} = -d[\text{A}]/dt = k[\text{A}]^n$ , where  $k$  is the rate constant,  $n$  is the order of the reaction and  $[\text{A}]$  is the concentration of reactant A. The reaction rate of photocatalytic oxidation represents the efficiency of photooxidation reaction and it can be influenced by such factors as humidity, light intensity, contaminant concentration and oxygen concentration.

A necessary step of a photocatalytic reaction is that the reactant molecules are adsorbed on the catalyst surface. The fact that only adsorbed species can be oxidized makes the adsorption process very important in the photocatalytic oxidation process. The Langmuir-Hinshelwood (L-H) mechanism for surface catalysis is widely used to describe the heterogeneous gas-solid reaction. These mechanisms consist of four different steps *i.e.* adsorption from the gas-phase, desorption to the gas-phase, dissociation of molecules at the surface and reactions between adsorbed molecules. With this reaction mechanism, the reacting components at the active centers of the catalyst must be adsorbed. This L-H model has been shown to provide a quantitative kinetics treatment of many solid gas reactions (Jacoby, 1995; Nimlos, 1996; Alberici,

1997; Bouzaza, 2002, Shang, 2002; Zhao, 2003). It includes the assumption that the Langmuir adsorption isotherm is valid for the surface reaction.

In general, the kinetics of heterogeneous catalysis would follow the L-H model, in which the reaction rate ( $r$ ) of a unimolecular surface reaction varies proportionally with the surface coverage ( $\theta$ ) as:

$$r = k\theta = \frac{kKC}{1 + KC} \quad (1.15)$$

$$\frac{1}{r} = \left( \frac{1}{kKC} + \frac{1}{k} \right) \quad (1.16)$$

where,  $k$  and  $K$  are the reaction rate constant and the adsorption equilibrium constant, and  $C$  is the concentration of VOCs (Ollis, 1991). A linear plot of the reciprocal value of the initial rate ( $1/r$ ) against the reciprocal values of the organic compound initial concentration ( $1/C_0$ ) gives  $k$  as the L-H rate constant and  $K$  as the Langmuir adsorption constant of the VOCs in the photocatalytic degradation reaction. Although in the presence of water vapour, OH groups are present on the  $\text{TiO}_2$  surface and their contribution to photooxidation cannot be discarded, the preliminary adsorption of organic compound is very important pre-requisite for highly efficient detoxification.

Pseudo-first-order reaction can be resulted from the L-H rate equation only when the term  $KC_0$  is much less than 1 ( $KC \ll 1$ ). L-H equation is often applied to evaluate the L-H rate constant  $k$  and the adsorption constant  $K$ , but it is only valid at the initial stage. During the photocatalytic process, intermediates are formed and their  $KC$  terms must be included in the L-H rate equation even when their adsorption on the  $\text{TiO}_2$  surface may be rather weak. For simplicity, however, it is better to employ the initial VOCs rate for the application of the equation. This can be done by an assumption that at initial time interval, the intermediate concentration can be considered to be negligible. Definitely, such an initial time interval should be as short as possible. In practice, however, a considerable error in the analysis would be made easily for such a small conversion of the substrate. So for this study the initial rate will be calculated for the first 15 minutes of the reaction time.

### 1.3.5 TiO<sub>2</sub> Thin Film

Most studies in heterogeneous photocatalytic oxidation of organic contaminants either in air or aqueous solution have been performed with powder TiO<sub>2</sub> particularly in anatase form (Pruden, 1983; Hisanaga, 1990; Peral, 1992; Alberici, 1997). However, several practical problems with using powders in photochemical processing are apparent. In aqueous phase reaction, the separation of the catalyst from the suspension after the reaction is difficult. The suspended particles also tend to aggregate, especially when they are present at high concentrations. Particulate suspensions are also not easily applicable to continuous flow systems.

In a packed bed photoreactor used for gas phase photooxidation, the distribution of the catalyst in the reactor is not uniform due to the non-uniform sizes and shapes of the photocatalysts particles. As a result most of the catalyst is probably not illuminated by the UV light, especially the portion in the interior of the porous particles (Fu, 1995). This so-called “shadowing effect” has also been observed in previous studies (Wei, 1991).

In order to alleviate these problems, the engineering properties of TiO<sub>2</sub> must be improved and several approaches have been taken by researchers in this field. One of the most widely used techniques is to immobilize the TiO<sub>2</sub> as thin film on various supports including glass, stainless steel, quartz, silica gel and glass beads.

The idea of immobilizing TiO<sub>2</sub> in the form of thin film was first recognized by Fujishima and Honda (Fujishima, 1972). They found that the thin film photocatalysts have a lower surface area than powdered form, resulting in a lower photocatalytic activity. However, several researches collected data later showed that thin film TiO<sub>2</sub> had a porous structure and exhibited high photoactivity towards organic degradation. Since then TiO<sub>2</sub> thin film emerged as a plausible photocatalyst in environmental applications. TiO<sub>2</sub> immobilized on various supports can be separated from the effluent much easier than its powder form (Anderson, 1995) and it can eliminate the problem of shadowing effect.

TiO<sub>2</sub> thin films have been prepared by variety of deposition techniques such as chemical vapor deposition (Babelon, 1998), reactive sputtering (Mardare, 2002; Liu, 2002), atomic layer deposition (Aarik, 2000), filtered arc deposition (Bendavid, 2000), pulse laser deposition (Sumita, 2002) and spray pyrolysis (Abou-Helal, 2002; Castaneda, 2002). However, the sol-gel method is the most commonly used method for the preparation of thin film (Sopyan, 1996; Noguchi, 1998; Xu, 1999a; Zorn, 2000; Blount, 2001).

Thin films formed using sol-gel technique (Brinker, 1991a) represent the oldest commercial application of sol-gel technology. In the sol-gel process a solution containing titanium-alkoxide is first prepared. The solution is then hydrolyzed to produce crystalline TiO<sub>2</sub> colloids. The sol-gel derived thin films are generally prepared by the dip- or spin coating of solutions of precursor molecules or sol solutions on substrates, followed by drying and heating process. This procedure can be repeated to increase the number of TiO<sub>2</sub> layer and its thickness. The quality of the resulting thin film is largely dependent not only on the properties of the coating solution (density, viscosity) but also on the pulling or spinning speed (Brinker, 1991). However, thin film by dipping used little raw materials and may be processed quickly without cracking, overcoming most of the disadvantages of sol-gel processing. In addition large substrate may be accommodated and it is possible to uniformly coat both sides of planar and axially symmetric substrates. Research on the use of TiO<sub>2</sub> thin film as a photocatalyst in air treatment however is very few but the modest data collected is sufficient enough to show that TiO<sub>2</sub> thin film has high photocatalytic efficiency in the photocatalytic oxidation of various VOCs.

### **1.3.6 Limitations of TiO<sub>2</sub>**

Most of heterogeneous photocatalysis report of the last decade, have dealt with aqueous solutions, exploring water decontamination and purification by the photoassisted oxidative destruction of hazardous solutes (Chemseddine, 1990; Hidaka, 1992; Herrmann, 1999; Fabiyi, 2000; Tanaka, 2000; Axelsson, 2001). Studies involving gas phase heterogeneous photocatalysts are far fewer, but the

modest existing literature has been demonstrated that near-UV illumination in concert with anatase titanium dioxide ( $\text{TiO}_2$ ) powdered photocatalyst and molecular oxygen can carry out the complete oxidation of a wide range of organic compounds.

However, most of the researches on gas phase photocatalysis have focused only on low concentration VOCs. Peral (1997) even suggested that heterogeneous photocatalysis is a promising new technology for the removal of dilute levels of organic contaminants in air rather than highly concentrated volatile organics. As the concentration of VOCs is higher in an industrialized area, a new improved  $\text{TiO}_2$  catalyst that can destroy both low and high concentration of VOCs is therefore needed.

Heterogeneous catalytic oxidation technology for gas phase pollution control has well been established in automotive exhaust and catalytic incineration. However, nearly all heterogeneous oxidations catalyst functions at elevated temperatures, whereas nearly all inhabited atmospheres of concern to humans exist at or near 20-25°C. A need, therefore exist for an air purification catalyst which can not only function at ambient conditions of temperature and pressure, but can also use the mildest and most prevalent oxidant, molecular oxygen ( $\text{O}_2$ ) and is active against the broadest possible range of contaminant structures (Hager, 2000).

Photocatalysis oxidation of VOCs using  $\text{TiO}_2$  has shown great potential in the field of air treatment. It gives a rapid and efficient destruction of a wide spectrum of low-level air pollutants (Hoffman, 1995). However, the light usable in the photocatalytic reaction of  $\text{TiO}_2$  is limited to light with wavelength lower than 400 nm (Fujishima, 1999). Materials that can use visible light would be more desirable in terms of the effective utilization of ordinary light. For that reason, the current research on  $\text{TiO}_2$  has been focused on catalyst modification, in the effort to search for a semiconductor that supports photocatalytic reactions with high efficiency and with the use of visible light.

There is also a growing interest in the use of thin transparent films of  $\text{TiO}_2$  as a sensitizer for the photodestruction of gaseous organic species, thereby generating a photodeodorizing surface, but also thin film that can generate a self cleaning surface.

The later film could find application in self-cleaning windows and automotive windshields. Such TiO<sub>2</sub> films need to be clear (*i.e.* they must not scatter visible light), adherent (with an abrasion resistance which is sufficient to withstand cleaning or impact by dust particles) and photoactive. The photoactivity must be such that it is greater than the rate of deposition, otherwise it will become fouled with UV-adsorbing non-volatile partial oxidation products.

#### **1.4 Research Objectives**

The aim of this research is to develop a photocatalyst with high photoactivity, which is stable and capable of degrading and mineralizing a wide class of recalcitrant VOCs using ultra violet light. The specific objectives of this research are:

- To develop transparent thin film TiO<sub>2</sub> photocatalyst with excellent photocatalytic activity.
- To improve the photoactivity of the thin film by doping with metal ions.
- To degrade noxious gases to non-toxic gases using the prepared TiO<sub>2</sub> and modified TiO<sub>2</sub> thin film.
- To study the chemical, physical and optical properties of the photocatalysts in terms of their chemical content, morphology and band-gap energy.
- To study the mineralization of VOCs during the photooxidation process using undoped and doped TiO<sub>2</sub>.

#### **1.5 Scope of Study**

This research is focused in developing a photocatalyst with high photocatalytic activities to degrade only gas phase hydrocarbons. The scopes of this study are listed below.

- The introduction of dopants (transition metal ions) into TiO<sub>2</sub> catalyst to enhance the photocatalytic activity of TiO<sub>2</sub>.
- The photodegradation testing of VOCs gases are conducted at laboratory scale using home built photocatalysis reactor.
- The characterization studies such as film surface morphology, elemental analysis and band-gap values will be carried out.
- The volatile organic compounds under study are benzene, acetone, toluene, *m*-xylene and tetrachloroethylene.
- The photocatalytic studies will be carried out under ambient temperature and pressure.

## REFERENCES

- Aarik, J., Aidla, A., Uustare, T., Ritala, M. and Leskela. (2000). "Titanium isopropoxide as a precursor for atomic layer deposition: characterization of titanium dioxide growth process." *Applied Surface Science*. **161**. 385-395.
- Abou-Helal, M.O. and Seeber, W.T. (2002). "Preparation of TiO<sub>2</sub> thin films by spray pyrolysis to be used as a photocatalyst." *Applied Surface Science*. **195**. 53-62.
- Alberici, R.M. and Jardim, W.F. (1997). "Photocatalytic destruction of VOCs in the gas phase using titanium dioxide." *Applied Catalysis B: Environmental*. **14**. 55-68.
- Amama, P.B., Itoh, K. and Murabayashi, M. (2001). "Photocatalytic oxidation of trichloroethylene in humidified atmosphere." *Journal of Molecular Catalysis A: Chemical*. **176**. 165-172.
- Amor, S.B., Baud, G., Jacquet, M. and Pichon, N. (1998). "Photoprotective titania coatings on PET substrates." *Surface and Coatings Technology*. **102**. 63-72.
- Anderson, C. and Bard, A.J. (1995). "An improved photocatalyst of TiO<sub>2</sub>/SiO<sub>2</sub> prepared by a sol-gel synthesis". *Journal of Physical Chemistry*. **99**. 9882-9885
- ATSDR, "Agency for Toxic Substances and Disease Registry". (1997). "Toxicological Profile for tetrachloroethylene." Atlanta, GA: U.S. Department of Health and Human Services, Public Health Service.
- ATSDR, "Agency for Toxic Substances and Disease Registry". (1994).



“Toxicological Profile for acetone.” Atlanta, GA: U.S. Department of Health and Human Services, Public Health Service.

ATSDR, “Agency for Toxic Substances and Disease Registry”. (1995).

“Toxicological Profile for xylenes.” Atlanta, GA: U.S. Department of Health and Human Services, Public Health Service.

ATSDR, “Agency for Toxic Substances and Disease Registry”. (2000).

“Toxicological Profile for toluene.” Atlanta, GA: U.S. Department of Health and Human Services, Public Health Service.

Augugliaro, V., Coluccia, S., Loddo, V., Marchese, L., Martra, G., Palmisano and L., Schiavello, M. (1999). “Photocatalytic oxidation of gaseous toluene on anatase TiO<sub>2</sub> catalyst: mechanistic aspects and FT-IR investigation.” *Applied Catalysis B: Environmental*. **20**. 15-27.

Avila, P., Bahamonde, A., Blanco, J., Sanchez, B., Cardona, A.I. and Romero, M. (1998). “Gas-phase photo-assisted mineralization of volatile organic compounds by monolithic titania catalysts.” *Applied Catalysis B: Environmental*. **17**. 75-88.

Avila, P., Sanchez, B., Cardona, A.I., Rebollar, M. and Candal, R. (2002).

“Influenced of the methods of TiO<sub>2</sub> incorporation in monolithic catalysts for the photocatalytic destruction of chlorinated hydrocarbons in gas phase.” *Catalysis Today*. **76**. 271-278.

Axelsson, A-K. and Dunne, L.J. (2001). “Mechanism of photocatalytic oxidation of 3,4-dichlorophenol on TiO<sub>2</sub> semiconductor surfaces.” *Journal of Photochemistry and Photobiology A: Chemistry*. **144**. 205-213.

Babelon, P., Dequiedt, A.S., Mostefa-Sba, H., Bourgeois, S., Sibillot, P. and Sacilotti, M. (1998). “SEM and XPS studies of titanium dioxide thin films grown by MOCVD.” *Thin Solid Films*. **322**. 63-67.

- Bendavid, A., Martin, P.J. and Takikawa, H. (2000). "Deposition and modification of titanium dioxide thin films by filtered arc deposition." *Thin solid Films*. **360**. 241-249.
- Blount, M.C. and Falconer, J.L. (2001). "Characterization of adsorbed species on TiO<sub>2</sub> after photocatalytic oxidation of toluene." *Journal of Catalysis*. **200**. 21-33.
- Bouzaza, A. and Laplanche, A. (2002). "Photocatalytic degradation of toluene in gas phase: comparative study of some TiO<sub>2</sub> supports." *Journal of Photochemistry and Photobiology A: Chemistry*. **150**. 207-212.
- Brickley, R.I., Munuera, G. and Stone, F.S. (1973). "Photoadsorption and photocatalysis at rutile surface II: Photocatalytic oxidation of isopropanol." *Journal of Catalysis*, **31**. 398-407.
- Brinker, C.J. and Scherer, G.W. (1990). "Sol-gel Science." New York: Academic Press.
- Brinker, C.J., Frye, G.L., Hurd, A.J. and Ashlet, C.S. (1991a). "Fundamentals of sol-gel dip coating." *Thin Solid Films*. **201**. 97-108.
- Brinker, C.J., Hurd, A.J., Frye, G.C., Schunk, P.R. and Ashley, C.S. (1991b). "Sol-gel Thin Film Formation." *The Ceramic Society of Japan*. **99** (10). 862-877.
- Cao, L., Gao, Zi., Suib, S.L., Obee, T.N., Hay, S.O. and Freihaut, J.D. (2000). "Photocatalytic oxidation of toluene on nanoscale TiO<sub>2</sub> catalysts: Studies of deactivation and regeneration." *Journal of Catalysis*. **196**. 253-261.
- Castaneda, L., Alonso, J.C., Ortiz, A., Andrade, E., Saniger, J.M. and Banuelos, J.G. (2002). "Spray pyrolysis deposition and characterization of titanium oxide thin films." *Materials Chemistry and Physics*. **77**. 938-944.
- Cavani, F., Koutyrev, M., Trifiro, F., Bartolini, A., Ghisletti, D., Iezzi, R., Santucci,

- A. and Del Piero, G. (1996). "Chemical and physical characterization of alumina-supported chromia-based catalysts and their activity in dehydrogenation of isobutane." *Journal of Catalysis*. **158**. 236-250.
- Chao, H.E., Yun, Y.U., Xiangfang, H.U. and Larbot, A. (2003). "Effect of silver doping on the phase transformation and grain growth of sol-gel titania powder." *Journal of the European Ceramic Society*. **23**. 1457-1464.
- Chemseddine, A. and Boehm, H.P. (1990). "A study of the primary step in the photochemical degradation of acetic acid and chloroacetic acids on a TiO<sub>2</sub> photocatalyst." *Journal of Molecular Catalysis*. **60**. 295-311.
- Chen, C.H., Kelder, E.M. and Schoonman, J. (1999). "Electrostatic sol-spray deposition (ESSD) and characterization of nanostructured TiO<sub>2</sub> thin films." *Thin Solid Films*. **342**. 35-41.
- Choi, W., Ko, J.K., Park, H. and Chung, J.S. (2001). "Investigation on TiO<sub>2</sub>-coated optical fibers for gas-phase photocatalytic oxidation of acetone." *Applied Catalysis B: Environmental*. **31**. 209-220.
- Choi, W., Termin, A. and Hoffmann, R. (1994). "The Role of Metal Ion Dopants in Quantum-Sized TiO<sub>2</sub>: Correlation between Photoreactivity and Charge Carrier Recombination Dynamics." *Journal of Physical Chemistry*. **98**. 13669-13679.
- Coronado, J.M., Zorn, M.E., Tejedor-Tejedor, I. and Anderson, M.A. (2003). "Photocatalytic oxidation of ketones in the gas phase over TiO<sub>2</sub> thin films: a kinetic study on the influence of water vapor." *Applied Catalysis B: Environmental*. Article in press.
- Cox, P.A. (1992). "Transition Metal Oxides: An Introduction to their Electronic Structure and Properties." Oxford: Clarendon Press. 121-123.
- D'Hennezel, O. and Ollis, D.F. (1997). "Trichloroethylene-promoted photocatalytic

oxidation of air contaminants.” *Journal of Catalysis*. **167**. 118-126.

D’Hennezel, O., Pichat, P. and Ollis, D.F. (1998). “Benzene and toluene gas-phase photocatalytic degradation over H<sub>2</sub>O and HCl pretreated TiO<sub>2</sub>: by-products and mechanisms.” *Journal of Photochemistry and Photobiology. A: Chemistry*. **118**. 197-204..

Da Silva, R.C., Alves, E. and Cruz, M.M. (2002). “Conductivity behaviour of Cr implanted TiO<sub>2</sub>.” *Nuclear Instruments and Methods in Physics Research B*. **191**. 158-162.

Department of Environment Malaysia. Ministry of Science, Technology and The Environment. (1998). “Malaysia Environmental Quality Report 1998: Executive Summary.”

Di Paola, A., Gracia-Lopez, E., Ikeda, S., Marci, G., Ohtani, B. and Palmisano, L. (2002). “Photocatalytic degradation of organic compounds in aqueous systems by transition metal doped polycrystalline TiO<sub>2</sub>.” *Catalysis Today*. **75**. 87-93.

Dibble, L.A. and Raupp, G.B. (1990). “Kinetics of the gas-solid heterogeneous photocatalytic oxidation of trichloroethylene by near UV illuminated titanium dioxide.” *Catalysis Letter*. **4**. 345-354.

Dibble, L.A. and Raupp, G.B. (1992). “Fluidized-bed photocatalytic oxidation of trichloroethylene in contaminated airstreams.” *Environmental Science Technology*. **26**. 492-495.

Djehri, N. and Teichner, S.J. (1980). “Heterogeneous photocatalysis: the photooxidation of 2-methylbutane.” *Journal of Catalysis*. **62**.99-106.

Djehri, N., Formenti, M., Juillet, F. and Teichner, S.J. (1974). “Photointeraction on the Surface of Titanium Dioxide between Oxygen and Alkanes.” *Faraday Discuss. Chem. Soc.* **58**. 185-193.

- Dvoranova, D., Brezova, V., Mazuir, M. and Malati, M.A. (2002). "Investigations of metal-doped titanium dioxide photocatalysts." *Applied Catalysis B: Environmental*. **37**. 91-105.
- Ebina, T, Iwasaki, T., Chatterjee, A., Hatagiri, M., Stucky, G.D. (1997). "Comparative study of XPS and DFT with reference to the distribution of Al in tetrahedral and octahedral sheets of phyllosilicate." *Journal of Physical Chemistry B*. **101**. 1125-1129.
- Einaga, H., Futamura, S. and Ibusuki, T. (2002). "Heterogeneous photocatalytic oxidation of benzene, toluene, cyclohexene and cyclohexane in humidified air: comparison of decomposition behaviour on photoirradiated TiO<sub>2</sub> catalyst." *Applied Catalysis B: Environmental*. **38**. 215-225.
- Fabiyi, M.E. and Skelton, R.L. (2000). "Photocatalytic mineralisation of methylene blue using buoyant TiO<sub>2</sub>-coated polystyrene beads." *Journal of Photochemistry and Photobiology. A: Chemistry*. **132**. 121-128.
- Fisherman, J. (1991). "The global consequences of increasing tropospheric ozone concentrations." *Chemosphere*. **22**. 685-695.
- Fox, M.A. and Dulay, M.T. (1993). "Heterogeneous Photocatalysis." *Chemical Review*. **93**. 341-357.
- Fu, X., Zeltner, W.A. and Anderson, M.A. (1995). "The gas-phase photocatalytic mineralization of benzene on porous titania-based catalysts." *Applied Catalysis B: Environmental*. **6**. 209-224.
- Fujishima, A. and Honda, K. (1972). "Electrochemical photolysis of water at a semiconductor electrode." *Nature*. **238**. 37-38.
- Fujishima, A., Hashimoto, K. and Watanabe, T. (1999). "TiO<sub>2</sub> Photocatalysis Fundamentals and Applications." First Edition. Japan. BKC, Inc.

- Gracia, F., Holgado, J.P., Yubero, F. and Gonzales-Elipe, A.R. (2002). "Phase mixing in Fe/TiO<sub>2</sub> thin films prepared by ion beam-induced chemical vapour deposition: optical and structural properties." *Surface and Coatings Technology*. **158-159**. 552-557.
- Gravelle, P.C., Juillet, F., Meriaudeau, P. and Teichner, S. (1971). "Surface reactivity of reduced titanium dioxide." *Faraday Discuss. Chem. Soc.* **52**. 140.
- Hager, S. and Bauer, R. (1999). "Heterogeneous Photocatalytic Oxidation of Organics for Air Purification by Near UV Irradiated Titanium Dioxide." *Chemosphere*. **38**. 1549-1559.
- Hager, S., Bauer, R. and Kudielka, G. (2000). "Photocatalytic oxidation of gaseous chlorinated organics over titanium dioxide." *Chemosphere*. **41**. 1219-1225.
- He, C., Yu, Y., Hu, X. and Larbot, A. (2002). "Influence of silver doping on the photocatalytic activity of titania films." *Applied Surface Science*. **200**. 239-247.
- Heller, A. (1995). "Chemistry and applications of photocatalytic oxidation of thin organic films." *Acc. Chem. Res.* **28**. 503-508.
- Herrmann, J.M., Disdier, J., Mozzanega, M-N. and Pichat, P. (1979). "Heterogeneous Photocatalysis: In situ photoconductivity study of TiO<sub>2</sub> during oxidation of isobutane into acetone." *Journal of Catalysis*, **60**. 369-377.
- Herrmann, J-M., Disdier, J. and Pichat, P. (1984). "Effect of Chromium Doping on the Electrical and Catalytic Properties of Powder Titania Under UV and Visible Illumination." *Chemical Physics Letter*. **108**. 618-622.
- Herrmann, J-M., Tahiri, H., Ait-Ichou, Y., Lassaletta, G., Gonzalez-Elipe, A.R. and Fernandez, A. (1997). "Characterization and photocatalytic activity in aqueous medium of TiO<sub>2</sub> and Ag-TiO<sub>2</sub> coatings on quartz." *Applied catalysis B: Environmental*. **13**. 219-228.

- Herrmann, J.-M., Tahiri, H., Guillard, C. and Pichat, P. (1999). "Photocatalytic degradation of aqueous hydroxy-butandioic acid (malic acid) in contact with powdered and supported titania in water." *Catalysis Today*. **54**. 131-141.
- Hidaka, H., Nohara, K. and Zhao, J. (1992). "Photo-oxidative degradation of the pesticide permethrin catalysed by irradiated TiO<sub>2</sub> semiconductor slurries in aqueous media." *J. Photochem. Photobiol. A: Chemistry*. **64**. 247-254.
- Hiramoto, M., Hashimoto, K. and Sakata, T. (1987). "Electron transfer and photoluminescence dynamics of CdS particles deposited on porous vycor glass." *Chem. Phys. Letter*. **133**. 440-444.
- Hisanaga, T., Harada, K. and Tanaka, K. (1990). "Photocatalytic degradation of organochlorine compounds in suspended TiO<sub>2</sub>." *Journal of Photochemistry and Photobiology A: Chemistry*. **54**. 113-118.
- Hoffman, M.R., Martin, S.T., Choi, W. and Bahnemann, D.W. (1995). "Environmental Applications of Semiconductor Photocatalysis." *Chemical Review*. **95**. 69-96.
- Hoflund, G.B. and Epling, W.S. (1997). "Oxidation study of a polycrystalline Ni/Cr alloy I: room-temperature exposure to O<sub>2</sub>." *Thin Solid Films*. **307**. 126-132.
- Ibusuki, T and Takeuchi, K. (1986). "Toluene Oxidation on UV Irradiated Titanium Dioxide With and Without O<sub>2</sub>, NO<sub>2</sub> or H<sub>2</sub>O at Ambient Temperature." *Atmospheric Environment*. **20**. 1711-1715.
- Ivanova, T., Harizanova, A., Surtchev, M. and Nenova, Z. (2003). "Investigation of sol-gel derived thin films of titanium dioxide doped with vanadium oxide." *Solar Energy Materials & Solar Cells*. **76**. 591-598.
- Jacoby, W.A., Blake, D.M., Fennel, J.A., Boulter, J.E., Vargo, L.M., George, M.C. and Dolberg, S.K. (1996). "Heterogeneous Photocatalysis for Control of Volatile

Organic Compounds in Indoor Air.” *J. Air & Waste Manage. Assoc.* **46**. 891-898.

Jacoby, W.A., Blake, D.M., Noble, R.D. and Koval, C.A. (1995). “Kinetics of the Oxidation of Trichloroethylene in Air via Heterogeneous Photocatalysis.” *Journal of Catalysis*. **157**. 87-96.

Jacoby, W.A., Nimlos, M.R. and Blake, D.M. (1994). “Products, Intermediates, Mass Balances, and Reaction Pathways for the Oxidation of Trichloroethylene in Air via Heterogeneous Photocatalysis.” *Environ. Sci. Technol.* **28**. 1661-1668.

Japer, S.M., Wallington, T.J., Rudy, S.J. and Chang, T.Y. (1991). “Ozone-forming potential of a series of oxygenated organic compounds.” *Environmental Science Technology*. **25**. 415.

Jones, A.P. (1999). “Indoor air quality and health”. *Atmospheric Environment*. **33**. 4535-4564.

Kang, M., Lee, J.H., Lee, S-H., Chung, C-H., Yoon, K.J., Ogino, K., Miyata, S. and Choung, S-J. (2003). “Preparation of TiO<sub>2</sub> films by the MOCVD method and analysis for decomposition of trichloroethylene using in situ FT-IR spectroscopy.” *Journal of Molecular Catalysis A: Chemical*. **193**. 273-283.

Karakitsou, K.E. and Verykios, X.E. (1993). “Effects of Altrivalent Cation doping on TiO<sub>2</sub> on its performance as a photocatalyst for water cleavage.” *Journal of Physical Chemistry*. **97**. 1184-1189.

Kim, J-S., Itoh, K. and Murabayashi, M. (1998). “Photocatalytic Degradation of trichloroethylene in the Gas-Phase Over TiO<sub>2</sub> sol-Gel Films: Analysis of Products.” *Chemosphere*. **36**. 483-495.

Ku, Y., Ma, C-M. and Shen, Y-S. (2001). “Decomposition of gaseous trichloroethylene in a photoreactor with TiO<sub>2</sub> coated nonwoven fiber textile.”



*Applied Catalysis B: Environmental*. **34**. 181-190.

- Kumar, P.M., Badrinarayanan, S. and Sastry, M. (2000). "Nanocrystalline TiO<sub>2</sub> studied by optical, FTIR and X-ray photoelectron spectroscopy: correlation to presence of surface states." *Thin Solid Films*. **358**. 122-130.
- Lambert, J.B., Shurvell, H.F., Lightner, D.A. and Cooks, R.G. (1998). "Organic Structural Spectroscopy." New Jersey. Prentice Hall. 346-386.
- Legrand-Buscema, C., Malibert, C. and Bach, S. (2002). "Elaboration and characterization of thin films of TiO<sub>2</sub> prepared by sol-gel process." *Thin Solid Films*. **418**. 79-84.
- Lin, H., Kumon, S., Kozuka, H. and Yoko, T. 1998. "Electrical properties of sol-gel derived transparent titania films doped with ruthenium and tantalum." *Thin Solid Films*. **315**. 266-272.
- Linsebigler, A.L., Lu, G. and Yates, J.Y. (1995). "Photocatalysis on TiO<sub>2</sub> Surfaces: Principles, Mechanisms and Selected Results." *Chem. Rev.* **95**. 735-758.
- Litter, M.I. and Navio, J.A. (1996). "Photocatalytic properties of iron-doped titania semiconductor." *Journal of Photochemistry and Photobiology A: Chemistry*. **98**. 171-181.
- Liu, F-M., and Wang, T-M. (2002). "Surface and optical properties of nanocrystalline anatase titania films grown by radio frequency reactive magnetron sputtering." *Applied Surface Science*. **195**. 284-290.
- Ma, H., Berthier, Y. and Marcus, P. (1999). "AES, XPS, and TDS study of the adsorption and desorption of NH<sub>3</sub> on ultra-thin film chromium oxide films formed on chromium single crystal surfaces." *Applied Surface Science*. **153**. 40-46.

- Maira, A.J., Yeung, K.L., Soria, J., Coronado, J.M., Belver, C., Lee, C.Y. and Augugliaro, V. (2001). "Gas-phase photo-oxidation of toluene using nanometer-size TiO<sub>2</sub> catalyst." *Applied Catalysis B: Environmental*. **29**. 327-336.
- Malati, M.A. and Wong, W.K. (1984). "Doping TiO<sub>2</sub> For Solar Energy Applications." *Surface Technology*. **22**. 305-322.
- Mardare, D. (2002). "Optical constant of heat treated TiO<sub>2</sub> thin films." *Materials Science and Engineering*. **95**. 83-87.
- Mardare, D., Tasca, M., Delibas, M. and Rusu, G.I. (2000). "On the structural properties and optical transmittance of TiO<sub>2</sub> r.f. sputtered thin film." *Applied Surface Science*. **156**. 200-206.
- Martra, G., Colussia, S., Marchese, L., Augugliaro, V., Loddo, Palmisano, L. and Schiavello, M. (1999). "The role of H<sub>2</sub>O in the photocatalytic oxidation of toluene in vapour phase on anatase TiO<sub>2</sub> catalyst – A FTIR study." *Catalysis Today*. **53**. 695-702.
- Morrison, R.T. and Boyd, R.N. (1987). "Organic Chemistry." 5<sup>th</sup> edition. Boston, MA. Allyn and Bacon. 886.
- Negishi, N., Iyoda, T., Hashimoto, K. and Fujishima, A. (1995). "Preparation of Transparent TiO<sub>2</sub> Thin Film Photocatalyst and Its Photocatalytic Activity." *Chemistry Letters*. 841-842.
- Nimlos, M.R., Jacoby, W.A., Blake, D.M., Milne, T.A. (1993). "Direct Mass Spectroscopy Studies of the Destruction of Hazardous Wastes. 2. Gas-Phase Photocatalytic Oxidation of Trichloroethylene over TiO<sub>2</sub>: Products and Mechanisms." *Environmental Science Technology*. **27**. 732-740.
- Nimlos, M.R., Wolfrum, E.J., Brewer, M.L., Fennell, J.A. and Bintner, G. (1996). "Gas-Phase Heterogeneous Photocatalytic Oxidation of Ethanol: Pathways and

Kinetic Modelling.” *Environmental Science Technology*. **30**. 3102-3110

Noguchi, T., Fujishima, A., Sawunyama, P. and Hashimoto, K. (1998).

“Photocatalytic degradation of gaseous formaldehyde using TiO<sub>2</sub> film.”

*Environmental Science Technology*. **32**.3831-3833.

Norback, D., Bjornsson, E., Janson, C., Widstrom, J. and Boman, G. (1995).

“Asthma and indoor environment: the significance of emission of formaldehyde and volatile organic compounds from newly painted indoor surfaces.”

*Occupational and Environmental Medicine*. **52**. 388-395.

Obee, T.N. and Brown, R.T. (1995). “TiO<sub>2</sub> Photocatalysis for Indoor Air

Applications: Effect of Humidity and Trace Contaminant Levels on the

Oxidation Rates of Formaldehyde, Toluene, and 1,3-Butadiene.” *Environment*

*Science Technology*. **29**. 1223-1231.

Oh, S-M., Kim, S-S., Lee, J. E., Ishigaki, T. and Park, D-W. (2003a). “Effect of

additives on photocatalytic activity of titanium dioxide powders synthesized by thermal plasma.” *Thin Solid Films*. **435**. 252-258.

Oh, S.H., Kim, D.J., Hahn, S.H. and Kim, E.J. (2003b). “Comparison of optical and

photocatalytic properties of TiO<sub>2</sub> thin films prepared by electron-beam evaporation and sol-gel dip-coating.” *Materials Letters*. Article in Press.

Ollis, D.F., Pelizzetti, E. and Serpone, N. (1991). “Destruction of water

contaminants.” *Environmental Science Technology*. **25**. 1523-1529.

Palmisano, L., Augugliaro, V., Sclafani, A. and Schiavello, M. (1988). “Activity of

Chromium-Ion-Doped Totania for the Dinitrogen Photoreduction to Ammonia

and for the Phenol Photodegradation.” *Journal of Physical Chemistry*. **92**. 6710-

6713.

Pang Hin Yue.. “Killing us softly with benzene.” New Straits Time Press.

Wednesday, 23 October, 1996.

Papaefthimou, P., Ioannides, T. and Verykios, X.E. (1998). "Performance of doped Pt/TiO<sub>2</sub> (W<sup>6+</sup>) catalyst for combustion of VOCs." *Applied Catalysis B: Environment*. **15**. 75-92.

Park, D.R., Zhang, J.L., Ikene, K., Yamashita, H. and Anpo, M. (1999). "Photocatalytic Oxidation of Ethylene to CO<sub>2</sub> and H<sub>2</sub>O on ultrafine powdered TiO<sub>2</sub> photocatalysts in the presence of O<sub>2</sub> and H<sub>2</sub>O." *Journal of Catalysis*. **185**. 114-119.

Pelizzetti, E. and Minero, C. (1999). "Role of oxidative and reductive pathways in the photocatalytic degradation of organic compounds." *Colloids and Surfaces. A: Physicochemical and Engineering Aspects*. **151**. 321-327.

Peral, J. and Ollis, D.F. (1992). "Heterogeneous Photocatalytic Oxidation of gas-phase organics for Air Purification: Acetone, 1-Butanol, Butyraldehyde, Formaldehyde, and m-Xylene oxidation." *Journal of Catalysis*. **136**. 554-565.

Peral, J., Domenech, X. and Ollis, D.F. (1997). "Heterogeneous photocatalysis for purification, decontamination and deodorization of air." *J. Chem. Technol. Biotechnol.* **70**. 117-140.

Phillips, L.A. and Raupp, G.B. (1992). "Infrared spectroscopic investigation of gas-solid heterogeneous photocatalytic oxidation of trichloroethylene." *Journal of Molecular Catalysis*. **77**. 297-311.

Pichat, P., Disdier, J., Hong-Van, C., Goutailler, G. and Gaysse, C. (2000). "Purification/deodorization of indoor air and gaseous effluents by TiO<sub>2</sub> photocatalysis." *Catalysis Today*. **63**. 363-369.

Pruden, L. and Ollis, D.F. (1983). "Photoassisted heterogeneous catalysis: the degradation of trichloroethylene in water." *Journal of Catalysis*. **82**. 404-417.

- Rahman, M.M., Krishna, K.M., Soga, T., Jimbo, T. and Umeno, M. (1999). "Optical properties and X-ray photoelectron spectroscopic study of pure and Pb-doped TiO<sub>2</sub> thin films." *Journal of Physics and Chemistry of Solids*. **60**. 201-210.
- Rampaul, A., Parkin, I.P., O'Neil, S.A., DeSouza, J., Mills, A. and Elliott, N. (2003). "Titania and tungsten doped titania thin film on glass; active photocatalysts." *Polyhedron*. **22**. 35-44.
- Ranjit, K.T. and Viswanathan, B. 1997. Synthesis, Characterization and Photocatalytic of Ion Doped TiO<sub>2</sub> Catalysts. *Journal of Photochemistry and Photobiology A: Chemistry*. **108**. 79-79.
- Raupp, G.B. and Dumesic, J.A. (1985). "Adsorption of CO, CO<sub>2</sub>, H<sub>2</sub> and H<sub>2</sub>O on titanis surfaces with different oxidation states." *Journal of Physical Chemistry*. **89**. 5240-5246.
- Renz, C. (1921). "Photo-reactions of the oxides of titanium, cerium and earth-acids." *Helv. Chim. Acta*, **4**. 961
- Rothenberger, G., Moser, J., Gratzel, M., Serpone, N. and Sharma, D.K. (1985). "Charge Carrier Trapping and Recombination Dynamics in Small Semiconductor Particles." *J. Am. Chem. Soc.* **107**. 8054-8059.
- Sanhueza, E., Hisatsune, I.C. and Heicklen, J. (1976). "Oxidation of haloethylenes." *Chemical Reviews*. **76**. 801-826.
- Schrauzer, G.N. and Guth, T.D. (1977). "Photolysis of Water and Photoreduction of Nitrogen on Titanium Dioxide." *J. Am. Chem. Soc.* **99**. 7188-7193.
- Serpone, N. and Pelizzetti, E., Eds., (1989). Photocatalysis – Fundamentals and Applications, Wiley Interscience, New York, 99
- Shang, J., Du, Y. and Xu, Z. (2002). "Photocatalytic oxidation of heptane in the gas-

phase over TiO<sub>2</sub>.” *Chemosphere*. **46**. 93-99.

Sopyan, I., Watanabe, M., Murasawa, S., Hashimoto, K. and Fujshima, A. (1996).

“An efficient TiO<sub>2</sub> thin film photocatalyst: photocatalytic properties in gas phase acetaldehyde degradation.” *Journal of Photochemistry and Photobiology A: Chemistry*, **98**. 79-86

Sumita, T., Yamaki, T., Yamamoto, S. and Miyashita, A. (2002). “Photo-induced surface charge separation of highly oriented TiO<sub>2</sub> anatase and rutile thin film.” *Applied Surface Science*. Article in Press.

Takeda, S., Suzuki, S., Odaka, H. and Hosono, H. (2001). “Photocatalytic TiO<sub>2</sub> thin film deposited onto glass by DC magnetron sputtering.” *Thin Solid Films*. **392**. 338-344.

Tanaka, K., Padermpole, K. and Hisanaga, T. (2000). “Photocatalytic degradation of commercial azo dye.” *Water Research*. **34**. 327-333.

Tang, H., Berger, H., Schmid, P.E., Levy, F. (1993). “Photoluminescence in TiO<sub>2</sub> Anatase Single Crystals.” *Solid State Communications*. **87**. 847-850.

Tang, H., Prasad, K., Sanjines, R., Schmid, P.E. and Levy, F. (1994). “Electrical and optical properties of TiO<sub>2</sub> anatase thin film.” *Journal of Applied Physics*. **75**. 2024-2047.

Toyozawa, Y. (1976). “Elementary Processes in Luminescence.” *Journal of Luminescence*. **12-13**. 13-21.

Toyozawa, Y. (1980). “Relaxation of Elementary Excitations.” (Edited by R. Kubo & E. Hansmura). New York: Springer-Verlag. 3-10.

Tseng, I-H, Chang, W-C and Wu, J.C.S. (2002). “Photoreduction of CO<sub>2</sub> using sol-gel derived titania and titania-supported copper catalysts.” *Applied Catalysis B*:

*Environmental*. **37**. 37-48.

Umebayashi, T., Yamaki, T., Itoh, H. and Asai, K. (2002). "Analysis of electronic structures of 3d transition metal-doped TiO<sub>2</sub> based on band calculations."

*Journal of Physics and Chemistry of Solids*. **63**. 1909-1920.

Vorontsov, A.V., Barannik, G.B., Snegurenko, O.I., Savinov, E.N. and Parmon, V.N. (1997). "Complete Heterogeneous Photocatalytic Oxidation of Acetone, Ethanol, and Diethyl Ether Vapors with Air over Honeycom-supported TiO<sub>2</sub>."

*Kinetics and Catalysis*. **38**. 97-101.

Wadge, A. and Salisbury, J. (1997). "Benzene." National Environmental Health Forum Monographs. Air Series No. 2" South Australia.

Wagner, C. and Muilnberg, G. (1979). "Handbook of X-ray Photoelectron Spectroscopy." Physical Electronics Division. Eden Prairie. Perkin-Elmer Corporation.

Walsh, M.P. (1999). "Motor vehicle pollution control. Global progress and remaining problems." Paper presented at 1<sup>st</sup> International Conference Health Effects of Vehicle Emissions. London.

Wang, K-H., Tsai, H-H. and Hsieh, Y-H. (1998). "The kinetics of photocatalytic degradation of trichloroethylene in gas phase over TiO<sub>2</sub> supported on glass bead." *Applied Catalysis B: Environmental*. **17**. 313-320.

Wang, T.M., Zheng, S.K., Hao, W.C. and Wang, C. (2002a). "Studies on photocatalytic activity and transmittance spectra of TiO<sub>2</sub> thin films prepared by r.f. magnetron sputtering method." *Surface and Coatings Technology*. **155**. 141-145.

Wang, W and Ku, Y. (2003). "Photocatalytic degradation of gaseous benzene in air streams by using an optical fiber photoreactor." *Journal of Photochemistry and*

*Photobiology A: Chemistry*. **159**. 47-59.

Wang, X-P., Yu, Y., Hu, X-F. and Gao, L. (2000). "Hydrophilicity of TiO<sub>2</sub> films prepared by liquid phase deposition." *Thin Solid Films*. **371**. 148-152.

Wang, Z., Helmersson, U. and Kall, P-O. (2002b). "Optical properties of anatase TiO<sub>2</sub> thin films prepared by aqueous sol-gel process at low temperature." *Thin Solid Films*. **405**. 50-54.

Wei, T-Y and Wan, C-C. (1991). "Heterogeneous photocatalytic oxidation of phenol with titanium dioxide powders." *Ind. Eng. Chem. Res.* **30**. 1293-1300.

Wilke, K. and Breuer, H.D. (1999). "The influence of transition metal doping on the physical and photocatalytic properties of titania." *Journal of Photochemistry and Photobiology A: Chemistry*. **121**. 49-53.

Wilkinson, C.F. (1987). "Being more realistic about chemical carcinogenesis". *Environmental Science Technology*. **21** (9). 843-847.

Wolkoff, P. and Nielsen, G.D. (2001). "Organic compounds in indoor air - their relevance for perceived indoor air quality?" *Atmospheric Environment*. **35**, 4407-4417

Xu, J-H and Shiraishi, F. (1999). "Photocatalytic decomposition of acetaldehyde in air over titanium dioxide." *Journal of Chemical Technology and Biotechnology*. **74**. 1096-1100.

Xu, W. and Raftery, D. (2001). "In Situ Solid-state Nuclear Magnetic Resonance Studies of Acetone Photocatalytic Oxidation on Titanium Oxide Surfaces." *Journal of Catalysis*. **204**. 110-117.

Xu, Y., Zheng, W. and Liu, W. (1999). "Enhanced photocatalytic activity of supported TiO<sub>2</sub>: dispersing effect of SiO<sub>2</sub>." *Journal of Photochemistry and Photobiology A: Chemistry*. **122**. 57-60



- Yamazaki, S., Tsukamoto, H., Araki, K., Tanimura, T., Tejedor-Tejedor, I. and Anderson, M.A. (2001). "Photocatalytic degradation of gaseous tetrachloroethylene on porous TiO<sub>2</sub> pellets." *Applied Catalysis B: Environmental*. **33**. 109-117.
- Yamazaki-Nishida, S., Fu, X., Anderson, M.A. and Hori, K. (1996). "Chlorinated byproducts from the photoassisted catalytic oxidation of trichloroethylene and tetrachloroethylene in the gas phase using porous TiO<sub>2</sub> pellets." *Journal of Photochemistry and Photobiology A: Chemistry*. **97**. 175-179.
- Yamazaki-Nishida, S., Nagano, K.J., Phillips, L.A., Cervera-March, S. and Anderson, M.A. (1993). "Photocatalytic degradation of trichloroethylene in the gas-phase using titanium dioxide pellets." *Journal of Photochemistry and Photobiology A: Chemistry*. **70**. 95-99.
- Yu, J., Zhao, X. and Zhao, Q. (2001a). "Photocatalytic activity of nanometer TiO<sub>2</sub> thin films prepared by the sol-gel method." *Materials Chemistry and Physics*. **69**. 25-29.
- Yu, J., Zhao, X., Zhao, Q. and Wang, G. (2001b). "Preparation and characterization of super-hydrophilic porous TiO<sub>2</sub> coating films." *Materials Chemistry and Physics*. **68**. 253-259.
- Yuan, Z., Jia, J. and Zhang, L. (2002). "Influence of co-doping of Zn(II) + Fe(III) on the photocatalytic activity of TiO<sub>2</sub> for phenol degradation." *Materials Chemistry and Physics*. **73**. 323-326.
- Zhang, F., Wolf, G.K., Wang, X. and Liu, X. (2001). "Surface properties of silver doped titanium oxide films." *Surface and Coatings Technology*. **148**. 65-70.
- Zhao, J. and Yang, X. (2003). "Photocatalytic oxidation for indoor air purification: a literature review." *Building and Environment*. **38**. 645-654

Zorn, M.E., Tompkins, D.T., Zeltner, W. and Anderson, M.A. (2000). "Catalytic and photocatalytic oxidation of ethylene on titania-based thin-films." *Environmental Science Technology*. **34**. 5206-5210.