

12th Global Conference on Sustainable Manufacturing

Production of Sustainable Energy by Carbon Nanotube/Platinum Catalyst in Microbial Fuel Cell

Elnaz Halakoo^a, Alireza Khademi^b, Mostafa Ghasemi^c, Noordin Mohd Yusof^b,
Rasoul Jamshidi Gohari^a, Ahmad Fauzi Ismail^{a,*}

^aAdvanced Membrane Technology Research Centre (AMTEC), Universiti Teknologi Malaysia (UTM), 81310 Johor Bahru, Malaysia

^bDept. of Materials, Manufacturing & Industrial Engineering, Faculty of Mechanical Engineering, Universiti Teknologi Malaysia (UTM), 81310 Johor Bahru, Malaysia

^cFuel Cell Institute, Universiti Kebangsaan Malaysia (UKM), 43600 UKM Bangi, Selangor, Malaysia

* Corresponding author. Tel.: +60 7 553 5592; fax: +60 7 558 1463. E-mail address: afauzi@utm.my, fauzi.ismail@gmail.com

Abstract

Platinum (Pt) is the most efficient and common cathode catalyst that is being applied in fuel cell technology, especially in microbial fuel cells (MFCs). However, its high price makes its use uneconomical in MFCs. Even though there are some other types of new catalysts, their performance could not compete with Pt. This is the main reason why scientists spend all their efforts to decrease the amount of Pt by making some composite of Pt for their use in MFCs thus making it viable and more economical. In this study, carbon nanotube-platinum (CNT/Pt) nanocomposite has been fabricated as a novel cathode catalyst in MFCs and its performance was compared with platinum in MFCs system. The CNT/Pt was synthesized by using the in situ method, and the performance is being compared in terms of power density generation in different concentration. The results have shown that CNT is a suitable support for catalyst in MFCs and CNT/Pt generally has better performance than Pt in MFCs. This can be due to better interaction with oxygen in the cathode chamber and high catalytic activity of CNT/Pt for oxygen reduction reaction. The potential of CNT/Pt nanocomposite in generating electricity from MFCs has been demonstrated and this can be a sustainable source of energy for the future.

© 2015 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license

(<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Peer-review under responsibility of Assembly Technology and Factory Management/Technische Universität Berlin.

Keywords: Carbon nanotube-platinum (CNT/Pt); Nanocomposite; Microbial fuel cell (MFC); Power density

1. Introduction

The depletion of non-renewable energy sources like fossil fuels and the changes in climate have encouraged scientists to work on finding new alternatives source of energy [1,2]. Fuel cells are energy converting devices with low or zero emission and high efficiency [3]. Microbial fuel cell (MFC) is one of the prominent fuel cells, which converts organic matter such as sugar to electrical energy by using bacteria as biocatalyst [4]. It means that MFCs generate electricity and treat wastewater simultaneously. MFCs consist of anode and cathode chambers that are separated by a proton exchange membrane (PEM) [5]. Electrons are produced in the anode chamber, while there are electron acceptors in the cathode chamber to accept the electrons and complete the circuit [6]. However, until now, there are different problems in making

MFCs economical. The most important challenge is the cost of the Platinum (Pt) that is used as cathode catalyst for accelerating the rate of oxygen reduction reaction (ORR) as it represents more than half of the price of MFCs [7]. So many are trying to replace or decrease the amount of Pt or even use low-cost and stable non-noble metals as cathode catalyst in order to make it more economical [8]. Nowadays, nanostructured carbon-based materials, especially carbon nanotubes (CNTs) are increasingly used as catalyst and its support due to their high surface area [9], high mechanical strength [10], high electrical conductivity [11] and catalytic activity [12]. Higher catalytic activity of CNTs based materials may be due to high surface area that causes better dispersion of materials as well as more places for functionalization and bonds. Reddy et al. [13] studied carbon nanotube based MFCs in membrane electrode assembly

(MEA) system. From their work it was concluded that functionalization of CNTs improved adhesion of Pt on its surface. Yuan et al. [14] studied amino functionalized multi-walled CNTs (MWCNT) as support for iron phthalocyanine cathode. They concluded MWCNT is an efficient support of the catalyst for ORR. Wang et al. [15] used carbon nanotube in their modified air cathode chamber of MFC. They concluded that the power produced by CNT was more than double to that of traditional carbon cloth cathodes. Ghasemi et al. [16] also fabricated and applied chemical activated carbon nanofiber (ACNF) in MFC. They found that chemical activated CNF has better power per cost than Pt and is more economical and applicable for real system.

In the present study, we designed an MFC which is inoculated by using activated palm oil mill effluent (POME) in anode chamber to get the highest power density by CNT/Pt nanocomposite electrode with just 25% Pt and 75% CNT.

2. Material and methods

2.1. MFC construction and operation

Two cylindrical and H-shaped chambers were constructed using Plexiglas material with a diameter of 6.2 cm and a length of 14 cm and were separated with Nafion 117, which acted as the proton exchange membrane (PEM). Oxygen was fed to the cathode continuously by an air pump (80 ml/min). Both the cathode and the anode surface area were noted to be 12 cm² and MFC was operated at ambient temperature and neutral pH (6.5-7) in anode and cathode [17,18]. The pH was adjusted by using the phosphate buffer solution. Plain carbon paper was used as the anode and carbon paper coated by different concentrations of Pt and CNT/Pt were used as the cathode. The schematic diagram of MFC is shown in the Fig. 1.

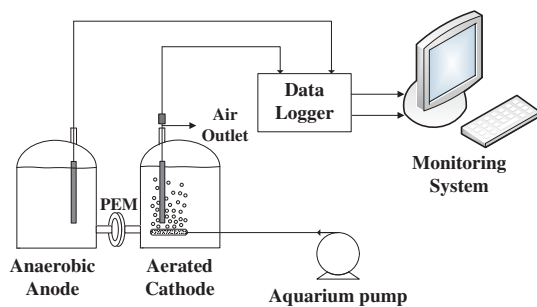


Fig. 1. Schematic representation and photograph of the fabricated MFC

Palm oil mill effluent (POME), anaerobic sludge (Selangor, Malaysia) was used to inoculate the reactor in the anode chamber. The media contained 5 g of glucose, 0.5 g of yeast extract, 0.2 g of KCl, 1 g of NaH₂PO₄·4H₂O, 3 g of NH₄Cl, 4 g of NaHCO₃ (Merck), 10 ml solution of Wolfe's mineral and 10 ml of Wolfe's vitamin solution were added per litre [19].

2.2. Electrode preparation

2.2.1. CNT electrode

CNTs are inert without any functionalization and do not have any positive effects. To functionalize, the CNTs were ultrasonicated in a 3:1 concentrated H₂SO₄ and HNO₃ solution for three hours. Next, the required amount of CNT (0.5 mg/cm²) was dispersed in the small amount of ethanol. This resulted in a stable dispersed CNT ink solution. The ink was brushed on the surface of carbon paper and then dried at 100°C for one hour, in order to eliminate any residual water.

2.2.2. Pt electrode

Pt was first washed with deionized water, filtered, and then dried. The required amount of Pt was then dispersed in the small amount of Nafion solution, to produce a Pt ink. This ink was then dispersed on to carbon paper (CP) uniformly, and the electrode was then dried in an oven for one hour at 100°C.

2.2.3. CNT/Pt composite nanocomposite electrode

A chemical reduction technique was used to produce CNT/Pt. First, CNT was ultrasonicated in nitric acid for approximately three hours. Then, the sample was dried and washed with deionized water several times, and then air-dried. The dried sample was then ultrasonicated with acetone for one hour and a 0.075 molar H₂PtCl₆ solution was added slowly during stirring. After 24 hours, the mixture was reduced using a 1 M NaOH and 0.1 M NaBH₄ solution. When the mixture was ready, it would be washed by deionized water and dried at 80°C for six hours [20].

2.3. Analysis and calculation

The current and power produced by the system was calculated using equations (1) and (2), respectively.

$$I = V/R \quad (1)$$

$$P = R \times I^2 \quad (2)$$

Where I is the current (ampere), V is the voltage (volt), R is the external resistance (Ω) and P is the power (watt) produced by the system.

3. Results and discussion

Fig. 2 shows the surface morphology of the carbon paper anode electrode at the end of the process, where a biofilm can be seen to be attached on the anode surface. The image obtained confirmed that different types of bacteria can easily be attached on CP anode electrode surface and have a significant role in the catalytic activity of the electrode [21,22]. It proves that a biofilm covered the electrode surface that acted as a biocatalyst for the production of bioelectricity and transfer of produced electron to the electrode surface.

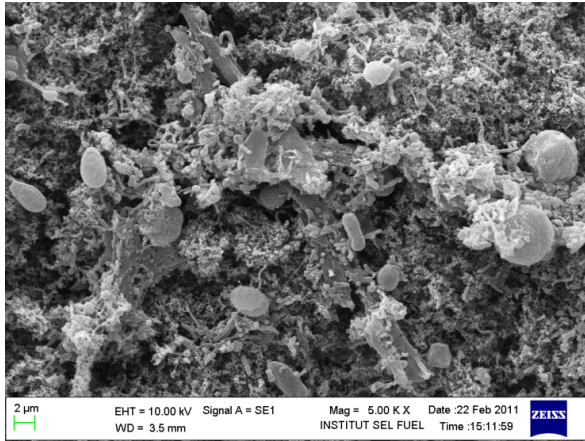


Fig. 2. SEM image of the attachment of microorganism on the electrode surface

The power density graphs of different MFCs are shown in Fig. 3 and Fig. 4. Fig. 3 depicts the power density of MFC with Pt electrode having different concentration of Pt. From Fig. 3, the maximum power density of neat CP is 44.7 mW/m² at 172.66 mA/m². After coating of Pt on the CP surface, power densities were increased. The cathode with 0.1 mg/cm² has maximum power density of 53.44 mW/m². The catalytic power of the cathode increased when the amount of Pt elevated to 0.2 mg/cm² and reached to 73.01 mW/m² at 246.67 mA/m². After that the power density increased slightly and reached to 75.95 (251.58), 77.028 (327.08) and 84.01 mW/m² (341 mA/m²) for 0.3 mg/cm², 0.4 mg/cm² and 0.5 mg/cm², respectively.

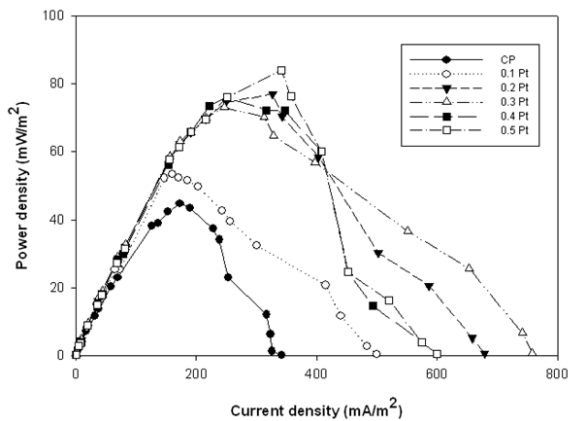


Fig. 3. Power density graph for Pt electrode

Fig. 4 shows the power density of different nanocomposite electrodes consist of Pt attached on CNT surface. The content of CNT/Pt composite coated on the CP is same as Pt. The generated power density and current density were increased in all cases. The power generation of electrode with 0.1 mg/cm² CNT/Pt was 73.48 mW/m² at 221.33 mA/m². The power was elevated by 1.7 times and reach to 124.99 mW/m² at 288.66

mA/m². The power achieved for the other three nanocomposite electrodes is approximately same and is 143.11 (445.83), 146.01 (312) and 147.1 mW/m² (285.556 mA/m²) for 0.3 mg/cm², 0.4 mg/cm² and 0.5 mg/cm², respectively.

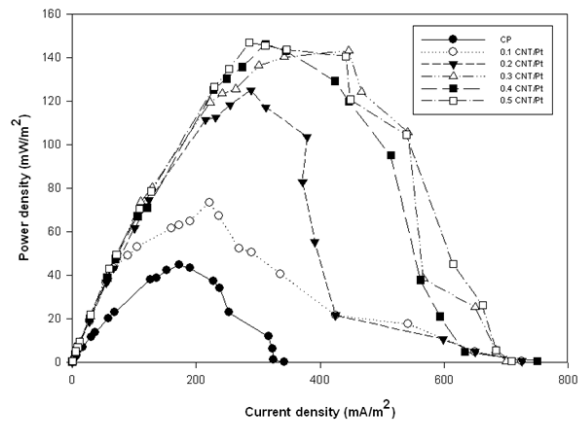


Fig. 4. Power density graph of CNT/Pt electrode

4. Conclusions

In the present study, the potential of CNT/Pt nanocomposite in generating electricity from MFC has been demonstrated. The CNT/Pt nanocomposite electrode upgraded the power production of MFCs and decreased the cost of cathode materials. This can be a sustainable source of electricity supply. CNTs with high surface area provided an enhanced condition for ORR to improve the efficiency of the cathode. So our next efforts should focus on application of other nanomaterials and nanocomposites in MFCs to make the cost of MFC cheaper with high performance.

Acknowledgements

Financial support from the Ministry of Higher Education (MOHE) and Universiti Teknologi Malaysia (UTM) through vote R.J130000.7824.4L804 is acknowledged with gratitude.

References

- [1] Shaffer G, Olsen SM, Pedersen JOP. Long-Term Ocean Oxygen Depletion in Response to Carbon Dioxide Emissions from Fossil Fuels. *Nat. Geosci* 2009;2:105-109.
- [2] Shafiee S, Topal E. When Will Fossil Fuel Reserves Be Diminished. *Energy Policy* 2009; 37:181-189.
- [3] Jang JK. Construction and Operation of a Novel Mediator- and Membrane-Less Microbial Fuel Cell. *Process Biochem* 2004; 39:1007-1012.
- [4] Yuan Y. Iron Phthalocyanine Supported on Amino-Functionalized Multi-Walled Carbon Nanotube as an Alternative Cathodic Oxygen Catalyst in Microbial Fuel Cells. *Bioresour Technol* 2011;102:5849-5854.
- [5] Kim JR, Cheng S, Oh SE, Logan BE. Power Generation Using Different Cation, Anion, and Ultrafiltration Membranes in Microbial Fuel Cells. *Environ Sci Technol* 2007; 41:1004-1009.
- [6] HaoYu E, Cheng S, Scott K, Logan B. Microbial Fuel Cell Performance With Non-Pt Cathode Catalysts. *J Power Sources* 2007;171: 275-281.

- [7] Lefebvre O, Ooi WK, Tang Z, Abdullah-Al-Mamun M, Chua DH, Ng HY. Optimization of a Pt-Free Cathode Suitable for Practical Applications of Microbial Fuel Cells. *Bioresour Technol* 2009;100: 4907-4910.
- [8] Kerzenmacher S, Ducree J, Zengerle R, Von Stetten F. Energy Harvesting By Implantable Abiotically Catalyzed Glucose Fuel Cells. *J Power Sources*. 2008; 182:1-17.
- [9] Baughman RH, Zakhidov AA, De Heer WA. Carbon Nanotubes-The Route Toward Applications. *Science* 2002; 297: 787.
- [10] Meincke O, Kaempfer D, Weickmann H, Friedrich C, Vathauer M, Warth H. Mechanical Properties and Electrical Conductivity of Carbon-Nanotube Filled Polyamide-6 and its Blends with Acrylonitrile/Butadiene/Styrene. *Polymer* 2004; 45: 739-748.
- [11] Berber S, Kwon YK, Tománek D. Unusually High Thermal Conductivity of Carbon Nanotubes. *Phys Rev Lett* 2000; 84: 4613-4616.
- [12] Gong K, Du F, Xia Z, Durstock M, Dai L. Nitrogen-Doped Carbon Nanotube Arrays with High Electrocatalytic Activity for Oxygen Reduction. *Science* 2009; 323: 760.
- [13] Reddy ALM, Ramaprabhu S. Design and Fabrication of Carbon Nanotube-Based Microfuel Cell and Fuel Cell Stack Coupled with Hydrogen Storage Device. *Int J Hydrogen Energy* 2007;32: 4272-4278.
- [14] Yuan Y, Zhao B, Jeon Y, Zhong S, Zhou S, Kim S. Iron Phthalocyanine Supported on Amino-Functionalized Multi-Walled Carbon Nanotube as an Alternative Cathodic Oxygen Catalyst in Microbial Fuel Cells. *Bioresour Technol*, 2011;102: 5849-5854.
- [15] Wang H, Wu Z, Plaseied A, Jenkins P, Simpson L, Engtrakul C, Ren Z. Carbon Nanotube Modified Air-Cathodes for Electricity Production in Microbial Fuel Cells. *J Power Sources*, 2011.
- [16] Ghasemi M, Shahgaldi S, Ismail M, Kim BH, Yaakob Z, Daud WRW. Activated Carbon Nanofibers as an Alternative Cathode Catalyst To Platinum in a Two-Chamber Microbial Fuel Cell. *Int J Hydrogen Energy* 2011; 36:13746-13752.
- [17] Zhao F, Harnisch F, Schroder U, Scholz F, Bogdanoff P, Herrmann I. Application of Pyrolysed Iron (II) Phthalocyanine and Cotmp Based Oxygen Reduction Catalysts as Cathode Materials in Microbial Fuel Cells. *Electrochem Commun* 2005;7:1405-1410.
- [18] Kim HJ, Park HS, Hyun MS, Chang SI, Kim M, Kim BH. A Mediator-Less Microbial Fuel Cell Using a Metal Reducing Bacterium, *Shewanella Putrefaciens*. *Enzyme Microb Technol* 2002;30: 145-152.
- [19] Trinh NT, Park JH, Kim BW. Increased Generation of Electricity in a Microbial Fuel Cell Using *Geobacter Sulfurreducens*. *Korean J Chem Eng* 2009; 26:748-753.
- [20] Xu L, Zhu Y, Tang L, Yang X, Li C. Biosensor Based on Self Assembling Glucose Oxidase and Dendrimer Encapsulated Pt Nanoparticles on Carbon Nanotubes for Glucose Detection. *Electroanalysis* 2007;19:717-722.
- [21] Tang X, Du Z, Li H. Anodic Electron Shuttle Mechanism Based on 1-Hydroxy-4-Aminoanthraquinone in Microbial Fuel Cells. *Electrochem Commun* 2010;12:1140-1143.
- [22] Tang X, Guo K, Li H, Du Z, Tian J. Microfiltration Membrane Performance in Two-Chamber Microbial Fuel Cells. *Biochem Eng J* 2010;52:194-198.