

INTEGRATION OF CERAMIC MEMBRANE THROUGH 3D PRINTING
TECHNOLOGY

LIM CHIN HWA

UNIVERSITI TEKNOLOGI MALAYSIA

INTEGRATION OF CERAMIC MEMBRANE THROUGH 3D PRINTING
TECHNOLOGY

LIM CHIN HWA

A project report submitted in partial fulfilment of the
requirements for the award of the degree of
Master of Science (Mechanical-Advanced Manufacturing Technology)

Faculty of Mechanical Engineering
Universiti Teknologi Malaysia

JANUARY 2016

I strongly dedicated this project to my beloved father (Lim Kiok Meng), mother (Rina Lestari) and my siblings (Lim Chin Siang and Lim Hui Kheng), with their sincere prayers and endless support afforded me to successfully accomplish this thesis.

ACKNOWLEDGEMENT

I wish to express my deepest gratitude to my project supervisor Dr. Norhayati Ahmad and my co-supervisor Mr. Khidzir Bin Zakaria, for their exceptional guidance and endless motivation throughout the entire course of this project. Special thanks to Dr. Uday M. Basheer Al-Naib for his valuable suggestions and precious knowledges. My sincere appreciation for their constant support and advice that greatly helped me until this project completed.

The contributions and cooperation from the staff and technicians in University Teknologi Malaysia is greatly appreciated. They are Mr. Reduan from Design Laboratory, Faculty of Mechanical, Miss Rosmawati Ahmad from Geotechnic Laboratory, Faculty of Civil Engineering, Mr. Jefri Samin and Mr. ayub from FESEM lab Faculty of Mechanical, Miss Farah Diana from Institute of Bioproduct Development, and Madam Anisah Salikin from Material Analysis Laboratory, Faculty of Sains, who have been involved directly and indirectly in the completion of this project.

Finally, I would like to thank for my beloved family and friends who have provided assistance, support, faith and encouragement to attain my goals in this project.

ABSTRACT

In this paper, 3D printing technology was being presented for its compatibility with ceramic materials due to its competitive process in terms of cost and speed, especially for the small quantities production. There were four types of ceramic membrane samples used in this study, which differ in their powder particle sizes and membrane shapes. They were 72 μ without hole (1a), 72 μ with hole (1b), 133 μ without hole (2a), and 133 μ with hole (2b). This paper presents the research effort that focuses on integration of ceramic powder with 3D printing technology in order to produce an effective ceramic membrane and characterize them on its physical, structural, and functional properties. Sample 1 has small particle size that results in small open (0.806cm³) and closed porosity (0.808cm³), which causes a higher bulk density (1.362g/cm³) if compared with sample 2, which has the open porosity (0.919cm³), closed porosity(1.127cm³) and bulk density (1.351g/cm³). The smaller particle forms an interconnecting structure that can trap the water molecules and increases the water absorption. The water absorption was 36.67% in sample 1 higher than that (33.24%) for sample 2. The 3D printing produces a ceramic membrane with an inhomogeneous structure which cause a deviation in its filtration rate. However, the membrane hole shape enhances the filtration rate by more than 50%, which is from 107.4ml/min to 171.1ml/min. The filtration rate was decreased with the treatment duration from 1 to 5 minutes due to the accumulation of particulate matters. The ceramic membrane with hole (1b and 2b) can improve the decreasing of filtration rate by 64.85% to 70.64% for particle size between 72 μ to 133 μ . The cleaning of the membrane was characterize by spectra detected by EDX and it shows an effectiveness in order to remove the accumulation of the particular matters after the backwash process. Among the samples, the ceramic membrane 1b has a higher efficiency in terms of chemical oxygen demand (COD) and total suspended solid (TSS), which were achieved 98.33% reduction in COD and 46.15% in TSS.

ABSTRAK

Dalam kertas ini, teknologi percetakan 3D telah dibentangkan untuk keserasian dengan bahan-bahan seramik kerana proses ini kompetitif dari segi kos dan kelajuan, terutamanya untuk pengeluaran kuantiti yang kecil. Terdapat empat jenis sampel membran seramik digunakan dalam kajian ini, ia berbeza dari segi saiz zarah serbuk dan bentuk membran. Ia terdiri daripada 72 μ tanpa lubang (1a), 72 μ dengan lubang (1b), 133 μ tanpa lubang (2a), dan 133 μ dengan lubang (2b). Kertas kerja ini membentangkan usaha penyelidikan yang memberi tumpuan kepada integrasi serbuk seramik dengan teknologi percetakan 3D untuk menghasilkan membran seramik yang berkesan dan menguji membran dengan sifat-sifat fizikal, struktur, dan fungsi. Sampel 1 mempunyai saiz zarah yang kecil yang menyebabkan keliangan terbuka (0.806cm³) dan keliangan tertutup (0.808cm³) yang kecil, ia menyebabkan ketumpatan pukal yang lebih tinggi (1.362g/cm³) jika dibandingkan dengan sampel 2 yang mempunyai keliangan terbuka (0.919cm³), keliangan tertutup (1.127cm³) dan ketumpatan pukal (1.351g / cm³). Zarah yang lebih kecil mempunyai struktur bersambung yang boleh memerangkap molekul air dan meningkatkan penyerapan air. Penyerapan air adalah 36,67% dalam sampel 1 (72 μ) lebih tinggi daripada sampel 2 (133 μ) yang mempunyai penyerapan air sebanyak 33.24%. Percetakan 3D menghasilkan membran seramik dengan struktur tak homogen yang menyebabkan penyelewengan dalam kadar penapisan itu. Walau bagaimanapun, bentuk lubang membran meningkatkan kadar penapisan lebih daripada 50%, iaitu dari 107.4ml/min ke 171.1ml/min. Kadar penapisan telah berkurangan dengan tempoh masa rawatan tersebut daripada 1 hingga 5 minit disebabkan oleh pengumpulan partikulat. Membran seramik dengan lubang (1b dan 2b) boleh meningkatkan penurunan kadar penapisan daripada 64.85% kepada 70.64% untuk saiz zarah antara 72 μ untuk 133 μ . Pembersihan membran dicirikan oleh spektrum yang dikesan oleh EDX dan ia menunjukkan keberkesanan dalam usaha untuk menghapuskan pengumpulan partikulat tertentu selepas proses pencucian terbalik. Di

antara sampel-sampel itu, membran seramik 1b mempunyai kecekapan yang lebih tinggi dari segi Keperluan Oksigen Kimia (KOK) dan Jumlah Pepejal Terampai (JPT), iaitu boleh mencapai pengurangan sebanyak 98.33% untuk COD dan 46.15% untuk TSS.

TABLE OF CONTENTS

CHAPTER	TITLE	PAGE
	DECLARATION	ii
	DEDICATION	iii
	ACKNOWLEDGEMENT	iv
	ABSTRACT	v
	ABSTRAK	vi
	TABLE OF CONTENTS	viii
	LIST OF TABLES	x
	LIST OF FIGURES	xi
	LIST OF SYMBOLS	xiii
	LIST OF APPENDICES	xiv
1.	INTRODUCTION	1
	1.1. Background of Study	1
	1.2. Problem Statement	3
	1.3. Objective of The Research	5
	1.4. Research Question	5
	1.5. Scope	6
	1.6. Significant of Study	6
2.	LITERATURE REVIEW	9
	2.1. Additive Manufacturing	9
	2.2. 3D Printing	13
	2.3. 3D Printing Advantages and Disadvantages	15
	2.4. 3D Printing Application	18

2.5.	3D Printing with Particle Characterization	21
2.6.	3D Printing with Ceramic Membrane	25
2.7.	Ceramic Membrane Efficiency	26
2.8.	Market Opportunity	30
2.9.	Sustainable Manufacturing	31
3.	METHODOLOGY	33
3.1.	Methodology Flow	33
3.2.	Design and Modeling	37
3.3.	Binder Preparation	39
3.4.	3D Printing and Its Material	41
3.5.	Sintering	42
3.6.	Water Treatment System	44
3.7.	Microstructural Analysis	45
4.	RESULTS AND DISCUSSION	47
4.1.	Parameters and Classifications	47
4.2.	Particle Size Distribution	49
4.3.	Ceramic Membrane Physical and Structural Properties	50
4.4.	Ceramic Membrane Filtration Rate	54
4.5.	Backwash Analysis	58
4.6.	Ceramic Membrane Efficiency	62
5.	CONCLUSION AND RECOMMENDATION	64
5.1.	Conclusion	64
5.2.	Recommendation	66
	REFERENCES	68
	APPENDICES A – APPENDICES D	73- 83

LIST OF TABLES

TABLE NO.	TITLE	PAGE
1.1	Comparisons for each rapid prototyping processes in terms of total material cost and processing time	8
2.1	Additive manufacturing criterion assessment	11
2.2	Pros and cons of AM techniques	12
2.3	3D printer pricing over time	14
2.4	Summary of 3D printing advantages and disadvantages	18
2.5	Important 3D printing applications	20
2.6	Physical properties of ceramic membranes prepared with SiC powders of various sizes	22
2.7	Particle characterization	24
4.1	Samples classification	48
4.2	Physical properties of ceramic membrane	51
4.3	Comparison of filtration rate at 1 minute and 5 minutes for each sample	57
4.4	SEM image and EDX for ceramic membrane before treatment, after treatment, and after backwash	60
4.5	Ceramic membrane filtration efficiency in terms of COD and TSS	63

LIST OF FIGURES

FIGURE NO.	TITLE	PAGE
1.1	Collection efficiencies of ceramic membranes prepared with SiC powders of various sizes	7
2.1	Additive manufacturing process	10
2.2	Breakeven analysis comparing conventional HPDC process and SLS technique	17
2.3	3D printed ceramic hanging herb garden tile	21
2.4	Pore size distribution of ceramic membranes prepared with SiC powders of various sizes	23
2.5	Particle characterization results of the IPS InLine Dentin powder	24
2.6	Porosity for varying wall thickness	27
2.7	Membrane efficiency for different initial powder size measured by Log Reduction Value (LRV)	28
2.8	Particle rejection for each filtration cycle	29
2.9	Measured bacteria concentrations before and after ceramic water treatment with subsequent increased in the batch number	30
3.1	Methodology flow	36
3.2	Ceramic membrane without present of hole	38
3.3	Ceramic membrane with the present of hole	38
3.4	Chemical structure of Maltodextrin	39

3.5	Maltodextrin binder solution preparation	40
3.6	Sintering profile	43
3.7	Water treatment system	44
4,1	Particle size distribution	50
4.2	Calculated density versus porosity for limestone material	52
4.3	FESEM observation for sample 1	53
4.4	FESEM observation for sample 2	54
4.5	Filtration rate for ceramic membrane	55
4.6	Filtration rate for ceramic membrane as a function of time.	
	(a) Sample 1a; (b) Sample 1b; (c) Sample 2a; (d) Sample 2b	56

LIST OF SYMBOLS

3DP	- Three Dimensional Printing
AM	- Additive Manufacturing
BSEs	- Backscattered Electrons
BSEs	- Backscattered Electrons
CAD	- Computer Aided Design
CAM	- Computer Aided Manufacture
COD	- Chemical Oxygen Demand
DLP	- Digital Light Processor
EDX	- Energy Dispersive X-ray
EDXA	- Energy Dispersive X-ray Analysis
EDXMA	- Energy Dispersive X-ray Micro Analysis
EPA	- Environmental Protection Agency
FDM	- Fused Deposition Modeling
FESEM	- Field Emission Scanning Electron Microscopy
HPDC	- High Pressure Die Casting
LRV	- Log Reduction Value
PLM	- Product Lifecycle Management
SEs	- Secondary Electrons
SiC	- Silicon Carbide
SLS	- Selective Laser Sintering
STL	- Stereolithography
TSS	- Total Suspended Solids

LIST OF APPENDICES

APPENDIX	TITLE	PAGE
Appendix A	Determination of Physical Properties of Ceramic Membrane	73
Appendix B	Filtration Rate As a Function of Time	77
Appendix C	Water Quality Analysis	80
Appendix D	Domestic Wastewater Standard	82

CHAPTER 1

INTRODUCTION

1.1 Background of Study

Three-dimensional printing (3D printing) is a technology which can convert 3D images from drawing into a physical object by using a printer. This technology has opened up the world to exciting possibilities. A lot of previous researchers have provided many benefits from the application of 3D printing technology such as product design, education, manufacturing, architecture, medical, and pharmaceutical sector. 3D printing has become a competitive strategy which involves product designing, customization, rapid prototyping, and creating a specific product. 3D printing technology application is further enhance by the decreasing costs of 3D printers, wide types of materials available, and the availability of 3D printing devices from different manufacturers (Brooks et al., 2014).

3D printable models can be created by a computer aided design (CAD) package or a 3D scanner. 3D printing can be used to produce a complex model such as printing toys, human implants, space flight components, and replacement parts. In this study, the ceramic membrane was produced by Z-Corporation 3D printer and additional indirect binder application method was applied to create sufficient strength for the green parts. The ceramic membrane was investigated for its efficiency through the water influent and effluent analysis. The material, kaolinite clay, is available in powder form, making them ideal to be used in powder-based 3D printing system.

This study explores the potential to fabricate the membrane from clay powder, wet it with printed liquid to turn it into its plastic form, before it dries to its green state. The green part produced can be increased its strength by applying the binder indirectly and further sintering up to 1300°C (Reay et al., 2011). The strength of bonded ceramic membrane is important to resist the pressure differential for the water medium across the ceramic membrane.

3D printing gives porosity to the ceramic membrane which builds up from the layer by layer basis. The effect of porosity may be influenced by its geometrical structure and microstructural properties (Beall et al., 2012). A high level of porosity may result in high specific area, high permeability, and high tortuosity. Porosity structure can be determined through its microstructural analysis. The porosity, particle density, and distribution structure will determine different filtration performance, thus should fully consider the structural factors.

The parameters used in this study were the powder sizes and membrane shapes. Powder sizes can be obtained from the original clay powder after sieving process while the membrane shapes can be obtained from the Unigraphic design software. Porosity of membrane is depending on the size of the powder. Different porosity will lead to different filtration rate and efficiency of the treatment. Moreover, filtration performance also depends on membrane shapes as it will lead to different surface areas.

1.2 Problem Statement

3D printing is a technology that employs an additive manufacturing process in which the printer deposits the materials based on the layer by layer manufacturing technologies in order to build up a different geometrical shape of 3D components (Withell et al., 2012). It differs from the conventional subtractive manufacturing where 3D printing builds up components from nothing, to layer by layer, until the part is complete, whereas the conventional subtractive manufacturing removes the material from a solid block to create the desired part.

In the aspect of design and production for the materials which are supplied as powders, the material characteristics are the critical concern. The powder characteristics such as powder particle size, shape, and distribution will influence the resulting microstructure, which impacts the material properties (Petrick & Simpson, 2013). These have become a barrier to achieve a finished quality ceramic parts. Various factors such as powder sizes and membrane shapes are considered as independent variables to evaluate the ceramic membrane efficiency in this experimental work.

The traditional production method which can generate shape and microstructure of finalizing part consumes a lot of raw materials, labor, energy, and impose a higher cost for the shop-volume production (Simonis & Basson, 2012). Particularly, the casting or molding method requires the need for producing the molds and tooling as well as inflexible to create, modify, and improve the shape for various applications. Final parts can be limited by the capabilities of the tools used in the manufacturing processes.

Furthermore, the use of pore former to produce porous ceramic membrane provides additional cost of material to the manufacturers. As the manufacturing cost is high, the treatment and replacement cost for wastewater treatment raised as well. 3D printing technology suits to produce a low cost porous ceramic membrane and

flexible to produce different membrane shape for different water treatment system application.

Water contamination is another problem, especially at rural areas and underdeveloped regions where the communities are lacking of capacity to receive the clean water. The environmental degradation occurs when pollutants are directly or indirectly discharge into the water bodies without adequate treatment to remove harmful components. The contaminants may include organic and inorganic substances. Some contaminants such as pathogens can produce waterborne diseases in either human or animal hosts. The ceramic membranes are effective to remove the bacteria and protozoa (Bielefeldt et al., 2010). They have been proven to remove 99.9% of microbiological contaminants (Malapane et al., 2012).

There are 780 million people around the world who are lacking in access to potable water and approximate 3.4 million people die each year from drinking unsanitary water supplies. According to Cooley et al. (2014), Asian rivers are three times higher than the global average results in bacteria levels from sewage and industrial waste. High demand for water treatment system from consumers is driven by the imposition of government environment legislation.

Several water filtration technologies have led to educational initiatives, government, and non-government organizations to resolve the potable water contamination. Millions of these porous clay ceramic membrane are in use at numerous location in Africa, Asia, and South America (Plappally et al., 2011). 3D printing technology may provides benefits in the manufacture of porous ceramic membranes because it is easier to transport and set up in a short period of time and reduce the treatment costs.

1.3 Objective of The Research

The objective is crucial in providing a clear purpose and as a guide to the assessment strategies to achieve the goal of studies. There are three main objectives for this study, which are:

- i. To determine the feasibility of 3D printing technology in order to produce a high efficiency ceramic membrane.
- ii. To analyze the membrane structure and physical properties.
- iii. To investigate the effect of powder sizes and membrane shapes towards the membrane efficiency.

1.4 Research Question

The research questions in this study are:

- i. Is the 3D printing technology compatible with clay powder to produce a ceramic membrane with a better filtration efficiency?
- ii. What are the membrane structures and physical properties of ceramic membrane produced by 3D printing technology?
- iii. Is the clay powder sizes and membrane shapes has a significant effects on the membrane efficiency?

1.5 Scope

The scope of this study focused on:

1. The preparation of the ceramic membrane by using two different sizes of clay powders.
2. Characterization of different sizes of clay powders by Malvern Zetasizer Nano S.
3. Characterize the surface morphological of ceramic membrane using the field emission scanning electron microscopy (FESEM).
4. Identify the bulk density, water absorption, porosity, and filtration rate of ceramic membrane fabricate at different parameters.
5. Chemical compositional analysis to characterize the backwash effect by using the energy dispersive x-ray spectroscopy (EDX).
6. Testing the ceramic membrane efficiency by water filtration process in terms of chemical oxygen demand (COD) and total suspended solids (TSS).

1.6 Significant of Study

3D printing is a modern technology that can work with low cost ceramic materials to produce ceramic membrane in this study. The ceramic membranes are significantly to remove bacteria and protozoa (Bielefeldt et al., 2010). The ceramic membrane also have been historically proven to be effective in removing 99.9% of microbiological contaminants (Malapane et al., 2012). Once the contaminated water is introduced to one side of a ceramic membrane, the 3D printer will produce a porous structure of the ceramic material which could blocks the passage of anything larger than the pore size.

Moreover, to the best of the knowledge, the ceramic membranes are useful to remove the bacteria and protozoa from processed water in the microfiltration

application, but still has a limited functionality of the membranes. The limitation is caused by the undesired growth of the bacteria cells through the membrane pores during long filtration times (Kroll et al., 2010). The efficiency may not be sustained after subsequent high levels of bacteria passing through the membranes. Some preventive measures for bacteria growth are suggested to be used for prolonged periods.

As refer to Figure 1.1, the collection efficiency for the printed ceramic membrane may significantly influenced by clay powder size and treatment particle size. Choi et al. (2014) demonstrated that the collection efficiency increased with increasing the treatment particle size and decreasing the silicon carbide (SiC) powder size at the filtration velocity of 1m/min. They found that the samples made with SiC100 and SiC 200 powders have low collection of efficiencies if compared with SiC10, 25, and 50. The results can be improved by avoiding the formation of pinholes and cracks for the samples.

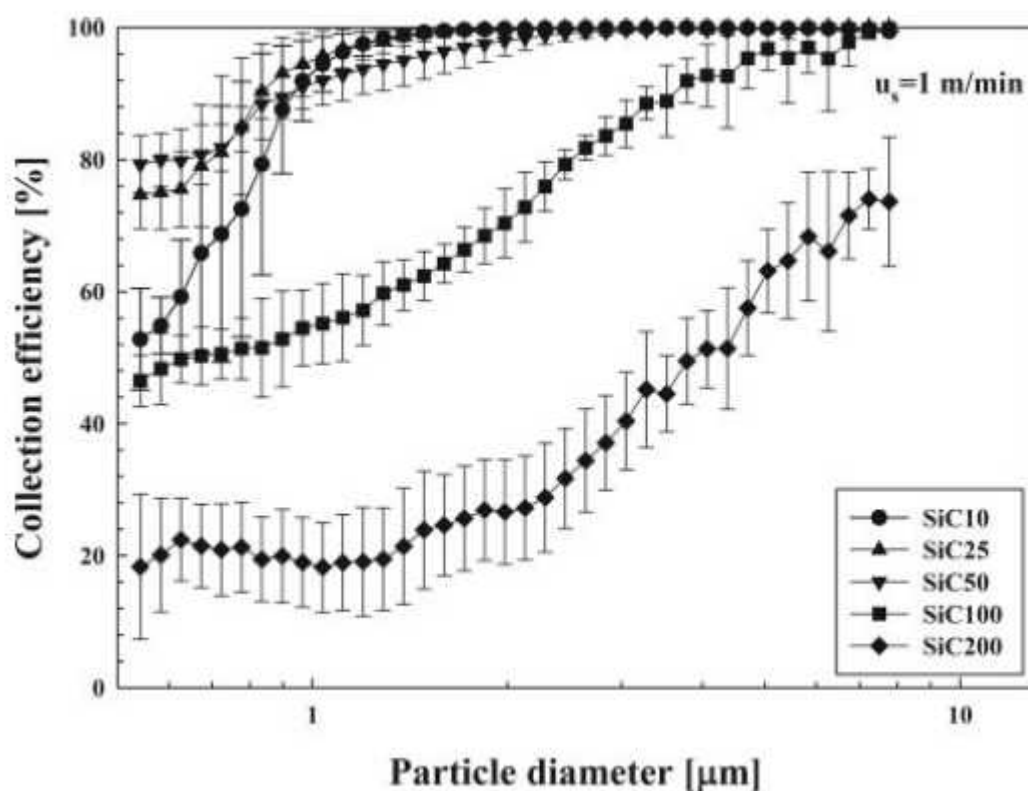


Figure 1.1: Collection efficiencies of ceramic membranes prepared with SiC powders of various sizes.

The significant of this study is due to the use of the low cost method which is one of the most promising technique to produce the ceramic membrane which can provide clean, safe, and affordable water for residential, industrial, and institutional use. The processing method for ceramic membrane which is simple and easy to set up benefits for commercial and pilot plant. The 3D printing requires fewer materials and less energy for the shaping process compared to the conventional casting and molding method. It is also sustainable because the materials can be reused and recycled.

A study made by Ulbrich et al. (2012) showed that 3D printing was faster and cheaper in terms of process time and material cost, compared to other rapid prototyping process. A comparison to describe the material cost consumed and processing time for each rapid prototyping technology is shown in Table 1.1. In today fast growing and competitive industry, the manufacturers favor to minimize their cost and time in order to maximize their profit, so that, the application of 3D printing technology will become another alternative trend.

Table 1.1: Comparisons for each rapid prototyping processes in terms of total material cost and processing time.

No	Rapid prototyping processes	Total material cost	Processing time
1	Selective Laser Sintering (SLS)	\$6.75	04hours07min
2	Fused Deposition Modeling (FDM)	\$20.39	13hours47min
3	Digital Light Processor (DLP)	\$15.22	06hours41min
4	Three Dimensional Printer (3DP)	\$6.75	01hours00min
5	Polyjet	\$42.90	03hours50min

REFERENCES

- Additive Manufacturing and 3D Printing. (2013). *Chemical Industry Digest*.
- Atzeni, E., & Salmi, A. (2012). Economics of additive manufacturing for end-usable metal parts. *The International Journal of Advanced Manufacturing Technology*. 62(9-12), 1147-1155.
- Bai, J., Yang, X., Shi, Y., Xu, S., & Yang, J. (2012). Fabrication of directional SiC porous ceramics using Fe₂O₃ as pore-forming agent. *Materials Letters*. 78, 192-194.
- Beall, D. M., Heibel, A. K.-E., & Tandon, P. (2012). Filtration structures for improved particulate filter performance.
- Belibi, P. B., Nguemtchouin, M., Rivallin, M., Nsami, J. N., Sieliechi, J., Cerneaux, S., et al. (2015). Microfiltration ceramic membranes from local Cameroonian clay applicable to water treatment. *Ceramics International*. 41(2), 2752-2759.
- Bergmann, C., Lindner, M., Zhang, W., Koczur, K., Kirsten, A., Telle, R., et al. (2010). 3D printing of bone substitute implants using calcium phosphate and bioactive glasses. *Journal of the European Ceramic Society*. 30(12), 2563-2567.
- Berman, B. (2012). 3-D printing: The new industrial revolution. *Business horizons*. 55(2), 155-162.
- Bielefeldt, A. R., Kowalski, K., Schilling, C., Schreier, S., Kohler, A., & Summers, R. S. (2010). Removal of virus to protozoan sized particles in point-of-use ceramic water filters. *water research*. 44(5), 1482-1488.
- Bielefeldt, A. R., Kowalski, K., & Summers, R. S. (2009). Bacterial treatment effectiveness of point-of-use ceramic water filters. *Water Research*. 43(14), 3559-3565.
- Bogue, R. (2013). 3D printing: the dawn of a new era in manufacturing? *Assembly Automation*. 33(4), 307-311.
- Borah, S. (2014). 3D printer filament length monitor.

- Brooks, G., Kinsley, K., & Owens, T. (2014). 3D Printing As A Consumer Technology Business Model. *International Journal of Management & Information Systems (IJMIS)*. 18(4), 271-280.
- Choi, H.-J., Kim, J.-U., Kim, S. H., & Lee, M.-H. (2014). Preparation of Granular Ceramic Filter and Prediction of Its Collection Efficiency. *Aerosol Science and Technology*. 48(10), 1070-1079.
- Cooley, H., Ajami, N., Ha, M.-L., Srinivasan, V., Morrison, J., Donnelly, K., et al. (2014). *Global Water Governance in the Twenty-First Century*. In *The World's Water* (pp. 1-18): Springer.
- Diegel, O., Withell, A., de Beer, D., Potgieter, J., & Noble, F. (2012). Low-cost 3D printing of controlled porosity ceramic parts. *International Journal of Automation Technology*. 6(5), 618-626.
- Farzadi, A., Solati-Hashjin, M., Asadi-Eydivand, M., & Osman, N. A. A. (2014). Effect of layer thickness and printing orientation on mechanical properties and dimensional accuracy of 3D printed porous samples for bone tissue engineering.
- Fatimah, I., Sahroni, I., Putra, H. P., Rifky Nugraha, M., & Hasanah, U. A. (2015). Ceramic membrane based on TiO₂-modified kaolinite as a low cost material for water filtration. *Applied Clay Science*. 118, 207-211.
- Global 3D Printer Market. (2014). (Journal, Electronic).
- Groot, C., & Gunneweg, J. (2010). The influence of materials characteristics and workmanship on rain penetration in historic fired clay brick masonry. *Heron*, 55 (2), 2010.
- Hall, C., & Hamilton, A. (2015). Porosity–density relations in stone and brick materials. *Materials and Structures*. 48(5), 1265-1271.
- Hwang, K.-J., Chan, C.-S., & Tung, K.-L. (2009). Effect of backwash on the performance of submerged membrane filtration. *Journal of Membrane Science*. 330(1–2), 349-356.
- Holmström, J., Partanen, J., Tuomi, J., & Walter, M. (2010). Rapid manufacturing in the spare parts supply chain: Alternative approaches to capacity deployment. *Journal of Manufacturing Technology Management*. 21(6), 687-697.
- Kroll, S., Treccani, L., Rezwani, K., & Grathwohl, G. (2010). Development and characterisation of functionalised ceramic microtubes for bacteria filtration. *Journal of Membrane Science*. 365(1–2), 447-455.

- Lindemann, C., Reiher, T., Jahnke, U., & Koch, R. (2015). Towards a sustainable and economic selection of part candidates for additive manufacturing. *Rapid Prototyping Journal*. 21(2), 216-227.
- Majouli, A., Younssi, S. A., Tahiri, S., Albizane, A., Loukili, H., & Belhaj, M. (2011). Characterization of flat membrane support elaborated from local Moroccan Perlite. *Desalination*. 277(1), 61-66.
- Malapane, T. A., Hackett, C., Netshandama, V., & Smith, J. (2012). Ceramic water filter for point-of-use water treatment in Limpopo province, South Africa. *Systems and Information Design Symposium (SIEDS), 2012 IEEE*. 107-111.
- Mançanares, C. G., Zancul, E. d. S., da Silva, J. C., & Miguel, P. A. C. (2015). Additive manufacturing process selection based on parts' selection criteria. *The International Journal of Advanced Manufacturing Technology*, 1-8.
- Melchels, F. P., Domingos, M. A., Klein, T. J., Malda, J., Bartolo, P. J., & Hutmacher, D. W. (2012). Additive manufacturing of tissues and organs. *Progress in Polymer Science*. 37(8), 1079-1104.
- Mellor, S., Hao, L., & Zhang, D. (2014). Additive manufacturing: A framework for implementation. *International Journal of Production Economics*. 149, 194-201.
- Mohamed, R. F. (2014). Emphasizing the advantage of 3d printing technology in packaging design development and production in local industries Dr. Rania F. Mohamed* Dr. Abeer S. Mahmoud*** & ** Assistant professors. *Computer-aided design*. 5, 10.
- Mota, C., Puppi, D., Chiellini, F., & Chiellini, E. (2015). Additive manufacturing techniques for the production of tissue engineering constructs. *Journal of tissue engineering and regenerative medicine*. 9(3), 174-190.
- Petrick, I. J., & Simpson, T. W. (2013). 3D printing disrupts manufacturing. *Research Technology Management*. 56(6), 12.
- Piller, F. T., Weller, C., & Kleer, R. (2015). *Business Models with Additive Manufacturing—Opportunities and Challenges from the Perspective of Economics and Management*. In *Advances in Production Technology* (pp. 39-48): Springer.
- Pîrjan, A., & Petro anu, D.-M. (2013). The impact of 3d printing technology on the society and economy. *Journal of Information Systems & Operations Management*. 7(2), 360-370.

- Plappally, A., Chen, H., Ayinde, W., Alayande, S., Usoro, A., Friedman, K. C., et al. (2011). A field study on the use of clay ceramic water filters and influences on the General Health in Nigeria. *Journal of Health Behavior and Public Health*. 1(1), 1-14.
- Reay, S., Withell, A., & Grupp, I. (2011). Porous ceramic filters through 3d printing. Rock density and porosity, 2015. http://petrowiki.org/Rock_density_and_porosity.
- Rüsenberg, S., Schmidt, L., Hosse, H., & Schmid, H. J. (2012). *Porosity as a key to increase material properties of laser sintered parts*. In (pp. 531-538).
- Schilling, C. H., Tomasik, P., & Kim, J. C. (1999). Processing technical ceramics with maltodextrins: crosslinking by acetalation. *Starch-Stärke*. 51(11-12), 397-405.
- Simonis, J., & Basson, A. (2012). Manufacturing a low-cost ceramic water filter and filter system for the elimination of common pathogenic bacteria. *Physics and Chemistry of the Earth, Parts A/B/C*. 50, 269-276.
- Transparency Market Research*. (2013). (T. M. Research o. Document Number)
- Ulbrich, C. B. L., Zavaglia, C. A. C., Neto, P. I., Oliveira, M. F., & Silva, J. V. L. (2012). *Comparison of five rapid prototype techniques (SLS/FDM/DLP/3DP/PolyJet)*. In (pp. 573-580).
- Utela, B., Anderson, R. L., & Kuhn, H. (2006). Advanced ceramic materials and processes for three-dimensional printing (3DP). *Solid Freeform Fabr. Symp. Proc.* 290-303.
- Werner, J., Besser, B., Brandes, C., Kroll, S., & Rezwani, K. (2014). Production of ceramic membranes with different pore sizes for virus retention. *Journal of Water Process Engineering*. 4, 201-211.
- Withell, A., Diegel, O., Grupp, I., & Reay, S. (2012). Porous ceramic filters through 3D printing. 313-318.
- Wong, K. V., & Hernandez, A. (2012). A review of additive manufacturing. *ISRN Mechanical Engineering*. 2012.
- Yanga, L., Zhanga, S., Oliveirab, G., & Stuckera, B. (2013). Development of a 3D Printing Method for Production of Dental Application. *Proceedings of the 24th International Solid Freeform Fabrication Symposium. Austin, TX, USA*.
- Yigit, N. O., Civelekoglu, G., Harman, I., Koseoglu, H., & Kitis, M. (2009). Effects of various backwash scenarios on membrane fouling in a membrane bioreactor. *Desalination*. 237(1-3), 346-356.

- Yoo, J., Cima, M., Khanuja, S., & Sachs, E. (1993). Structural ceramic components by 3D printing. *Solid Freeform Fabrication Symposium*. 40-50.
- Zhanga, S., Miyanajia, H., Yanga, L., Zandinejadb, A. A., Dilipa, J., & Stuckera, B. (2014). An Experimental Study of Ceramic Dental Porcelain Materials Using A 3D Print (3DP) Process. *Proceeding of Solid Freeform Fabrication (SFF) Symposium*.