

APPLICATION OF ANIONIC PORPHYRIN AS CHROMOGENIC INDICATOR
AND METALLOPORPHYRIN CATALYSTS FOR
OXIDATION OF BENZYL ALCOHOL

WONG WEN YEE

UNIVERSITI TEKNOLOGI MALAYSIA

APPLICATION OF ANIONIC PORPHYRIN AS CHROMOGENIC INDICATOR
AND METALLOPORPHYRIN CATALYSTS FOR
OXIDATION OF BENZYL ALCOHOL

WONG WEN YEE

A thesis submitted in fulfilment of the
requirements for the award of the degree of
Doctor of Philosophy (Chemistry)

Faculty of Science
Universiti Teknologi Malaysia

FEBRUARY 2017

*Specially dedicated to my dearest parents, sister, brother and
beloved Wilson Loh*

ACKNOWLEDGEMENT

First and foremost I would like to express my sincere gratitude to my supervisors – Prof Dr. Salasiah Endud and Dr Mohd Bakri Bakar for their enthusiastic support, encouragement and thoughtful guidance in all the time of research and writing of this thesis. My appreciation also sends to my co-supervisor, Assist. Prof. Dr. Wong Ka Lun from National Institute of Education, Singapore not only for his insightful comments and constructive advice, but also for hard questions which incited me to widen my research in various perspectives.

My word of gratitude is also extended to Prof. Dr. Mustaffa Shamsuddin and Dr. Leny Yuliati for allowing me to carry out catalyst characterization and catalytic studies in their respective laboratories. Besides, I would like to acknowledge the Science Officers and Assistant Science Officers, En. Azmi, En. Amin, Pn. Suhani, Pn. Ramlah, En. Rahim, En. Faiz, En. Azidy, En. Rasyidi, En Sobri and Pn. Normah for their technical support and assistance throughout the data collection processes in the Department of Chemistry and the University Industrial Research Laboratory (UIRL), Universiti Teknologi Malaysia.

Special thanks to the Ministry of Education Malaysia for the financial support through Research University Grant no. 08H34 and scholarship under mybrain15 Scheme, and Ministry of Science, Technology and Innovation for the Nanotechnology Directorate Top-Down Grant R.J130000.7926.4H007. I would like to thank the National Institute of Education, Singapore, Ibnu Sina Institute Fundamental Science Studies and Faculty of Science, Universiti Teknologi Malaysia for the research facilities.

I would also like to thank my colleagues, Liana, Hannah, Shika, Eida, Yana, Suhaila, Ila and Cassy for the stimulating discussions and all the fun, celebrations we had together. Also, I would like to thank my closest friends, Ke Xin and Sze Ting that will always be there for me.

Finally, I would like to express my deepest appreciation to my beloved parents, sister, brother and Wilson Loh for their love and spiritual support during the thesis writing process and throughout all aspects of life.

ABSTRACT

In recent years, extensive research has been carried out on the synthesis of anionic water-soluble porphyrin, *meso*-tetrakis(4-sulphonatophenyl)porphyrin (TSPP) due to the potential applications in photodynamic therapy, sensors, optical devices and catalysis. However, the information on anion recognition properties of free-base TSPP and performance of TSPP metalloporphyrin complexes in heterogeneous catalytic oxidation are relatively scarce. Hence, this research is divided into two main parts. Firstly, free-base TSPP was utilized as chromogenic reagent for recognition of acetate and citrate ions in aqueous solutions and the optical properties were characterized by ultraviolet-visible (UV-Vis) and fluorescence spectroscopies. The interaction of TSPP with the acetate and citrate ions was quantitatively analyzed at pH 4 using different acids (H_2SO_4 , HCl, HNO_3 , H_3PO_4 and CH_3COOH) for the pH adjustments. The anion sensing mechanism was based on protonation of the imino nitrogens of TSPP porphyrin core in the presence of acids (pH~4), whereby the optical changes observed in the absorption and emission spectra of the pH 4 TSPP solution were the effects of pH changes induced by acetate or citrate anion during deprotonation of TSPP. The Stern-Volmer constant based on the fluorescence quenching spectra revealed that the sensitivity of pH 4 TSPP was almost unaffected by the different acids used for the pH adjustment. For the UV-Vis spectroscopy method, the lowest limit of detection (LOD) of acetate ion (5.61×10^{-6} M) was obtained using nitric acid, while for the fluorescence spectroscopy method, the LOD (4.66×10^{-6} M) of acetate ion was obtained when sulphuric acid was used. Detection of citrate ion was only possible when acetic acid was used for the pH adjustment, with LOD of 9.59×10^{-6} M and 9.79×10^{-6} M for UV-Vis and fluorescence spectroscopies, respectively. Matrix anions (chloride, nitrate, phosphate, carbonate and sulphate ions) effects on the acetate and citrate detection were also studied. The linear range of the fluorescence detection was wider ($2\text{--}19 \times 10^{-5}$ M) as compared to the UV-Vis detection ($4\text{--}18 \times 10^{-5}$ M). Besides, no significant matrix anion effect could be observed in the fluorescence spectra. The microspecies distributions of TSPP, acetate and citrate ions were simulated using the Marvin Bean ChemSketch[®] analysis. The results suggested that the pH of the TSPP solution was instantaneously increased upon the addition of acetate or citrate anion. Consequently, the -2 charge TSPP was converted to -4 charge TSPP, accompanied with significant optical changes. In the second part of this work, TSPP was coordinated to Mn(III), Fe(II), Co(II) and Cu(II) ions to yield the *meso*-tetrakis(4-sulphonatophenyl)porphyrinato metal complexes (TSPP-M) for catalytic oxidation of benzyl alcohol to benzaldehyde with *tert*-butyl hydroperoxide as oxidant. The neat TSPP-M showed superior catalytic performance ($\sim 60\%$ conversion) as compared to that of free-base TSPP (4.8% conversion). Subsequently, TSPP-M was immobilized on the mesoporous silica support *Santa-Barbara Amorphous-15* (SBA-15) via post-synthesis method to afford the heterogeneous catalysts TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu). The TSPP-M/SBA-15 catalysts exhibited high BET (Brunauer-Emmett-Teller) surface areas $> 150 \text{ m}^2 \text{ g}^{-1}$ with average pore diameters $> 5 \text{ nm}$. The effects of reactant to oxidant molar ratio, reaction temperature, solvent, and reaction time were further investigated. Under the optimal conditions, the catalytic trend was in the order: Mn(III) $>$ Fe(II) $>$ Co(II) $>$ Cu(II). The TSPP-Mn/SBA-15 catalysts gave $> 99\%$ selectivity and turn over frequency of 665 h^{-1} after 3 hours of reaction. In addition, all the TSPP-M/SBA-15 catalysts could be reused up to three recycles without significant loss of catalytic activity. The catalytically active species leached out of TSPP-M/SBA-15 surface was extremely small and generally, can be considered negligible. Findings of present studies are significant because the anionic free-base TSPP was reported for the first time as chromogenic reagent for anion recognition. Furthermore, the TSPP-M/SBA-15 has great potential as an environmental friendly heterogeneous catalyst that offers the prospect of commercialization in the production of chlorine-free benzaldehyde.

ABSTRAK

Sejak tahun kebelakangan ini, penyelidikan meluas telah dijalankan ke atas sintesis porfirin anionik terlarut dalam air, *meso*-tetrakis(4-sulfanatofenil)porfirin (TSPP) disebabkan oleh potensi aplikasinya dalam terapi fotodinamik, sensor, peranti optik dan pemangkinan. Namun begitu, maklumat mengenai sifat pengecaman anion TSPP bebas logam dan prestasi kompleks metaloporfirin TSPP dalam pengoksidaan pemangkinan heterogen secara relatifnya jarang ditemui. Maka penyelidikan ini terbahagi kepada dua bahagian utama. Pertamanya, TSPP bebas logam telah digunakan sebagai reagen kromogenik bagi pengecaman anion asetat dan sitrat dalam larutan akueus dan ciri optik telah dicirikan menggunakan spektroskopi ultralembayung-nampak (UV-Vis) dan pendafluor. Interaksi antara TSPP dan ion asetat dan sitrat telah dianalisis secara kuantitatif pada pH 4 dengan menggunakan asid yang berlainan (H_2SO_4 , HCl , HNO_3 , H_3PO_4 dan CH_3COOH) bagi pelarasan pH. Mekanisme pengecaman anion adalah berasaskan protonasi nitrogen imino pada teras porfirin TSPP dengan kehadiran asid (pH~4), di mana perubahan optik yang dicerap dalam spektrum penyerapan dan pemancaran larutan pH 4 TSPP adalah kesan perubahan pH yang diaruh oleh anion asetat atau sitrat semasa penyahprotonasi TSPP. Pemalar Stern-Volmer berdasarkan spektrum pelindapan pendafluor mendedahkan bahawa kepekaan TSPP pH 4 hampir tidak terjejas dengan penggunaan asid berlainan untuk pelarasan pH. Untuk kaedah spektroskopi UV-Vis, had pengesanan (LOD) paling rendah (5.61×10^{-6} M) untuk ion asetat diperoleh dengan menggunakan asid nitrik, manakala bagi kaedah spektroskopi pendafluor, LOD (4.66×10^{-6} M) untuk ion asetat diperoleh apabila asid sulfurik digunakan. Pengesanan ion sitrat hanya dapat dilakukan apabila asid asetik digunakan untuk pelarasan pH, dengan LOD 9.59×10^{-6} M dan 9.79×10^{-6} M untuk spektroskopi UV-Vis dan pendafluor, masing-masing. Kesan anion matriks (ion klorida, nitrat, fosfat, karbonat dan sulfat) terhadap pengesanan asetat dan sitrat turut dikaji. Julat linear pengesanan pendafluor didapati lebih luas ($2\text{--}19 \times 10^{-5}$ M) berbanding dengan pengesanan UV-Vis ($4\text{--}18 \times 10^{-5}$ M). Di samping itu, tiada kesan anion matriks yang ketara boleh diperhatikan pada spektrum pendafluor. Taburan mikrospecies TSPP, ion asetat dan sitrat telah disimulasi menggunakan analisis Marvin Bean ChemSketch[®]. Keputusan kajian mencadangkan bahawa pH larutan TSPP meningkat secara serta-merta semasa penambahan anion asetat atau sitrat. Akibatnya, cas -2 TSPP bertukar kepada cas -4 TSPP, disertai dengan perubahan optik yang jelas. Di bahagian kedua kajian, TSPP telah dikoordinasikan dengan ion Mn(III), Fe(II), Co(II) dan Cu(II) untuk menghasilkan kompleks logam *meso*-tetrakis(4-sulfanatofenil)porfirinato (TSPP-M) bagi pemangkinan pengoksidaan benzil alkohol kepada benzaldehid menggunakan *tert*-butil hidroperoksida (TBHP) sebagai oksidan. Mangkin TSPP-M tulen menunjukkan prestasi pemangkinan yang cemerlang (penukaran ~60%) berbanding dengan TSPP bebas logam (penukaran 4.8%). Seterusnya, TSPP-M dipegunkan ke atas penyokong silika mesolias *Santa-Barbara Amorphous-15* (SBA-15) melalui kaedah pasca-sintesis bagi menghasilkan mangkin heterogen TSPP-M/SBA-15 (M: Mn, Fe, Co dan Cu). Mangkin TSPP-M/SBA-15 mempamerkan luas permukaan BET (Brunauer-Emmett-Teller) yang tinggi $> 150 \text{ m}^2 \text{ g}^{-1}$ dengan purata diameter liang > 5 nm. Kesan reaktan terhadap nisbah molar pengoksida, suhu tindak balas, pelarut dan masa tindak balas telah dikaji. Di bawah keadaan optimum, tren pemangkinan ialah dalam turutan: Mn(III) $>$ Fe(II) $>$ Co(II) $>$ Cu(II). Mangkin TSPP-Mn/SBA-15 memberikan kepilihan $>99\%$ dan frekuensi pusingan balik 665 h^{-1} selepas 3 jam bertindak balas. Di samping itu, kesemua mangkin TSPP-M/SBA-15 boleh diguna semula hingga tiga kitaran tanpa kehilangan aktiviti pemangkinan yang signifikan. Spesies aktif mangkin yang larut lesap dari permukaan TSPP-M/SBA-15 juga didapati amat sedikit dan pada umumnya, boleh diabaikan. Hasil kajian ini adalah penting kerana TSPP anionik bebas logam julung kali dilaporkan sebagai reagen kromogenik untuk pengecaman anion. Tambahan pula, TSPP-M/SBA-15 sangat berpotensi sebagai mangkin heterogen mesra alam yang menawarkan prospek komersialisasi dalam penghasilan benzaldehid bebas klorin.

TABLE OF CONTENTS

CHAPTER	TITLE	PAGE
	DECLARATION	ii
	DEDICATION	iii
	ACKNOWLEDGEMENT	iv
	ABSTRACT	vi
	ABSTRAK	vii
	TABLE OF CONTENTS	viii
	LIST OF TABLES	xiii
	LIST OF FIGURES	xvi
	LIST OF ABBREVIATIONS	xxiv
	LIST OF APPENDICES	xxvii
1	INTRODUCTION	1
	1.1 Background of Research	1
	1.2 Problem Statement	7
	1.3 Research Objectives	10
	1.4 Scope of Study	11
	1.5 Significance of Study	13
2	LITERATURE REVIEW	14
	2.1 Porphyrin	14
	2.1.1 Nomenclature and Synthetic Methods of Porphyrin	15
	2.1.2 Water-Soluble Porphyrin	19
	2.2 Optical Properties of Porphyrin – Absorption	

	and Emission	22
2.3	Protonation and Self-Assembly of Protonated Porphyrin	25
2.4	Acetate and Citrate Ions Studies	29
2.4.1	Acetate and Citrate Receptors	32
2.4.2	Applications of Porphyrins as Anion Sensing Materials	40
2.4.3	Applications of Water-Soluble <i>meso</i> -Tetrakis(sulphonatophenyl)porphyrin as Sensing Materials	46
2.5	Metalloporphyrin as Biomimetic Catalyst	51
2.5.1	Oxidation of Benzyl Alcohol	53
2.5.2	Application of Metalloporphyrins as Catalysts	56
2.5.3	Applications of Water-Soluble <i>meso</i> -Tetrakis(4-sulphonatophenyl)-porphyrin as Catalysts	57
2.6	Porous Silicate Material	61
2.6.1	Mesoporous Material Supported Metalloporphyrin as Heterogeneous Catalyst	63
3	EXPERIMENTAL	68
3.1	Chemicals	68
3.2	Synthetic Methods	69
3.2.1	Synthesis of <i>meso</i> -Tetrakis(phenyl)-porphyrin (TPP)	69
3.2.2	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrin (TSPP)	70
3.2.3	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrinato Manganese(II) (TSPP-Mn)	70

3.2.4	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrinato Iron(II) (TSPP-Fe)	71
3.2.5	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrinato Cobalt(II) (TSPP-Co)	71
3.2.6	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrinato Copper(II) (TSPP-Cu)	72
3.2.7	Synthesis of Mesoporous SBA-15	72
3.2.8	Synthesis of APTES Functionalized SBA-15 (APTES-SBA-15)	72
3.2.9	Synthesis of <i>meso</i> -Tetrakis-(4-sulphonatophenyl)porphyrinato Metal (TSPP-M) Immobilized SBA-15 (TSPP-M/SBA15)	73
3.3	Characterization Methods	74
3.3.1	Fourier Transform Infrared (FTIR) Spectroscopy	74
3.3.2	Ultraviolet-visible (UV-Vis) Spectroscopy	75
3.3.3	Nuclear Magnetic Resonance (NMR) Spectroscopy	75
3.3.4	Fluorescence Spectroscopy	76
3.3.5	Power X-ray Diffraction (XRD)	76
3.3.6	Diffuse Reflectance Ultraviolet-visible (DR UV-Vis) Spectroscopy	77
3.3.7	Nitrogen Adsorption-Desorption Analysis	77
3.3.8	Cross Polarization Magic Angle Spinning Nuclear Magnetic Resonance (CP MAS NMR) Spectroscopy	78
3.3.9	Field Emission Scanning Electron Microscopy (FESEM)	79
3.3.10	Transmission Electron Microscopy (TEM)	80

3.3.11	Inductively Coupled Plasma-Optical Emission Spectroscopy (ICP-OES)	80
3.3.12	Gas Chromatography-Flame Ionization Detector (GC-FID)	80
3.4	Optical Change Measurement of <i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin	81
3.5	Quantitative Spectroscopic Analysis of Acetate and Citrate Ions in Water Using Free-Base TSPP	81
3.6	Catalytic Testing of Neat <i>meso</i> -Tetrakis (4-sulphonatophenyl)porphyrinato Metal and <i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato Metal Immobilized SBA-15 (TSPP-M/SBA-15)	83
4	OPTICAL AND ANION RECOGNITION PROPERTIES OF <i>MESO</i>-TETRAKIS(4- SULPHONATOPHENYL)PORPHYRIN	85
4.1	Introduction	85
4.2	Physicochemical Properties of <i>meso</i> -Tetrakis(4- sulphonatopheny)porphyrin (TSPP)	85
4.3	UV-Vis Absorption Changes of <i>meso</i> -Tetrakis(4- sulphonatophenyl)porphyrin with Different pH and Acid Counter Ion	90
4.4	Recognition Properties of <i>meso</i> -Tetrakis(4- sulphonatophenyl)porphyrin Dication (H_2TSPP^{2-}) on Acetate and Citrate Ions in Water	96
4.4.1	Detection Linear Range and Detection Limit	96
4.4.2	Matrix Effect Studies	105
4.4.3	Sensing Mechanism	113
4.4.4	Marvin Bean ChemSketch [®] Simulation Studies	115
4.4.5	Real Sample Test	119

4.5	Summary	120
5	STRUCTURAL CHARACTERIZATION AND CATALYTIC PROPERTIES OF <i>MESO</i>-TETRAKIS(4-SULPHONATOPHENYL)-PORPHYRINATO METAL IMMOBILIZED SBA-15	122
5.1	Introduction	122
5.2	Physicochemical Properties of <i>meso</i> -Tetrakis(4-sulphonato)phenyl)porphyrinato Metal	123
5.2.1	Physicochemical Properties Pure Silica SBA-15	128
5.2.2	Physicochemical Properties of TSPP-M Immobilized onto APTES-SBA-15 in Various Loadings	134
5.3	Catalytic Testing	149
5.3.1	Optimized Catalytic Condition of TSPP-M Immobilized SBA-15 as Benzyl Alcohol Catalyst	154
5.3.1.1	Effect of Oxidation Molar Ratio	155
5.3.1.2	Effect of Reaction Temperature	157
5.3.1.3	Effect of Solvent	158
5.3.1.4	Effect of Reaction Time	159
5.4	Reusability of Catalyst	169
5.4.1	Leaching Test	172
5.5	Mechanism of the Catalytic Reaction	172
5.6	Summary	175
6	CONCLUSIONS AND RECOMMENDATIONS	176
6.1	Conclusions	176
6.2	Recommendations for Future Work	178
	REFERENCES	180
	Appendices A-Q	209-230

LIST OF TABLES

TABLE NO.	TITLE	PAGE
1.1	Examples of water-soluble porphyrins based on their classes	3
2.1	Summary of applications of TSPP as summary of applications of TSPP as sensing materials in analysis of cations, anions and neutral molecules	47
2.2	Applications of TSPP as catalyst	58
2.3	Classes of porous materials based on pore diameter (Sing <i>et al.</i> , 1985)	61
3.1	Loading of TSPP-M and abbreviations of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	73
3.2	²⁹ Si chemical shift of silicone building units in silica framework	78
3.3	²⁹ Si chemical shift of RSi(SiO) _m units in silica frameworks	79
3.4	Absorption wavelength of metals – Mn, Fe, Co and Cu	80
3.5	Abbreviations of pH 4 TSPP prepared by different acids	82
4.1	¹ H NMR data of TPP and TSPP	87
4.2	¹³ C NMR data for TPP and TSPP	88
4.3	FTIR spectra data of TPP and TSPP	90
4.4	The detection linear range and LOD of acetate and citrate ions by using pH 4 TSPP prepared with different acids as chromogenic indicator, measured with UV-Vis spectrophotometer	103
4.5	The detection linear range and LOD of acetate and citrate ions by using pH 4 TSPP prepared with different acids as	

	fluorogenic indicator, measured with fluorescence spectrophotometer	103
4.6	Stern-Volmer constant (K_{sv}) of TSPP adjusted with different acid	104
4.7	Comparison between slope and elevation of regression lines of H_2SO_4 -TSPP and H_2SO_4 -TSPP with matrix anions, measured by UV-Vis spectroscopy	108
4.8	Comparison between slope and elevation of regression lines of HCl-TSPP and HCl-TSPP with matrix anions, measured by UV-Vis spectroscopy	108
4.9	Comparison between slope and elevation of regression lines of HNO_3 -TSPP and HNO_3 -TSPP with matrix anions, measured by UV-Vis spectroscopy	109
4.10	Comparison between slope and elevation of regression lines of H_3PO_4 -TSPP and H_3PO_4 -TSPP with matrix anions, measured by UV-Vis spectroscopy	109
4.11	Comparison between slope and elevation of regression lines of CH_3COOH -TSPP and CH_3COOH -TSPP with matrix anions, measured by UV-Vis spectroscopy	110
4.12	Comparison between slope and elevation of regression lines of H_2SO_4 -TSPP and H_2SO_4 -TSPP with matrix anions, measured by fluorescence spectroscopy	110
4.13	Comparison between slope and elevation of regression lines of HCl-TSPP and HCl-TSPP with matrix anions, measured by fluorescence spectroscopy	111
4.14	Comparison between slope and elevation of regression lines of HNO_3 -TSPP and HNO_3 -TSPP with matrix anions, measured by fluorescence spectroscopy	111
4.15	Comparison between slope and elevation of regression lines of H_3PO_4 -TSPP and H_3PO_4 -TSPP with matrix anions, measured by fluorescence spectroscopy	112
4.16	Comparison between slope and elevation of regression lines of CH_3COOH -TSPP and CH_3COOH -TSPP with matrix anions, measured by fluorescence spectroscopy	112
4.17	Determination of acetate ion in water samples using the TSPP- H_2SO_4	120

5.1	FTIR Data of TSPP and TSPP-M (M: Mn, Fe, Co and Cu)	124
5.2	UV-Vis spectra characteristic of TSPP and TSPP-M	126
5.3	d-Spacing and unit cell parameter of SBA-15	131
5.4	DR UV-Vis data of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	138
5.5	d-Spacing and unit cell parameter of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	140
5.6	Surface properties of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	144
5.7	^{29}Si MAS NMR data and silicate species of SBA-15, APTES-SBA-15 and 25TSPP-Co/SBA-15	146
5.8	Catalytic performance of TSPP-M (M: Mn, Fe, Co and Cu) at the 6 hours of reaction time	151
5.9	Optimum catalytic conditions	160
5.10	Electronic configuration and spin state of TSPP-M metal core	165
5.11	Comparison of important parameters for oxidation of benzyl alcohol	169
5.12	Leaching test of TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) catalyst	172

LIST OF FIGURES

FIGURE NO.	TITLE	PAGE
1.1	Molecular structure of (a) : porphyrin, (b) : chlorophyll and (c) : haemoglobin	1
1.2	Molecular structure of (a) <i>meso</i> -tetrakis(4-sulphonatophenyl)porphyrin and (b) <i>meso</i> -tetrakis(4-sulphonatophenyl)porphyrinato metal complex; M: transition metal	4
1.3	TSPP-M (M: Mn, Fe, Co and Cu) immobilized onto APTES functionalized SBA-15 by post-synthesis modification step	6
1.4	Outline of research	12
2.1	Molecular structure of (a) vitamin B12, (b) co-enzyme F430, (c) protoporphyrin IX	15
2.2	Molecular structure of porphyrin ring	15
2.3	Porphyrins named with Fisher system	16
2.4	Q-bands UV-Vis spectra of metalloporphyrin	19
2.5	Molecular structures of TPyP and TMPyP	20
2.6	Molecular structures of TCPP and TPP	21
2.7	Molecular structure of neutral porphyrins appended with poly(ethyleneglycol) and glycosylated	22
2.8	Electronic transitions of Soret band and Q-bands	23
2.9	UV-Vis Q-bands of free-base porphyrin. (a) <i>etio</i> -type (b) <i>rhodo</i> - type (c) oxorhodo- type (d) <i>phyllo</i> -type spectra	25
2.10	Porphyrin emission band electronic transitions	25
2.11	Side views of TSPP J- and H- aggregates	27

2.12	Schematic of the side view of H ₂ TSPP ²⁻ J-aggregates in bmim ⁺ ionic liquid	28
2.13	Molecular structure of acetate ion (resonance)	29
2.14	Molecular structure of citrate ion	31
2.15	Design of anion chemosensor based on the covalent bonding of the signaling unit with binding unit	32
2.16	Receptor L sensing mechanism	33
2.17	Azo-based acetate (AcO ⁻) receptor sensing mechanism	33
2.18	Thiourea derivative acetate (AcO ⁻) sensing mechanism	34
2.19	Benzimidazole based acetate receptor sensing mechanism	35
2.20	Calix[2]bispyrrolyarenes based acetate receptor	35
2.21	Molecular structure of Lawsone	36
2.22	BDH based acetate receptor	36
2.23	Coumarin based citrate sensing mechanism	37
2.24	Guanidium based citrate sensing material	38
2.25	Rhodamine-Pb complex based citrate receptor sensing mechanism	38
2.26	Molybdenum complex based citrate receptor sensing mechanism	39
2.27	Molecular structure of sapphyrin	41
2.28	Molecular structure of “picket fence” type porphyrin receptor (a) carbamate appended porphyrin (b) azo-dye appended porphyrin	42
2.29	Molecular structure of β -substituted porphyrin as anion receptor	42
2.30	Molecular structures of (NH ₂) ₄ TPP and NH ₂ (SO ₃) ₃ TPP	43
2.31	Induced-fit binding of (a) nitrate by zinc(II) porphyrin-urea and (b) dihydrogen phosphate by sulfonamide appended zinc(II) porphyrin	44
2.32	Porphyrin derivatives as phosphate anion receptor	45

2.33	Supramolecule composed of cyclodextrin and TSPP-Fe	50
2.34	Molecular structure of cytochrome P450	52
2.35	Cytochrome P450 catalytic route with oxidant and molecular oxygen	52
2.36	Hydrolysis of benzyl chloride and oxidation of toluene	53
2.37	Mechanism of the oxidation of benzyl alcohol with activated DMSO	54
2.38	Proposed mechanism of oxidation of benzyl alcohol with KCrClO ₄ in DMSO-CH ₂ Cl ₂	55
2.39	Proposed mechanism of oxidation of benzyl alcohol with KMnO ₄	55
2.40	Mesoporous structure – (a) hexagonal pore array (b) cubic pore shape (c) non – calcined lamellar structure	62
2.41	SBA-16 supported <i>meso</i> -tetra(4-chlorophenyl)-porphyrinato Cu(II) as cyclohexene oxidation catalyst	63
2.42	[PdTSPP] ⁴⁺ functionalized ionic liquid anchored SBA-15	64
2.43	FeTpyP immobilized onto SBA-15	65
2.44	Structure of hybrid material (SBA-15)-O-Si-(CH ₂) ₃ -NH-CO-(CH ₂) ₂ -OC-HN-5m-Etio-III-Ni ²⁺	66
2.45	Molecular structure of chloro[<i>meso</i> -tetra(4-N-methylpyridinio)-porphyrinato] manganese(III) tetrachloride	66
3.1	Synthesis of <i>meso</i> -Tetrakis(4-phenyl)porphyrin scheme	69
4.1	Scheme of sulphonation of TPP with concentrated sulphuric acid	86
4.2	¹ H NMR spectra of TPP and TSPP	86
4.3	¹³ C NMR spectra of TPP and TSPP	88
4.4	FTIR spectra of TPP and TSPP	89
4.5	Acid base equilibrium between TSPP and H ₂ TSPP ²⁻	91
4.6	UV-Vis absorption spectra of TSPP at pH 2-5, adjusted by sulphuric acid (a) Soret band (b) Q-bands	91

4.7	UV-Vis absorption spectra of TSPP at pH 2-5, adjusted by hydrochloric acid (a) Soret band (b) Q-bands	92
4.8	UV-Vis absorption spectra of TSPP at pH 2-5, adjusted by nitric acid (a) Soret band (b) Q-bands	92
4.9	UV-Vis absorption spectra of TSPP at pH 2-5, adjusted by acetic acid (a) Soret band (b) Q-bands	92
4.10	UV-Vis absorption spectra of TSPP at pH 5.92 and 7, adjusted by sodium hydroxide (a) Soret band (b) Q-bands	93
4.11	“Tail-to-Face” J-aggregation phenomena of TSPP	94
4.12	Side view of the proposed model for the J-aggregation of TSPP, X as the anion that chelated to center NH of TSPP (Luca <i>et al.</i> , 2006)	94
4.13	UV-Vis absorption spectra of TSPP at pH 2, with pH adjustment using various acids	95
4.14	UV-Vis absorption spectra of TSPP-H ₂ SO ₄ (2×10^{-6} M) upon titration with acetate ion ($0-210 \times 10^{-6}$ M). The arrows showed the changes of absorbance due to increasing concentration of acetate ion	97
4.15	Fluorescence emission spectra of TSPP – H ₂ SO ₄ (2×10^{-6} M) upon titration with acetate ion ($0-210 \times 10^{-6}$ M). The arrow showed the quenching of emission upon addition of acetate ion	98
4.16	Plot of absorbance changes of pH 4 TSPP ($\lambda = 414$ nm) versus concentration of acetate or citrate ion. (a) acetate-H ₂ SO ₄ -TSPP (b) acetate-HCl-TSPP (c) acetate-HNO ₃ -TSPP (d) acetate-H ₃ PO ₄ -TSPP (e) citrate-CH ₃ COOH-TSPP	100
4.17	Plot of fluorescence intensity of pH 4 TSPP ($\lambda = 669$ nm) versus concentration of acetate or citrate ion: (a) acetate-H ₂ SO ₄ -TSPP (b) acetate-HCl-TSPP (c) acetate-HNO ₃ -TSPP (d) acetate-H ₃ PO ₄ -TSPP (e) citrate-CH ₃ COOH-TSPP	102
4.18	Optimized configuration of porphyrin in D _{2h} and D _{4h} (Ma <i>et al.</i> , 2000)	114
4.19	Overlap of H ₂ SO ₄ -TSPP UV-Vis absorption and fluorescence spectra. Arrow in the spectra indicated	

	changes of bands after addition of acetate ions to H ₂ OS ₄ -TSPP	115
4.20	Microspecies distribution of TSPP at pH 0-14 based on calculation of Marvin Bean ChemSketch [®]	116
4.21	Molecular structure of TSPP with different charges (a) –3 charged TSPP (b) –6 charged TSPP	117
4.22	Microspecies distribution of acetate ion at pH 0-14 based on the calculation from Marvin Bean ChemSketch [®]	118
4.23	Microspecies distribution of citrate ion at pH 0 – 14 based on the calculation from Marvin Bean ChemSketch [®]	119
5.1	Scheme oxidation of benzyl alcohol to benzaldehyde with TBHP as oxidant, TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) as catalyst	123
5.2	FTIR spectra of TSPP and TSPP-M (M: Mn, Fe, Co and Cu)	124
5.3	UV-Vis spectra of TSPP and TSPP-M (M: Mn, Fe, Co and Cu) taken in deionized water (a) Soret Band (b) Q-bands	125
5.4	Molecular orbital diagram of free-base TSPP which displays normal type spectra	126
5.5	Molecular orbital diagram of TSPP-M (M: Fe, Co and Cu) which displays hypso type spectra	127
5.6	Molecular orbital diagram of TSPP-Mn displayed hyper d-type UV-Vis spectrum	128
5.7	FTIR spectra of as-synthesized, after Soxhlet extraction and APTES functionalized SBA-15 materials (APTES-SBA-15)	129
5.8	Powder XRD patterns of as-synthesized, after Soxhlet extraction and APTES-SBA-15 materials	130
5.9	FESEM micrograph of SBA-15 after Soxhlet extraction. The inset shows the circled area in higher magnification	132
5.10	Transmission electron micrographs of SBA-15 with different orientations (a) vertical orientation (b) parallel orientation	133

5.11	FTIR spectra of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	135
5.12	DR UV-Vis spectrum of APTES-SBA-15	136
5.13	DR UV-Vis spectra of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15 – (a) TSPP-Mn/SBA-15 (b) TSPP-Fe/SBA-15 (c) TSPP-Co/SBA-15 (d) TSPP-Cu/SBA-15 (e) Plot of intensity (K-M) of TSPP-M/SBA-15 versus catalyst loading	137
5.14	XRD patterns of 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	139
5.15	Nitrogen adsorption-desorption isotherms of SBA-15 and APTES-SBA-15	141
5.16	Nitrogen adsorption-desorption isotherms 10, 25 and 50 μ mole loading of TSPP-M (M: Mn, Fe, Co and Cu) immobilized SBA-15	142
5.17	Schematic representation of advanced condensation in undulated cylindrical pore	143
5.18	^{29}Si MAS NMR spectra of SBA-15, APTES-SBA-15 and 25TSPP-Co/SBA-15	145
5.19	^{13}C MAS NMR spectra of APTES-SBA-15 and 25TSPP-Co/SBA-15	147
5.20	FESEM micrograph of 25TSPP-Co/SBA-15. The inset shows the circled area in higher magnification	147
5.21	Transmission electron micrographs of 25TSPP-Co/SBA-15. The circled area in (a) is shown with higher magnification in (b)	148
5.22	Conversion of benzyl alcohol and selectivity towards benzaldehyde by free-Base TSPP (Reaction condition: 40 mg TSPP, 80°C, molar ratio of substrate:oxidant = 1:1)	149
5.23	% Conversion of benzyl alcohol and % selectivity towards benzaldehyde by various types of neat TSPP-M (Reaction condition: 40 mg TSPP-M, 80°C, molar ratio of substrate:oxidant = 1:1, acetonitrile)	150
5.24	The plot of log of the second-order rate constant (K_{YOOH}) for the reaction of manganese porphyrin with	

	percarboxylic acid (YOOH) versus pKa carboxylic acid leaving group (pK _{YOH}) (Yuan and Bruice, 1984)	152
5.25	Nucleophilic displacement reaction of manganese porphyrin with percarboxylic acid	153
5.26	% Conversion of benzyl alcohol and % selectivity towards benzaldehyde by APTES-SBA-15 (Reaction condition: 80 mg APTES-SBA-15, 80°C, molar ratio of substrate:oxidant = 1:1, acetonitrile)	154
5.27	Effect of oxidant to reactant ratio on the conversion of benzyl alcohol and selectivity over 25TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) catalysts. (Reaction condition: 80 mg 25TSPP-M/SBA-15, 80°C, 6 h reaction time, acetonitrile)	155
5.28	Effect of temperature on the conversion of benzyl alcohol and selectivity toward benzaldehyde over 25TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) Catalysts (Reaction Condition: 80 mg 25TSPP-M/SBA-15, 6 h reaction time, acetonitrile)	157
5.29	Bimetallic peroxo-bridge complex and superoxo metal complex	158
5.30	Effect of solvent on the conversion of benzyl alcohol and selectivity toward benzaldehyde over 25TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) catalysts (Reaction condition: 80 mg catalyst, 80°C, 6 h reaction time)	159
5.31	Effect of reaction time on conversion of benzyl alcohol and selectivity towards benzaldehyde over TSPP-Mn/SBA-15 as catalyst (Reaction condition: 80 mg TSPP-Mn/SBA-15, R.T., molar ratio of substrate:oxidant = 1:1, acetonitrile)	161
5.32	Effect of reaction time on conversion of benzyl alcohol and selectivity towards benzaldehyde with TSPP-Fe/SBA-15 as catalyst (Reaction condition: 80 mg TSPP-Fe/SBA-15, R.T., molar ratio of substrate:oxidant = 1:1, acetonitrile)	161
5.33	Effect of reaction time on conversion of benzyl alcohol and selectivity towards benzaldehyde over TSPP-Co/SBA-15 as catalyst (Reaction condition: 80 mg TSPP-Co/SBA-15, 80°C, molar ratio of substrate:oxidant = 1:1.5, acetonitrile)	162

5.34	Effect of reaction time on conversion of benzyl alcohol and selectivity towards benzaldehyde over TSPP-Cu/SBA-15 as catalyst (Reaction condition: 80 mg TSPP-Cu/SBA-15, 80°C, molar ratio of substrate:oxidant = 1:1.5, acetonitrile)	163
5.35	TON of TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) with different loading of catalyst	163
5.36	TOF of TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu) with different loading of catalyst	164
5.37	Redox cycle of metalloporphyrin during oxidation reaction	165
5.38	Spin change of Fe(II) and Co(II) during redox change	166
5.39	Correlation between surface area of different loadings of TSPP-M/SBA-15 (M= Mn, Fe, Co and Cu) immobilized SBA-15 and TOF	168
5.40	Recyclability test result of various TSPP-M/SBA-15 - (a) TSPP-Mn/SBA-15, (b) TSPP-Fe/SBA-15, (c) TSPP-Co/SBA-15 and (d) TSPP-Cu/SBA-15	171
5.41	Proposed mechanism for oxidation of benzyl alcohol over TSPP-M/SBA-15 (M= Mn, Fe and Co)	173
5.42	The scheme of homolytic and heterolytic cleavage of oxygen-oxygen bond (Lee and Bruice, 1985)	174

LIST OF ABBREVIATIONS

λ	-	Wavelength
$^{\circ}\text{C}$	-	Degree Celcius
^{13}C NMR	-	Carbon-13 nuclear magnetic resonance
^1H NMR	-	Proton nuclear magnetic resonance
^{29}Si NMR	-	Silica-29 nuclear magnetic resonance
2θ	-	Bragg angle
Å	-	Ångström
AcO ⁻	-	Acetate ion
a_0	-	Unit cell parameter
APTES-SBA-15	-	(3-aminopropyl)triethoxysilane functionalized SBA-15
BJH	-	Barrett-Joyner-Halenda
BmimBF ₄ ⁻	-	1-butyl-3-methylimidazolium tetrafluoroborate
CDCl ₃	-	Deuterated chloroform
c-Hex	-	Cyclohexane
cmc	-	Critical micellar concentration
CoA	-	Coenzyme A
CP MAS	-	Cross polarization magic angle spinning
CTAB	-	cetyltrimethylammonium bromide
Cu K _α	-	X-ray diffraction from copper K _α energy levels
DCC	-	N,N'-dicyclohexylcarbodiimide
DCM	-	dichloromethane
DDQ	-	2,3-dichloro-5,6-dicyano-1,4-benzoquinone
DMSO	-	Dimethyl sulfoxide
DR	-	Diffuse reflectance
ϵ	-	Molar absorptivity
FeTPyP	-	Iron(III)-5,10,15,20-tetrakis(4-pyridyl)-porphyrin
FIA	-	Flow-injection Analysis

FTIR	-	Fourier transform infrared
GC-FID	-	Gas chromatography-flame ionization detector
h	-	Hour
H ₂ O ₂	-	Hydrogen peroxide
H ₂ TSPP ²⁻	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin dication
H ₃ TSPP ⁻	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin trication
HOMO	-	Highest occupied molecular orbital
HPLC	-	High performance liquid chromatography
ICP-OES	-	Inductively coupled plasma-optical emission spectroscopy
IUPAC	-	International Union of Pure and Applied Chemistry
<i>J</i>	-	Coupling constant
K-M	-	Kubelka-Munk
K _{sv}	-	Stern-Volmer constant
LMCT	-	Ligand-to-metal charge-transfer
LOD	-	Limit of detection
LUMO	-	Lowest unoccupied molecular orbital
<i>m</i>	-	<i>Meta</i> -
M	-	Molarity
MCM	-	Mobil composition of matter
Me	-	Methyl
MLCT	-	Metal-to-ligand charge-transfer
nm	-	nanometer
<i>o</i>	-	<i>Ortho</i> -
<i>p</i>	-	<i>Para</i> -
PDT	-	Photodynamic therapy
pK _a	-	Acid dissociation constant
ppm	-	Part per million
R.T.	-	Room temperature
SBA	-	Santa-Barbara Amorphous
TBHP	-	<i>Tert</i> -butyl hydroperoxide
TCPP	-	<i>meso</i> -Tetrakis(4-carboxyphenyl)porphyrin
TEM	-	Transmission electron microscopy

TMPyP	-	<i>meso</i> -Tetrakis(N-methylpyridyl)porphyrin
TOF	-	Turnover frequency
TON	-	Turnover number
TPP	-	<i>meso</i> -tetrakis(4-phenyl)porphyrin
TPyP	-	<i>meso</i> -Tetreakis(pyridyl)porphyrin
TSPP	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin
TSPP ⁻	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin monoanion
TSPP ²⁻	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin dianion
TSPP-Co	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato cobalt(II)
TSPP-Cu	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato copper(II)
TSPP-Fe	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato iron(II)
TSPP-M	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato metal
TSPP-M/SBA-15	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)- porphyrinato metal immobilized SBA-15
TSPP-Mn	-	<i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrinato manganese(II)
UV-Vis	-	Ultraviolet-visible
XRD	-	X-ray Diffraction
β	-	Beta
δ	-	Chemical shift
μmol	-	Micromole
π	-	pi

LIST OF APPENDICES

APPENDIX	TITLE	PAGE
A	Computational study – Marvin Bean ChemSketch®	209
B	¹³ C, DEPT 90 and DEPT 135 NMR Spectra of <i>meso</i> -Tetrakisphenylporphyrin (TPP)	211
C	¹³ C, DEPT 90 and DEPT 135 <i>meso</i> -Tetrakis(4-sulphonatophenyl)porphyrin (TSPP)	212
D	MALDI-TOF spectrum of TPP	213
E	MALDI-TOF spectrum of TSPP	214
F	UV-Vis spectroscopic data of TSPP at pH 2 - 7	215
G	UV-Vis absorption spectra of TSPP-HCl and TSPP-HNO ₃ upon anion titration	217
H	UV-Vis absorption spectra of TSPP-H ₃ PO ₄ and TSPP-CH ₃ COOH upon anion titration	218
I	Fluorescence emission spectra of TSPP-HCl and TSPP-HNO ₃ upon anion titration	219
J	Fluorescence emission spectra of TSPP-H ₃ PO ₄ and TSPP-CH ₃ COOH upon anion titration	220
K	Plot of absolute absorbance of pH 4 TSPP at 414 nm against acetate or citrate ion concentration (a) acetate-H ₂ SO ₄ -TSPP (b) acetate-HCl-TSPP (c) acetate-HNO ₃ -TSPP (d) acetate-H ₃ PO ₄ -TSPP (e) citrate-CH ₃ COOH-TSPP	221

L	Plot of absolute emission of pH 4 TSPP emission at 669 nm against acetate or citrate ion concentration. (a) acetate-H ₂ SO ₄ -TSPP (b) acetate-HCl-TSPP (c) acetate-HNO ₃ -TSPP (d) acetate-H ₃ PO ₄ -TSPP (e) citrate-CH ₃ COOH-TSPP	222
M	Stern-Volmer plots for (a) TSPP-H ₂ SO ₄ , (b) TSPP-HCl, (c) TSPP-HNO ₃ , (d) TSPP-H ₃ PO ₄ and (e) TSPP-CH ₃ COOH	223
N	Table B Metal content of 10 μmol, 25 μmol and 50 μmol loadings MTSPP (M: Mn, Fe, Co and Cu) immobilized SBA-15	224
O	BJH pore size distribution of SBA-15, APTES-SBA-15 and 10, 25, 50 μmol loading of TSPP-M/SBA-15 (M: Mn, Fe, Co and Cu)	225
P	UV-Vis spectra of benzyl alcohol catalytic mixture with 25TSPP-M/SBA-15 as catalyst	227
Q	Quantitative gas chromatography calibration plot of benzyl alcohol by using ethyl benzoate as internal standard	228
R	An example of GC chromatogram for liquid products of oxidation of benzyl alcohol to benzaldehyde at 353 K by using ethyl benzoate as internal standard	229
S	List of Publications and Presentations	230

CHAPTER 1

INTRODUCTION

1.1 Background of Research

Porphyrins are natural occurring compounds consisting of tetrapyrrolic macrocycle as shown in **Figure 1.1 (a)**. Porphyrins are essential for living organism as they involve in various biological processes such as oxygen binding, electron transfer, biocatalysis and photochemical routes (Cragg, 2005). Metals in biological system are often bound to porphyrin forming metalloporphyrins. For example, magnesium binds to porphyrin to form chlorophyll (**Figure 1.1 (b)**) that plays the role as a light harvesting agent in the photosynthesis process. While iron binds to porphyrin to form haemoglobin (**Figure 1.1 (c)**) which is responsible for sophisticated oxygen transport in mammals (Donald, 2001).

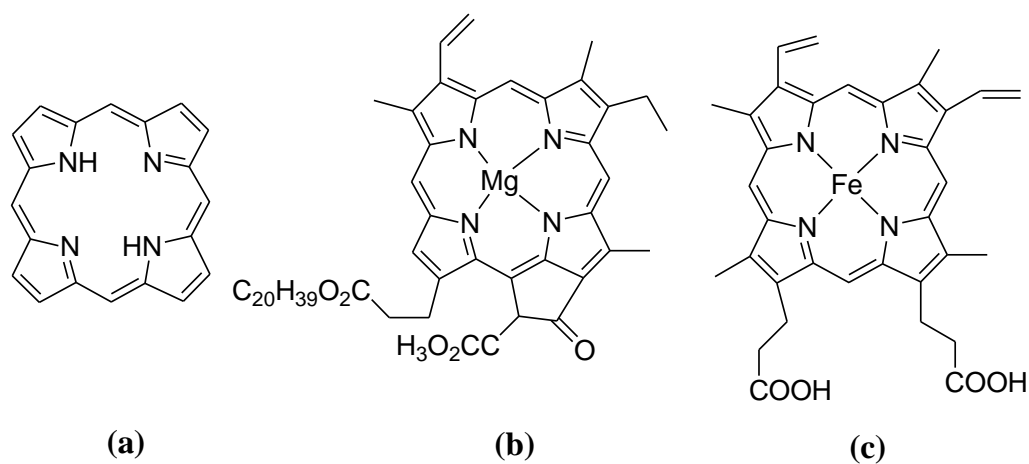


Figure 1.1 Molecular structure of (a): porphyrin, (b): chlorophyll and (c): haemoglobin

The abundance and importance of porphyrin in nature make it interesting scaffold for technological and scientific studies. The π electrons rich macrocycle of porphyrin makes its structure rigid and stable. In addition, the four nitrogen atoms in the macrocycle readily coordinate to wide variety transition metals. Besides, the large macrocycle in porphyrin provides spaces for further functionalization. Its properties can be fine-tuned by introducing substituents or changing the central metal ion.

This ability enables porphyrin to be modulated to fit different applications by simple chemical modification of porphyrin multifunctional core, such as protonation by acids. In addition, metal complexes of porphyrins possess photochemically and electrochemically interesting characteristics that can be used to introduce new functionalities of the materials. With these attractive features, porphyrin has been studied intensively in various applications such as sensing, catalysis, photodynamic therapy, energy harvesting and others (Král *et al.*, 2006; Meunier, 1992).

The water solubility of porphyrin is dependent strictly on the functional group substituted at the porphyrin macrocycle. For example, *meso*-tetrakis(4-chlorophenyl)porphyrin with non-polar chlorophenyl- as the substituent group is sparingly soluble in water at room temperature, while *meso*-tetrakis(methylpyridyl)porphyrin with positively charged methylpyridyl- as the substituent is soluble in water. The non-water-soluble porphyrins are not suitable for most of the bio-chemical applications which usually occur in aqueous medium.

Due to the difficulty of preparation, only a limited number of water-soluble porphyrins have been successfully synthesized. In general, water-soluble porphyrin can be divided into three classes, i.e. positively charged porphyrin, negatively charged porphyrin and neutral porphyrin (Simonnaeux *et al.*, 2011). Examples of water-soluble synthetic porphyrins based on their classes are given in **Table 1.1**.

Table 1.1 Examples of water-soluble porphyrins based on their classes

Class of Porphyrin	Examples
positively charged	<i>meso</i> -tetrakis(4-pyridyl)porphyrin, <i>meso</i> -tetrakis(4-N,N,N-trimethylanilinium)porphyrin
negatively charged	α , β , γ , δ -tetraphenylporphine trisulfonate, <i>meso</i> -tetrakis(4-sulphonatophenyl)porphyrin (TSPP)
neutral Porphyrin	glycosylated porphyrins (bearing appended glycol groups)

Compared to other water-soluble porphyrins, the preparation of negatively charged *meso*-tetrakis(4-sulphonatophenyl)porphyrin (hereafter referred as TSPP) was much easier (Fleischer *et al.*, 1971). TSPP is a tetra-anionic porphyrin which consists of four sulphonatophenyl- charge groups (**Figure 1.2(a)**) that enable it to possess excellent water solubility.

When a metal is inserted in the porphyrin core, the resulting complex, *meso*-tetrakis(4-sulphonatophenyl)porphyrinato metal (hereafter referred as TSPP-M), possesses a molecular structure as shown in **Figure 1.2(b)**, which has the potential to undergo redox reactions at the metal centre rather than on the porphyrin ring.

However, not much work has been devoted to the applications of TSPP until a less-tedious protocol was developed by Fleischer *et al.* (1971). Soon after, some TSPP derivatives have been successfully prepared up to gram scale based on the improved version of Fleischer's method (Srivastava and Tsuisui, 1972; Dong and Scammells, 2007; Simões *et al.*, 2012). This has sparked the interest of researchers to explore more potential applications of TSPP. In general, the TSPP application studies can be grouped into three categories, i.e. sensing, catalysis, and bio-medical applications (Taies and Mohammed, 2013; Cristaldi *et al.*, 2015; Zoltan *et al.*, 2015).

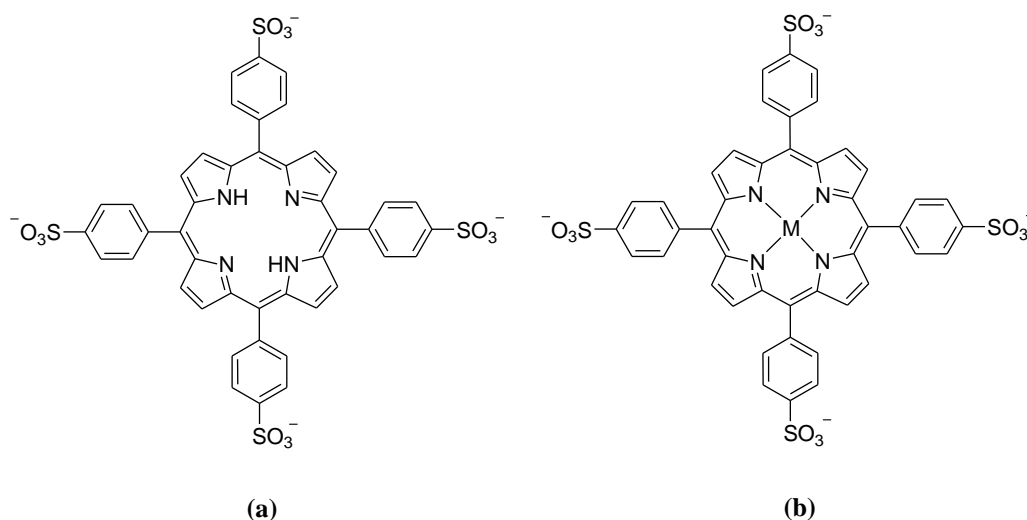


Figure 1.2 Molecular structure of (a) *meso*-tetrakis(4-sulphonatophenyl)porphyrin and (b) *meso*-tetrakis(4-sulphonatophenyl)porphyrinato metal complex; M: transition metal

In various sensing applications, the TSPPs were used as optical sensing materials for the quantitative analysis by spectrophotometric and high performance liquid chromatography (HPLC) methods (Xu *et al.* 1990). Cation sensing was studied by means of HPLC, UV-Vis and fluorescence spectroscopies while, anion sensing by potentiometric and UV-Vis spectroscopy studies. Besides, neutral molecules and gases were sensed by probes that were modified with TSPP. In the analytical study of cation using TSPP as the host component, the porphyrin structure was reported to undergo a planarity change upon the chelation with the target cation.

The structural change of TSPP was significant and could be observed in both the UV-Vis and fluorescence spectra (Biesaga *et al.*, 2000). Porphyrins usually possess high absorption coefficient at 400–450 nm (visible range) and large stokes shift that minimize the effect of background noise. However, the use of fluorescence spectroscopy for the analysis of target analyte with TSPP is still limited. Hence, the first part of this research highlighted on the application of TSPP in anion recognition studies by UV-Vis and fluorescence spectroscopies. In addition, the distribution of charged species at different pH was simulated using Marvin Bean ChemSketch[®] to probe the conformational change in TSPP during the anion recognition process.

Since the discovery of cysteine-haem enzyme in cytochrome P450 more than fifty years ago, various types of metalloporphyrins have been developed that aimed to mimic the oxidation properties of cytochrome P450 (Luzgina *et al.*, 1977). Metalloporphyrin coordinated to various transition metals with great variety of new structures have been synthesized (Nakagaki *et al.*, 2013). Some of these metalloporphyrins were TSPP-Ms which were tested as potential catalysts in oxidation, reduction, photodegradation and polymerization reactions (Olaya *et al.*, 2012; Tanimoto *et al.*, 2008; Nabid *et al.*, 2013).

The TSPP-Ms gave good catalytic performances, particularly in oxidation of hydrocarbons (Ren *et al.*, 2009; Ricoux *et al.*, 2009). It was demonstrated that the metal species should be carefully chosen so that the metal-oxo-porphyrin formed could act as active oxidizing species. Noted that most of the TSPP-Ms reported in the literature possessed Mn(III) and Fe(II) as the central metal ion. Oxidative catalyst on TSPP-Ms with Co(II) and Cu(II) core are still scarce. In this study, the physicochemical properties of TSPP coordinated to Mn(III), Fe(II), Co(II) and Cu(II) were synthesized. Their catalytic potential as oxidation catalysts were studied. Their physicochemical properties of these TSPP-Ms were also investigated.

Heterogeneous catalysts are highly desired as they can be easily separated and recovered from the reaction medium. Heterogeneous catalysts based on TSPP-Ms can be obtained by immobilizing the TSPP-Ms onto a solid support. However, the solid support has to be carefully selected so that desirable catalyst properties such as high surface area, good thermal and chemical stabilities can be achieved. Mesoporous silica SBA-15 which consists of high surface area ($>500 \text{ m}^2/\text{g}$), high hydrothermal stability, easily accessible and uniform mesopores (20 – 100 Å) is an excellent candidate as the solid support for the porphyrin macrocycles. Previous studies have reported that the immobilization of porphyrin catalyst onto SBA-15 enhanced the catalyst stability and selectivity and made the reusability of the catalyst possible (Espinosa *et al.*, 2011; Zhu *et al.*, 2014; Najafian *et al.*, 2015).

Therefore, immobilizing the metalloporphyrin catalyst on a high surface area SBA-15 can lead to the desired catalytic activity. The porphyrin complexes can be introduced onto SBA-15 by two approaches: either by entrapment of the porphyrin in the silica support by *in-situ* synthesis, or immobilization of the porphyrin onto the porous silica surface in a post-synthesis modification step. In the present study, the latter approach was performed to immobilize the TSPP onto SBA-15 via electrostatic interaction between TSPP-M and (3-aminopropyl)triethoxysilane (APTES) functionalized SBA-15 as proposed in **Figure 1.3**.

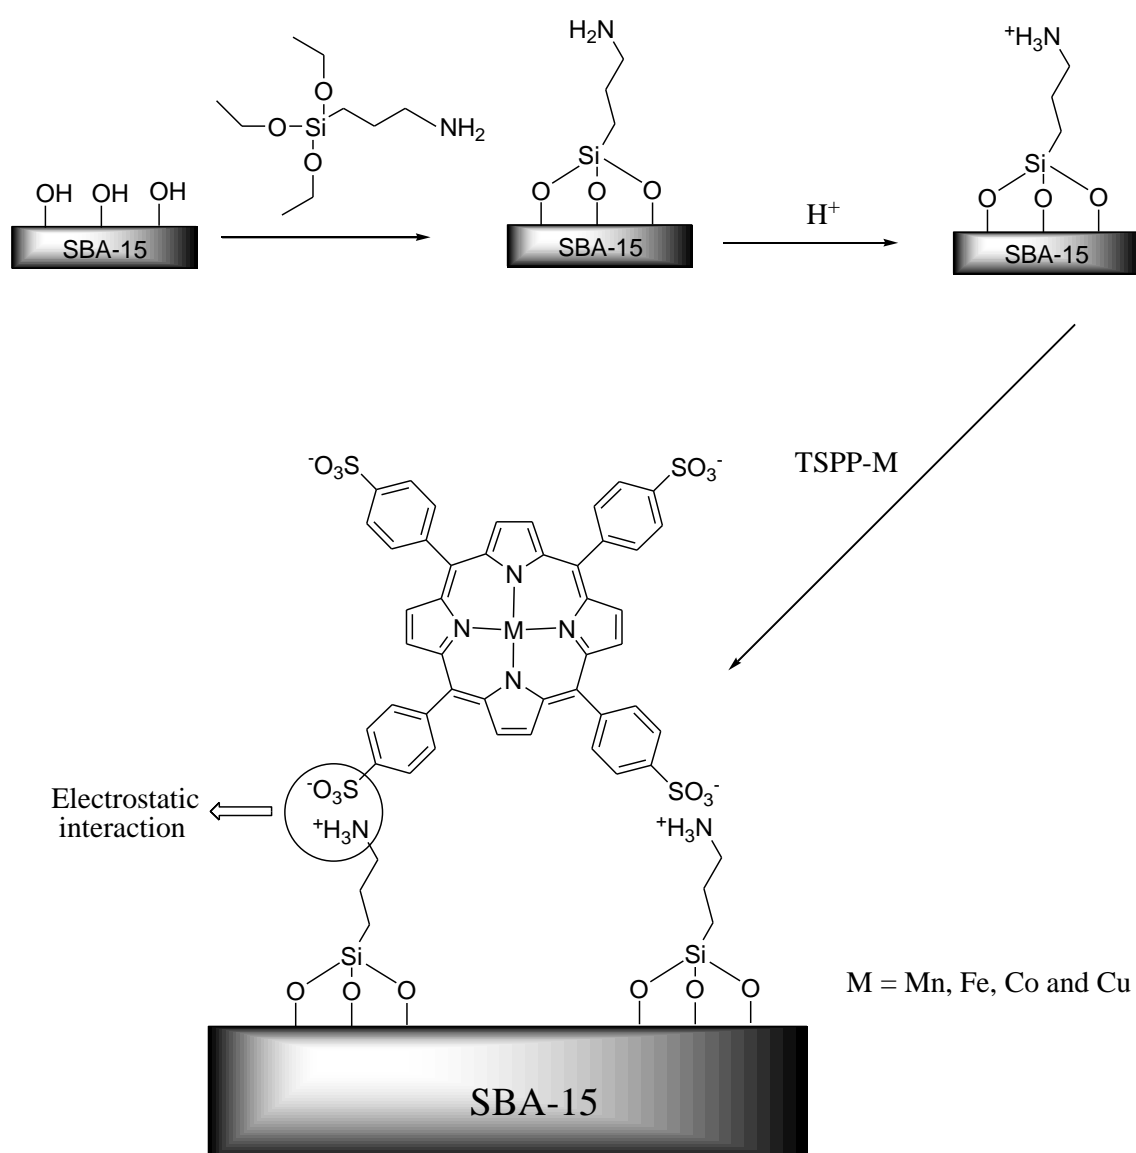


Figure 1.3 TSPP-M (M: Mn, Fe, Co and Cu) immobilized onto APTES functionalized SBA-15 by post-synthesis modification step

1.2 Problem Statement

As anion interactions play a vital role in chemistry and biology, the development of new, sensitive method for the determination of extremely small amounts of anions in solution is deemed important. For example, the concentration of acetate ion is utilized to monitor the fermentation process in sediment and sludge reactor (Orcutt *et al.*, 2013; Chua *et al.* 2003); while the concentration of citrate ion in urine can be used to diagnose nephrolithiasis and nephrocalcinosis disease (Schell-Feith *et al.*, 2006).

Because of the relevance to the needs, a wide variety of methods have been devised to analyse acetate and citrate ions such as capillary ion electrophoresis (Williams *et al.*, 1997) isotope labelling method (Morrison *et al.*, 2004), flow injection analysis (Forman *et al.*, 1991) and ion-chromatography methods (Erdema and Bedir, 2014). All of these known methods required tedious sample pre-treatment and complicated instrument set up which limited their widespread applicability. Consequently, UV-Vis absorption and fluorescence spectroscopy techniques are considered as effective tools owing to their sensitivity, simple instrument implementation, as well as safe and short response time (Chahal and Sankar, 2015; Kiefer *et al.*, 2010).

In order to prepare anions sensing material, numerous chromogenic and fluorogenic indicators consist of functional groups such as amide (Goswani *et al.*, 2012), phenolic hydroxyl (Hijji, 2012) and thiourea derivatives (Liu *et al.*, 2012) have been developed for acetate and citrate ions analyses. Most of the indicators were only soluble in aprotic solvents such as acetonitrile, hence limiting their applications for detecting anions in aqueous samples (Huang *et al.*, 2010). This is because non-water-soluble molecular scaffolds tend to agglomerate in aqueous medium. Furthermore, the physicochemical properties of the anion, such as large size and high solvation energy often make the design of anion indicator/receptor more challenging. Because of the larger size of anion as compared to cation, a bigger host is required for the binding of anion.

Currently, quantitative determination of anions can be carried out using commercially available bio-chemical sensors based on enzymes (Keevil *et al.*, 2005). However, many enzymes are very sensitive to sample conditions and unstable at high temperature and extreme pH. As a result, the enzyme-based sensors are not suitable to be applied to samples that are without any pre-treatment. On the other hand, porphyrins have been used in sensor applications due to their high sensitivity. As mentioned in **Section 1.1**, the rich photochemistry of TSPP would enable it to be used as a chromogenic indicator for cation and anion analysis.

Spectral shifts of porphyrins could be used as a “marker” for the presence of different anions. With the high sensitivity of porphyrin to the pH change, the optical behaviour can be altered through modification of the porphyrin structure. In the case of TSPP, owing to its low pK_a (~4.86), the porphyrin can be easily protonated and deprotonated at the pyrrolic nitrogen (-NH), which depends on pH change of the medium (Delmarre *et al.* 1999). The protonation and deprotonation processes during interactions with the target analytes can affect the conformations of porphyrin macrocycle which may also result in observable changes in the UV-Vis and fluorescence spectra. Therefore, it is possible to use TSPP as anion recognition material for basic anions such as acetate and citrate; without tedious macrocycle modification.

To the best knowledge of the author, using TSPP as fluorogenic indicators for quantitative fluorescence spectroscopic analysis of anion has not been reported yet. Only quantitative absorption spectrophotometric technique has been explored so far. In addition, the application of TSPP, especially free-base TSPP, as chromogenic and fluorogenic indicators for quantitative anion analysis is still scarce. Hence, in the first part of this study, the conformational change of water-soluble TSPP during diprotonation and deprotonation by acids was being utilized for anion analysis in aqueous medium.

In the second part of this research, the TSPP-M immobilized SBA-15 samples were explored in heterogeneous catalysis of benzyl alcohol in order to understand the structure-catalytic property relationship in this catalyst system. In homogeneous

catalysis, oxidation of alcohols to corresponding aldehyde and ketone requires a stoichiometric amount of oxidant such as chromium(VI), permanganate, DMSO and DDQ (Cardona and Permegiani, 2015). Consequently, all of these oxidants suffer drawbacks of generating high amounts of organic and inorganic toxic side products after the reaction. Furthermore, these methods are usually carried out in halogenated organic solvent that will produce undesirable halogenated waste and caused safety hazardous concern. Hence, the catalytic reaction with little amount of oxidant has attracted attention in the past decade.

In the conventional method, benzaldehyde was produced by hydrolysis of benzyl chloride or oxidation of toluene and styrene with stoichiometric amounts of chromium and manganese salt. These methods generate copious wastes and the chloride inevitably will present in the benzaldehyde as an impurity (Yu *et al.*, 2010; Patel and Pathan, 2012). Moreover, these methods suffer from the drawbacks of lack of selectivity, generation of undesired side product, unenviable toxic waste and usage of toxic reagent. Consequently, an alternative environmentally benign heterogeneous catalyst for the oxidation of benzyl alcohol is required.

In this work, the TSPP was core modified using a series of transition metals such as Mn(III), Fe(II), Co(II) and Cu(II) as oxidation catalyst for conversion of benzyl alcohol as model reaction. Hence, it would be expected that stability of valence electron and oxidative properties of TSPP ligand will affect the catalytic activity trend. Previous studies have shown that various TSPP-Ms were utilized as epoxidation and oxidation catalysts (Ren *et al.*, 2009; Rémy *et al.*, 2009; Nabidi *et al.*, 2013).

However, till date, TSPP-M catalyst has never been reported for its application in the liquid phase oxidation of benzyl alcohol to benzaldehyde. Thus, present study reported for the first time that TSPP-Ms with different metal cores were used as catalysts for the oxidation of benzyl alcohol. In addition, the usage of “clean” oxidant such as *tert*-butyl hydroperoxide (TBHP) for the liquid phase oxidation of benzyl alcohol possesses great potential from the point of view of green chemistry.

Neat metalloporphyrin catalyst typically shows high efficiency and selectivity under mild reaction conditions. This is because the reactant molecules interact with the catalyst molecules in the same reaction phase, generally liquids, which make chemical reactions more efficient and easy to form the desired products. However, the use of metalloporphyrin as a homogeneous catalyst has suffered a few drawbacks such as insoluble in the reaction medium, liable to oxidative self-destruction, mass transfer limitation and aggregation through π - π stacking interaction that lead to deactivation of the catalyst (Rosa *et al.*, 2000).

Furthermore, the difficult recovery of homogenous catalyst leads to the substantial loss of the catalyst and adds significantly to production costs of commercial processes. In order to overcome these drawbacks, immobilization of homogenous catalyst onto mesoporous solid support was demonstrated in this study in order to produce environmentally benign heterogeneous catalyst which could be a very promising, alternative approach.

1.3 Research Objectives

The main goal of this research is to investigate the application of TSPP as anion indicator and oxidation catalyst.

The main objectives of this research are shown as follows:

1. To synthesize and characterize *meso*-tetrakis(4-sulphonatophenyl)porphyrin (TSPP).
2. To investigate the colorimetric and fluorogenic properties of TSPP as anion recognition material.
3. To evaluate and optimize the catalytic condition of *meso*-tetrakis(4-sulphonatophenyl)porphyrinato metal (TSPP-M) immobilized SBA-15 in the synthesis of benzaldehyde by oxidation of benzyl alcohol.

1.4 Scope of Study

In this research, the anionic porphyrin entity, TSPP was used throughout the study. In Chapter 4, the physicochemical properties of TSPP were studied by Fourier Transform Infrared (FTIR) spectroscopy, ^1H , ^{13}C NMR spectroscopies and matrix-assisted laser desorption – time of flight (MALDI-TOF) mass spectrometry. The correlations between optical changes of TSPP aqueous solution and anion concentration have been investigated by the addition of different acids and base for pH adjustment in the range of 2 to 7. Furthermore, matrix effect studies were carried out in the presence of additional anions, i.e. chloride, nitrate, phosphate, carbonate and sulphate, respectively. Additionally, the charge species distribution of TSPP during the anion interaction was predicted using the Marvin Bean ChemSketch[®].

In Chapter 5, the TSPP was coordinated to different transition metals (Mn(III), Fe(II), Co(II) and Cu(II)) and immobilized onto SBA-15 (TSPP-M/SBA-15) through electrostatic interaction. The physicochemical properties of the resulting organic-inorganic hybrid materials were characterized with Fourier Transform Infrared (FTIR) spectroscopy, diffuse reflectance ultraviolet-visible (DR UV-Vis) spectroscopy, ^{29}Si , ^{13}C cross polarization magic angle spinning nuclear magnetic resonance (CP-MAS NMR) spectroscopy, X-ray diffraction analysis (XRD), nitrogen absorption measurement, inductively coupled plasma optical emission (ICP-OES) spectrometry, field emission scanning electron microscopy (FESEM) and transmission electron microscopy (TEM).

The catalytic properties and reusability of TSPP-M immobilized SBA-15 samples were tested in the oxidation of benzyl alcohol. Various catalytic conditions such as the substrate to oxidant ratio, temperature, solvent, reaction time and catalyst loadings have been optimized. The research outline is illustrated in **Figure 1.4**.

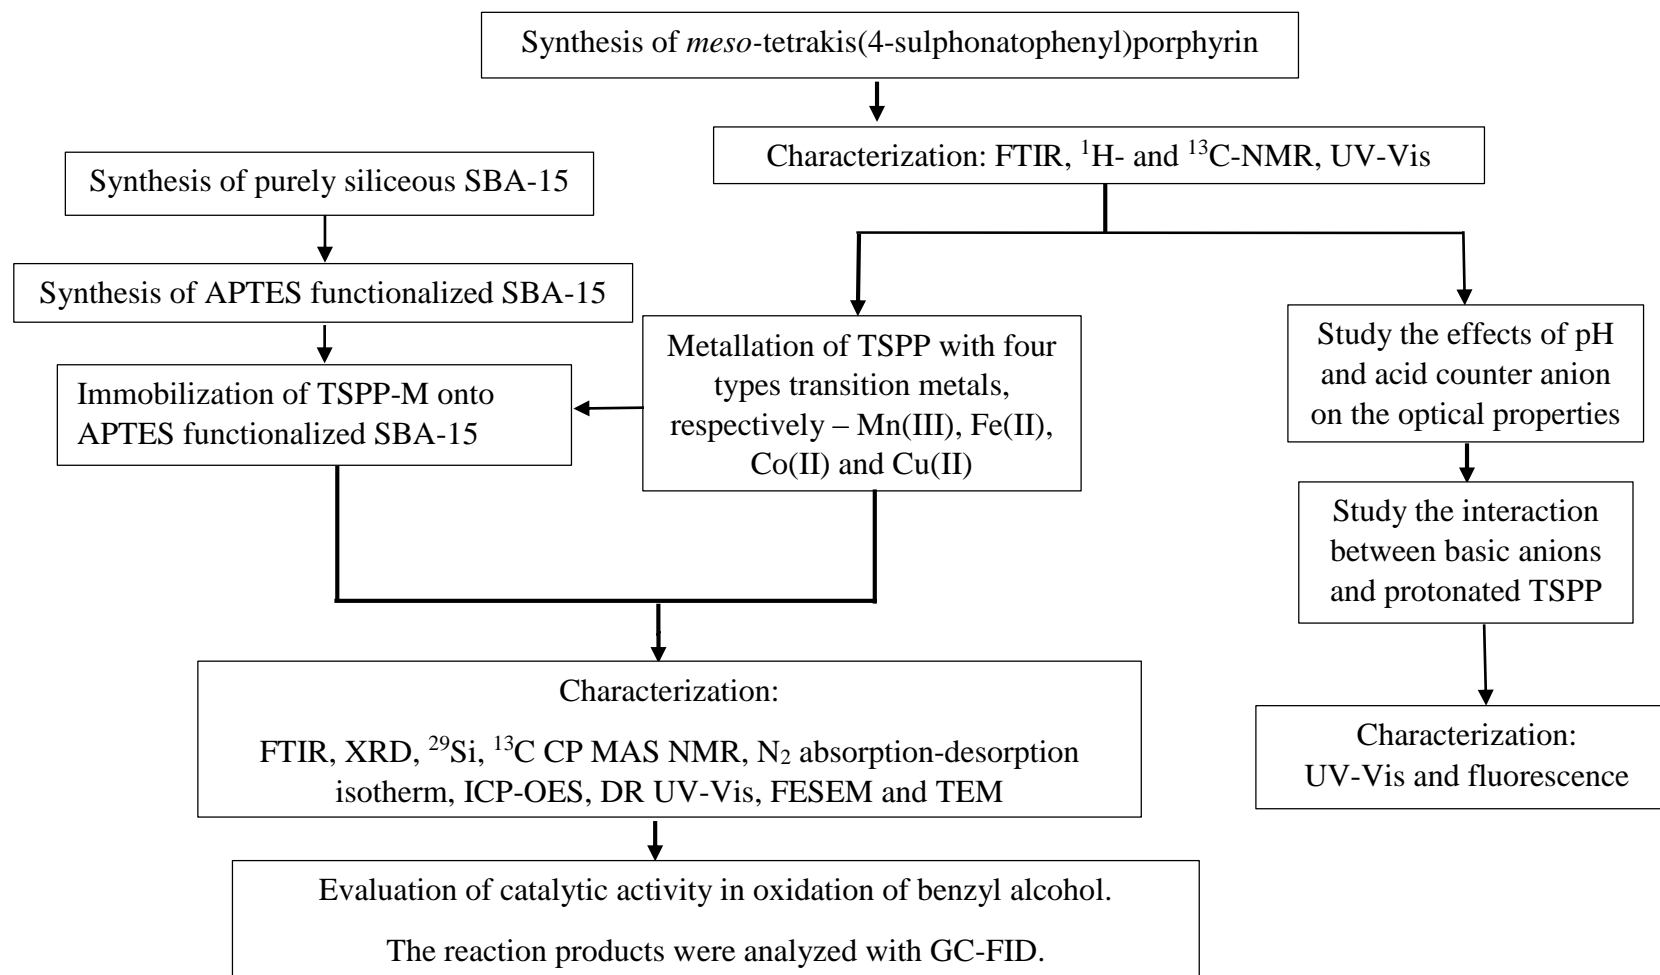


Figure 1.4 Outline of research

1.5 Significance of Study

In this research, the porphyrin *meso*-tetrakis(4-sulphonatophenyl)porphyrin (TSPP) which fulfils the prerequisite of high water-solubility, low toxicity and commercially available up to gram scale is an exciting candidate for a wide variety of research studies involving aqueous samples (Böhm and Gröger, 2015). The TSPP can be prepared in aqueous medium, making it more environmentally friendly as the usage of non-sustainable and flammable organic solvents can be minimised.

Furthermore, a new chromogenic and fluorogenic indicator based on TSPP has been developed for the quantitative analysis of acetate and citrate ions. The rich photochemistry of TSPP allows for the analysis of anions to be carried out by means of UV-Vis and fluorescence spectroscopies which do not require complicated instrument set up. Moreover, new techniques, fluorescence spectroscopy and prediction with Marvin Bean ChemSketch[®] (Chem Axon) were developed for the anion detection and prediction of TSPP charge species, respectively.

Additionally, the strong coordination properties of TSPP towards various kinds of transition metals allow for the development of selective biomimetic catalysts based on porphyrins. Green synthesis of benzaldehyde using alcohol as precursor and TBHP as oxidant for the transformation of benzyl alcohol to benzaldehyde can possibly reduce the generation of toxic side products and undesired inorganic contaminants. Recyclable and selective oxidation catalysts based on TSPP derivatives offer the prospect of commercialization and the oxidation reaction can be practically implemented to produce chlorine-free benzaldehyde that meets the stringent requirements of cosmeceutical and pharmaceutical industries.

REFERENCES

- Adam, F. and Ooi, W.-T. (2012) Selective Oxidation of Benzyl Alcohol to Benzaldehyde over Co-metalloporphyrin Supported on Silica Nanoparticles. *Applied Catal. A*. 445-446: 252-260.
- Adam, F. and Ooi, W.-T. (2013) Nickel Porphyrin Hybrid Material Based on Functionalised Silica for the Selective Oxidation of Benzyl Alcohol. *J. Phys. Sci.*24:1-19.
- Adler, A.D., Longo, F. R., Finarelli, J.D., Goldmacher, J., Assour, J. and L. (1967). A Simplified Synthesis for *meso*-Tetraphenylporphyrin. *J. Org. Chem.* 32: 476.
- Adler, A.D., Longo, F.R., Kampas, Fr., Kim, J. (1970) On the Preparation of Metalloporphyrins. *J. Inorg. & Nuc. Chem.* 37: 2443-2445.
- Ali, M., Kumar, V., Baker, S.N., Baker, G.A., Pandey, S. (2010) J-aggregation of Ionic Liquid Solutions *meso*-Tetrakis(4-sulfonatophenyl)porphyrin. *Phys. Chem. Chem. Phys.* 12: 1886-1894.
- Almeda, S., Gandolfi, H.E., Arce, L., Valcarcel, M. (2009) Potential of Porphyrins as Chromogenic Reagents for Determining Metals in Capillary Electrophoresis. *J. Chromatogr A*. 1216: 6256-6258.
- Amao, Y. and Watanabe (2009) Photochemical and Enzymatic Methanol Synthesis from HCO_3^- by Dehydrogenases Using Water-Soluble Zinc Porphyrin in Aqueous Media. *Applied Catal. B* 86: 109-113.
- Amao, Y., Hiraishi, T., Okura, I. (1997) Photoinduced Hydrogen Evolution using Water Soluble Viologen-Linked Trisulfonatophenylporphyrins (TPPSC_nV) with Hydrogenase. *J. Mol. Catal. A* 126: 21-26.
- Amolegbe, S.A., Adewuyi, S., Akinremi, C.A., Adediji, J.F., Lawal, A., Atayese, A.O., Obaleye, J.A. (2015) Iron(III) and Copper(II) Complexes Bearing 8-Quinolinol with Amino-Acids Mixed Ligands: Synthesis, Characterization and Antibacterial Investigation. *Arab. J. Chem.* 8: 742-747.

- Anantha, N.V., Azam, M., Sheardy, R.D. (1998) Porphyrin Binding to Quadruplexed T4G4. *Biochem.* 37: 1-9.
- Andrade, S.M. and Costa, S.M.B. (2008) Ordered Self-assembly of Protonated Porphyrin Induced by the Aqueous Environment of Biomimetic Systems. *Annals of the New York Acad. of Sci.* 1130: 305-313.
- Andrighetto, P., Carofiglio, T., Fornaiser, R., Tonellato, U. (2000) A Highly Sensitive Method for the Analysis of Nitrite Ions by Capillary Zone Electrophoresis using Water-Soluble Aminophenylporphyrin Derivative as Chromogenic Reagent. *Electrophoresis.* 21: 2384 – 2389.
- Antipas, A., Buchler, J.W., Gouterman, M., Smith, P.D. (1977) Porphyrin 36. Synthesis and Optical and Electronic Properties of Some Ruthenium and Osmium Octaethylporphyrins. *J. Am. Chem. Soc.* 100: 3015-3024.
- Antonisse, M. M. G. and Reinhoudt, D. N. (1998). Neutral Anion Receptors Design and Applications. *J. Chem. Soc., Chem. Commun.* 443-448.
- Arvind, M., Mohammad, S., Pratibha, D. (2009) An Efficient Thiourea-Based Colorimetric Chemosensor for Naked-Eye Recognition of Fluoride and Acetate Anions: UV-Vis and ¹H-NMR Studies. *Talanta.* 80: 532-538.
- Awawdeh and Harmon (2004) Spectrophotometric Detection of Pentachlorophenol (PCP) in Water using Immobilized and Water-Soluble Porphyrins. *Biosen. & Bioelectron.* 20: 1595-1601.
- Awawdeh M.A., Legako, J.A., Harmon, H.J. (2003) Solid-State Optical Detection of Amino Acids. *Sensor & Actuat. B.* 91: 227-230.
- Bai, L., Xie, Z., Cao, K., Zhao, Y., Xu, H., Zhu, C., M, Z., Zhong, Q., Gu, Z. (2014) Hybrid Mesoporous Colloid Photonic Crystal Array for High Performance Vapor Sensing. *Nanoscale.* 6: 5680-5685.
- Balaji, T., El-Safty, S.A., Matsunaga, H., Hanaoka, T., Mizukamim, F. (2006) Optical Sensors Based on Nanostructured Cage Materials for the Detection of Toxic Metal Ions. *Angew. Chem. Int. Ed.* 45: 7202-7208.
- Banerji, K.K. and Nath, P. (1969) Kinetics of the Oxidation of Benzyl Alcohol by Acid Permanganate. *Bull. Chem. Soc. Jap.* 42: 2038-2040.
- Beaudette P., Rossi N.A, Hoesgen P.F, Yu, X., Shenoi R.A., Doucet A., Overall C.M., Kizhakkedathu J.N. (2011) Development of Soluble Ester-linked Aldehyde Polymers for Proteomics. *Anal. Chem.* 83: 6500-6510.

- Benaqlia, M., Danelli, T., Pozzi, G. (2003) Synthesis of Poly(ethylene glycol)-supported Manganese Porphyrins: Efficient, Recoverable and Recyclable Catalysts for Epoxidation of Alkenes. *Org. Biomol. Chem.* 1: 454-456.
- Benerji, K.K. (1973) Kinetics and Mechanism of the Oxidation of Benzyl Alcohol to Benzaldehyde by Acid Permanganate. *J. Chem. Soc., Perkin Trans. 2.* 4: 435-437.
- Benerji, K.K. (1973) Kinetics and Mechanism of the Oxidation of Benzyl Alcohol to Benzaldehyde by Acid Permanganate. *J. Chem. Soc. Perkin II.* 435-437.
- Bertini, I., Gray, H.B., Lippard, S.J., Valentine, J.S. (1994) Bioinorganic Chemistry. United State of America, University Science Book.
- Battioni, P., Renaud, J.P., Bartoli, J.F., Artiles, M.R.-, Fort, M., Mansuy, D. (1988) Monooxygenase-like Oxidation of Hydrocarbons by H₂O₂ Catalyzed by Manganese Porphyrins and Imidazole: Selection of the Best Catalytic System and Nature of the Active Oxygen Species. *J. Am. Chem. Soc.* 110: 8462-8470.
- Beyene, B.B., Mane, S.B., Hung, C.-H. (2015) High Efficient Electrocatalytic Hydrogen Evolution from Neutral Aqueous Solution by a Water-Soluble Anionic Cobalt(II) Porphyrin. *Chem. Commun.* 51: 15067-15070.
- Bhyrappa P., Young, J.K., Moore, J.S., Suslick, K.S. (1996) Shape Selective Epoxidation of Alkenes by Metalloporphyrin-Dendrimers. *J. Mol. Catal. A: Chem.* 113: 109-116.
- Biesaga, M., Pyrzyńska, K., Trojanowicz, M. (2000) Porphyrin in Analytical Chemistry. A Review. *Talanta.* 51: 209-224.
- Böhm, P. and Gröger, H. (2015) Iron(III)-porphyrin Complex FeTSP: A Versatile Water-soluble Catalyst for Oxidations in Organic Syntheses, Biorenewables Degradation and Environmental Applications. *Chem. Cat. Chem.* 7: 22-28.
- Bommarius, A.S., Riebel, B.R. (2004) Biocatalysis. *Weinheim, Willy-VCH.*
- Borboloi, A., Mathew, N.T., Lefebvre, F., Halligudi, S.B. (2008) Inorganic-organic Hybrid Materials based on Functionalized Silica and Carbon: A Comprehensive Understanding toward the Structural Property and Catalytic Activity difference over Mesoporous Silica and Carbon Supports. *Mesopor & Micropor Mater.* 115: 345-355.
- Borcherding, H., Leikefeld, S., Frey, C., Diekmann, S., and Steinrucker, P. (1999). Enzymatic Microtiter Plate-Based Nitrate Detection in Environmental and Medical Analysis. *Anal Biochem.* 282: 1-9.

- Borissevitch, I.E., Tominaga, T.T., Imasato, H., Tabak, M. (1997) Resonance Light Scattering Study of Aggregation of Two Water Soluble Porphyrin Due to Their Interaction with Bovine Serum Albumin. *Anal. Chim. Acta.* 343: 281-286.
- Boucher, L.J. and Katz, J.J. (1966) The Infrared Spectra Metalloporphyrins (4000-160 cm^{-1}). *J. Am. Chem. Soc.* 89: 1340-345.
- Bowman-James, K. and Werner, A. (2005). The Coordination Chemistry of Anions. *Acc. Chem. Res.* **38**, 671-678.
- Bragg, W.L. (1973) The Diffraction of Short Electromagnetic Waves by a Crystals. *Proc. Chem. Shil. Soc.* 17: 43-57.
- Briñas, R.P. and Brückner, C. (2005). Synthesis of 5,10-diphenylporphyrin. *Tetrahedron.* **58**, 4375-4381.
- Bruice, T.C., Noar, J.B., Ball, S.S., Venkataram, U.V. (1983) Monooxygen Donation Potential of 4a-Hydroperoxyflavins as Compared with Those of a Percarboxylic Acid and Other Hydroperoxides. Monooxygen Donation to Olefin, Tertiary Amine, Alkyl Sulfide, and Iodide Ion. *J. Am. Chem. Soc.* 105:2452-2463.
- Buchler, J.W. (1978) Synthesis and Properties of Metalloporphyrins. *The Porphyrins.* New York: Academic Press.
- Burri, E., Öhm, M., Daguene, C., Severin, K. (2005) Site-Isolated Porphyrin Catalysts in Imprinted Polymers. *Chem. A Eur. J.* 11: 5055-5061.
- Campestrini, S. and Meunier, B. (1992) Olefin Epoxidation and Alkane Hydroxylation Catalyzed by Robust Sulfonated Manganese and Iron Porphyrins Supported on Cationic Ion-Exchange Resin. *Inorg. Chem.* 31: 1999-2006.
- Cardona, F. and Permezziani, C. (2015) Transition Metal Catalysis in Aerobic Alcohol Oxidation. *Italy:* Royal Chemical Society.
- Castro, K.A.D.F., Halma, M., Machado, G.S., Ricci, G.P., Ucoski, G.M., Ciuffi, K.J., Nakagaki, S., (2010) Preparation of Catalysts based on Iron(III) Porphyrins Heterogenized on Silica Obtained by the Sol-Gel Process for Hydroxylation and Epoxidation Reactions. *J. Braz. Chem. Soc.* 21: 1329-1340.
- Chahai, M.K. and Sankar, M. (2015) 1,8-Naphthylthyridine-based Fluorescent Receptors for Picric detection in Aqueous Media. *Anal. Methods.* 7: 10272-10279.
- Chandra, B., Mahanta, S.P., Pati, N.N., Baskaran, S., Kanaparthi, R.K., Sivasankar, C., Panda, P.K. (2013) Calix[2]bispyrrolylarenes : New Expanded

- Calix[4]pyrroles for Fluorometric Sensing of Anions via Extended π -Conjugation. *Org Lett.* 15: 306-309.
- Chen, X., Ding, K., Jun, L. (2015) Synthesis, Identification and Application of Aldehyde Reactive Dyes. *Dyes & Pigments.* 123: 404-412.
- Chen, Y., Huang, Y., Xiu, J., Han, X., Bao, X. (2004) Direct Synthesis, Characterization and Catalytic Activity of Titanium-substituted SBA-15 Mesoporous Molecular Sieves. *Appl. Cat. A: Gen.* 273: 185-191.
- Cheng, B., Munro, O.Q., Marques, H.M., Scheidt, W.R. (1997) An Analysis of Porphyrin Molecular Flexibility – Use of Porphyrin Diacids. *J. Am. Chem. Soc.* 119: 10732-10742.
- Cho, S.J., Satoshi, S., Kazunori, I., Isao, K. (2002). A Simple Nitrate Sensor System Using Titanium Chloride and an Ammonium Electrode. *Sensor & Actuat B.* 85: 120-125.
- Choi, M.Y., Pollard, J.A., Webb, M.A., McHale, J.L. (2003) Counterion-Dependent Excitonic Spectra of Tetra(p-carboxyphenyl)porphyrin Aggregates in Acidic Aqueous Solution. *J. Am. Chem. Soc.* 125: 810-820.
- Choudary B.M., Kantam, M.L., Sreekanth, P., Bandopadhyay, T., Figueras, F., Tuel, A. (1999) Knoevenagel and Aldol Condensations Catalysed by a New Diamino-functionalised Mesoporous Material. *J. Mol. Catal. A.* 142: 361-365.
- Choudhary, V. and Dumbre, D.K. (2009) Oxidation of Benzyl Alcohol to Benzaldehyde by *tert*-Butyl Hydroperoxide over Nanogold Supported on TiO₂ and other Transition and Rare Earth Metal Oxide. *Ind. Eng. Chem. Res.* 51: 732-740.
- Chua, A.S.M., Takabatake, H., Satoh, H., Mino, T. (2003) Production of polyhydroxyalkanoates (PHA) by activated sludge treating municipal wastewater: effect of pH, sludge retention time (SRT), and acetate concentration in influent. *Water Res.* 37: 3602-3611.
- Ciriminna, R., Pandarus, V., Béland, F., Xu, Y.-J., Pagliaro, M. (2015) Heterogeneously Catalyzed Alcohol Oxidation for the Fine Chemical Industry. *Org. Process Res. & Dev.* 19: 1554-1558.
- Collini, E., Ferrante, C., Bozio, R. (2005) Strong Enhancement of the Two-Photon Absorption of Tetrakis(4-sulphonatophenyl)porphyrin Diacid in Water upon Aggregation. *J. Phys. Chem. B.* 109: 2-5.

- Comes, M., Aznar, E., Moragues, M., Marcos, M.D., Máñez, R.M., Sancenón, F., Soto, J., Villaescusa, L.A., Gil, L., Amorós, P. (2009) Mesoporous Hybrid Materials Containing Nanoscopic “Binding Pockets” for Colorimetric Anion Signaling in Water by using Displacement Assays. *Chem. Eur. J.* 15: 9024-9033.
- Cordes, D.B., Miller, A., Gamsey, S. Singaram (2007) Simultaneous Use of Multiple Fluorescence Reporter Dyes for Glucose Sensing in Aqueous Solution. *Anal. Bioanal. Chem.* 387: 2767-2773.
- Cordes, D.B., Miller, A., Gamsey, S., Sharrett, Z., Thoniyot, P., Wessling, R., Singaram, B. (2005) Optical Glucose Detection Across the Visible Spectrum Using Anionic Fluorescent Dyes and a Viologen Quencher in a Two-Component Saccharide Sensing System. *Org. Biomol. Chem.* 3: 1708-1713.
- Cragg, P.J. (2005). A Practical Guide to Supramolecular Chemistry. *United Kingdom.* John Willey & Sons, Ltd.
- Craig J., D., and Mary G., P. (1986) Buffer Capacity of Various Acetic Acid-Sodium Acetate Systems: A Lecture Experiment. *J. Chem. Edu.* 62: 337.
- Cristaldi, D.A., Capuano, R., D’urso, A. Randazzo, R., Paolesses, R., Natale, C.D., Purrello, R., Fragalà (2016) Spontaneous Deposition of Porphyrin-Based Layers on Polylysinated Substrates: Role of the Central Metal on Layer Structural and Sensing Properties. *J. Phys. Chem. C.* 120: 724-730.
- Czolk and Ache (1995) Fluorimetric Determination of Mercury with a Water-soluble Porphyrin and Porphyrin-doped Sol-gel Films. *Anal. Chim. Acta.* 304: 107-113.
- Daied, N.N., Atkinson, S.T., Nolan, K.B. (1993) Synthetic porphyrins/metalloporphyrins which mimic states in catalytic cycle of cytochrome P-450 and peroxidases. *Pure & Appl. Chem.* 65: 1547-1548.
- Das, O. and Paine, T.K. (2015) Copper Catalysts for Aerobic Oxidations of Alcohols. Cardona, F. and Parmegianni. 40. *UK: The Royal Society of Chemistry.*
- DBL™ Sodium Acetate Concentrated Injection [Data sheet]. Retrieved from: www.medsafe.govt.nz/profs/datasheet/d/dblsodiumacetatesol.pdf.
- Delmarre, D., Renault, R.M., Charreton, C.B., Pasternack, R.F. (1999) Incorporation of Water-soluble Porphyrins in Sol-gel Matrices and Application to pH sensing. *Anal. Chim Acta.* 401: 125-128.

- Donald, T.S. (2001) The Nature of the Bonding between Metalloporphyrins [Fe(II), Co(II), Mn(II)] and Oxygen Species ($\cdot\text{O}_2$, $\text{H}_2\text{O}^+\cdot/\text{HO}\cdot$, $\text{HOO}\cdot$, $\text{O}\cdot$). *J. Porphyrin & Phthalocyanine*. 5: 889-894.
- Dong, Z. and Scammells, P.J. (2007) New Methodology for the D-methylation of Opiate Alkaloid. *J. Org. Chem.* 72: 9881-9885.
- Dorough, G. D., Miller, J. R. and Huennekens, F. M. (1951) Spectra of the metallo-derivatives of α , β , γ , δ - tetraphenylporphine. *J. Am. Chem. Soc.* 73. 4315-4320.
- Eaton, S.S. and Eaton, G.R. (1976) Carbon-13 Nuclear Magnetic Resonance of Substituted Tetraphenylporphyrins and Their Complexes with Ruthenium, Indium and Titanium. *Inorg. Chem.* 15:134-137.
- El-Safty, S.A. (2009) Organic-Inorganic Hybrid Mesoporous Monoliths for Selective Discrimination and Sensitive Removal of Toxic Mercury Ions. *J. Mater. Sci.* 44: 6764-6774.
- El-Safty, S.A., Ismail, A.A., Matsunaga, H., Hanaoka, T., Mizukami, F. (2008) Optical Nanoscale Pool-on-Surface Design for Control Sensing Recognition of Multiple Cations. *Adv. Funct. Mater.* 18: 1485-1500.
- Ember, L. (1990) Added Gene Corrects Cystic Fibrosis Cells. *Chem & Engineering News Archive*. 5a-6.
- Engelhardt, G. and Michel, D. (1987) High Resolution Solid-State NMR of Silicates and Zeolites. *Norwich: John Willey & Sons*.
- EnzyChrom™ Acetate Assay Kit [Data Sheet] Retrieve from: <https://www.bioassaysys.com/Acetate-Assay-Kit.html>
- Erdema, M. and Bedir, A. (2014) A Novel Method for the Determination of Urinary Citrate Levels: Ion Pair and High Performance Liquid Chromatography with Liquid Membrane Extraction Technique. *J. Exp. Clin. Med.* 31: 237-240.
- Esparza, J.M., Ojeda, M.L., Campero, A., Domínguez, A., Kornhauser, I., Rojas, F., Vidales, A.M., López, R.H., Zgrablich, G. (2004) N_2 Sorption Behavior of SBA-15 Porous Substrates. *Colloids & Surf. A: Physicochem. Eng. Aspects*. 241: 35-45.
- Espinosa, M., Pacheco, S., Vargas, S., Estevez, M., Llanos, M.E., Rodríguez (2011) Homogenous and Heterogeneous Catalytic Behavior of Ni-porphyrines Immobilized in SBA-15 for Esterification of DMT. *Appl Catal. A*. 401: 119-123.

- Eur J. (1979). IUPAC and IUB Joint Commission on Biochemical Nomenclature on tetrapyrroles. *Pure & Appl. Chem* 51: 2251.
- Everett, D. H. (1967) *The Solid-Gas Interface*. New York: Marcel Dekker.
- Ezoe, M., Yagi, S., Nakazumi, H., Itou, M., Araki, Y., Ito, O. (2006) Molecular Recognition of Viologen by Zinc Porphyrinic Receptors with Diarylurea Sidearms. Towards Construction of a Supramolecular Electron Transfer System. *Tetrahedron*. 62: 2501-2510.
- Fagadar-Cosma, E., Mirica, M.C., Balcu, I., Bucovicean, C., Cretu, C., Armeanu, I., Fagadar-Cosma, G. (2011) Syntheses, Spectroscopic and AFM Characterization of Some Manganese Porphyrins and Their Hybrid Silica Nanomaterials. *Molecules*. 14: 1370-1388.
- Fan, M.K., Huang, C.Z., Li, Y.F. (2002) Fluorescent Microscopic Determination of Cadmium Water Samples with the Self-Ordered Ring of α , β , γ , δ -tetra(5-sulfophenyl)porphine Formed on the Solid Support of Glass Slides. *Anal. Chim. Acta* 453: 97-104.
- Feiters, M.C., Rowan, A.E., Nolte, R.J.M. (2000) From Simple to Supromolecular Cytochrome P450 mimics. *Chem. Soc. Rev.* 29: 375-384.
- Fleischer, E.B. (1970) Structure and Porphyrin and Metalloporphyrins. *Acc. Chem. Res.* 3: 105-112.
- Fleisher, E.B., Palmer, J.M., Srivastava, T.S., Chatterjee (1971) Thermodynamic and Kinetic Properties of an Iron-Porphyrin System. *J. Am. Chem. Soc.* 13: 3162-3166.
- Forman, L.W., Thomas, B.D., Jacobson, F.S. (1991) On-line monitoring and control of fermentation processes by flow-injection analysis. *Anal. Chim Acta*. 249: 101-111.
- Fuhrhop, J.-H. and Mauzerall, D. (1969) One-electron Oxidation Metalloporphyrins. *J. Am. Chem. Soc.* 91: 4174-4181.
- Fukushima, M. and Tatsumi, K. (2007) Degradation of Pentachlorophenol in Contaminated Soil Suspensions by Potassium Monopersulfate Catalyzed Oxidation by a Supramolecular Complex between Tetra(p-sulfophenyl)porphineiron(III) and Hydrxypropyl- β -Cyclodextrin. *J. Hazard. Mater.* 144: 222-228.
- G. Leofanti, M. Padovan, G. Tozzola, B. Venturelli (1998) Surface Area and Pore Texture of Catalysis. *Catal Today*. 41: 207-219.

- Gao, B., Chen, Y., Lei, Q. (2012) Hydroxylation of Cyclohexane with Molecular Oxygen Catalyzed by Highly Efficient Heterogeneous Mn(III) Porphyrin Catalysts Prepared by Special Synthesis and Immobilization Method. *J. Inclusion Phenom Macrocyclic Chem.* 74: 455-465.
- Giovanetti, R. (2011) The Use of Spectrophotometry UV-Vis for the Study of Porphyrins in Macro to Nano Spectrometry. Ed. Jamal Uddin, Intech *Eur.*, Ch. 6: 88-108.
- Gispert, J.R. (2008) Coordination Chemistry. *Wienhem*: Willey-VCH Verlag GmbH & Co. KGaA.
- Glagolev, N.N., Belyaev, V.E., Rzheznikov, V.M., Solov'eva, A.B., Golubovskaya, L.E., Kiryukhin, Y.I., Luzgina, V.N. (2009) Effect of the Nature of Polymer Matrix on the Process of Cholesterol Photooxidation in the Presence of Immobilized Tetraphenylporphyrins. *Russian J. of Phys. Chem. A.* 83: 2362-2367.
- Gmurek, M., Kubat, P., Mosinger, J., Miller, J.S. (2010) Comparison of two photosensitizers Al(III) Phthalocyanine Chloride Tetrasulfonic Acid and *Meso*-tetrakis(4-sulfonatophenyl)porphyrin in the Photooxidation of n-butylparaben. *J. Photochem. & Photobio. A.* 223: 50-56.
- Goswami, S., Das, A.K., Sen, D., Aich, K., Fun, H.-K., Quah, C.K. (2012) A Simple Naphthalene-Based Colorimetric Sensor Selective for Acetate. *Tetrahedron Lett* 53: 4819-4823.
- Gouterman, M. (1978) The Porphyrins. *Phy. Chem. Part A.* 3: 1-165.
- Grand, C.L., Han, H., Munoz, R.M., Weitman, S., Von Hoff, D.D., Hurley, L.H. and Bearss, D.J. (2002) The Cationic Porphyrin TMPyP4 Down-Regulates c-MYC and Human Telomerase Reverse Transcriptase Expression and Inhibits Tumor Growth in Vivo. *Mol. Cancer Therapeutics.*1: 565-573.
- Gregg, S. J. and Sing, K. S. W. (1982) Adsorption, Surface Area and Porosity. *London*: Academic Press.
- Gross, Z. and Simkhovich, L. (1998). Hydroxylation of Simple Alkanes by Iodosylbenzene is Catalyzed More Efficiently by Second than by Third Generation Iron(III) Porphyrins. *Tetrahedron Lett.* 39, 8171-8174.
- Groves, J.T., Nemo, T.E., Myers, R.S. (1979) Hydroxylation and Epoxidation catalyzed by Iron-porphine Complexes. Oxygen Transfer from Iodosylbenzene. *J. Am. Chem. Soc.* 101: 1032-1033.

- Groves, K., Wilson, A.J., Hamilton, A.D. (2004) Catalytic Unfolding and Proteolysis of Cytochrome C Induced by Synthetic Binding Agents. *J. Am. Chem. Soc.* 126: 12833-12842.
- Gryko, D. and Lindsey, J.S. (2000) Rational Synthesis of Meso-Substituted Porphyrins Bearing One Nitrogen Heterocyclic Group. *J. Org. Chem.* 65: 2249-2252.
- Guého, C., Halma, M., Charradi, K., Forano, C., Mousty, C. (2011) Structural and Electrochemical Characterization of Metallo-Porphyrins Intercalated into ZnCr-Layered Double Hydroxides: some Evidence of Dimer Formation. *New J. Chem.* 35: 1898 - 1905.
- Gunter, M.J. and Turner, P. (1991) The Role of Axial Ligand in Meso-tetraarylmetalporphyrin Models of the P450 Cytochromes. *J. Mol. Catal.* 66: 121-141.
- Gupta, V.K., Goyal, R.N., Sharma, R.A. (2008) Anion Recognition Using Newly Synthesized Hydrogen Bonding Disubstituted Phenylhydrazone-Based Receptors: Poly(vinyl Chloride)-Based Sensor for Acetate. *Talanta.* 76: 859-864.
- Haddad, R.E., Gazeau, S., Pecaut, J., Marchin, J.C., Medforth, C.J., Shelnut, J.A. (2003) Origin of the Red Shift in the Optical Absorption Bands of Nonplanar Tetraalkylporphyrins. *J. Am. Chem. Soc.* 125: 1253-1268.
- Hagen, J. (2006). Industrial Catalysis: A Practice Approach. (2nd, completely rev. and extended ed.) *Weinheim: Wiley-VCH.*
- Hagiwara, H., Inoue, T., Kaneko, K., Tatsumi, I. (2009) Charge-Transfer Mechanism in Pt/KTa(Zr)O₃ Photocatalysts Modified with Porphyrinoids for Water Splitting. *Chem. A Eur. J.* 15: 12862-12870.
- Halma, M., Castro, K.A.D.d.F., Prévot, V., Forano, C., Wypych, F., Nakagaki, S. (2009) Immobilization of Anionic Iron(III) Porphyrins into Ordered Macroporous Layered Double Hydroxides and Investigation of Catalytic Activity in Oxidation Reactions. *J. Mol. Catal.: Chem.* 310: 42-50.
- Hamon, L., Heymans, N., Llewelyn, P.L., Guilerm, V., Ghoufi, A., Vaesen, S., Maurin, G., Serre, C., Weireld, G.D., Pirngruber, G.C. (2012) Separation of CO₂-CH₄ Mixtures in the Mesoporous MIL-100(Cr) MOF: Experimental and Modelling Approaches. *Dalton Tran.* 41: 4052-4059.

- Hatano, K., Usui, K., Ishida, Y. (1981) Redox Reaction of the Central Metal Ions Coordinated to Tetra-(p-sulfophenyl)porphine(TPPS) I. Photoreduction of Co(II)TPPS by Methanol and 2-Propanol. *Bull. Chem. Soc. Jpn.* 54: 413-419.
- Hatay, I., Su, B., Méndez, M.A., Corminboeuf, C., Khoury, T., Gros, C.P., Bourdilon, M., Meyer, M., Barbe, J.-M., Ersoz, M., Zális, S., Samec, Z., Girault, H.H. (2010) Oxygen Reduction Catalyzed by a Fluorinated Tetraphenylporphyrin Free Base at Liquid/Liquid Interfaces. *J. Am. Chem. Soc.* 132: 13733-13741.
- Headicke, I.E., Li, T., K., Zhu, Y.L.K., Martinez, F., Hamilton, A.M., Murrell, D.H., Nofiele, J.T., Cheng, H.-L. M., Scholl, T.J., Fostar, P.J., Zhang, X.-an (2016) An Enzyme-Activatable and Cell-Permeable Mn^{III}- porphyrin as Highly Efficient T₁ MRI Contrast Agent for Cell Labelling. *Chem. Sci.* Edge Article.
- Herath, A.C., Karunaratne, V., Rajapakse, R.M.G., Wickramasinghe, A. (2012) Electrochemical Investigation of the New Dyad of the Zn²⁺ Derivative of *Meso*-5-(5-hydroxyphenyl)-10,15,20-tris(4-methoxyphenyl)porphyrin and *Meso*-5-(4-hydroxyphenyl)-10,15,20-trisphenylporphyrin Points to Photoinduced Electron Transfer. *J. Natn. Sci. Foundation Sri Lanka.* 40: 149-156.
- Herrmann, O., Mehdi, S.H., Corsin, A. (1977) Heterogeneous Metal Insertion: A Novel Reaction with Porphyrins. *Can. J. Chem.* 56: 1084-1087.
- Heuer, V., Elvert, M., Tille, S., Krummen, M., Mollar, X.P., Hmelo, L.R., Kai-Uwe Hinrichs, K.-U. (2006) Online $\delta^{13}\text{C}$ analysis of volatile fatty acids in sediment/porewater systems by liquid chromatography–isotope ratio mass spectrometry. *Limnol. Oceanogr.: Methods.* 4: 346-357.
- Hijji, Y.M., Barare, B., Zhang, Y. (2012) Lawsone (2-hydroxy-1,4-naphthoquinone) as a Sensitive Cyanide and Acetate Sensor. *Sensors & Actua. B.* 169: 106-112.
- Hirano, K., Suzuki, E., Ishikawa, A., Moroi, T., Shiroishi, H., Kaneko, M. (2000) Sensitization of TiO₂ Particles by Visible Light. *J. Photochem & Photobio. A.* 136: 157-161.
- Ho, C.-M., Zhang, J.-L., Zhou, C.-Y., Chan, O.-Y., Yan, J.J., Zhang, F.-Y., Huang, J.-S., Che, C.-M. (2010) A Water-Soluble Ruthenium Glycosylated Porphyrin Catalyst for Carbenoid Transfer Reactions in Aqueous Media with Applications in Bioconjugation Reactions. *J. Am. Chem. Soc.* 132: 1886-1894.

- Horváth, T., Kaizer, J. and Speier, G. (2004). Functional Phenoxazinone Synthase Models: Kinetic Studies on the Copper-Catalyzed Oxygenation of 2-Aminophenol. *J. Mol. Catal. A: Chem.* 215, 9-15.
- Hribar, B., Southhall, N.T., Vlachy, V., Dill, K.A. (2002) How Ions Affect the Structure of Water. *J. Am. Chem. Soc.* 12302-12311.
- Huang, W., Su, H., Li, J., Lin, H., Lin, H. (2010) An Acetate Sensor Based on Azo in Aqueous Media. *Spec. Chim. Acta A.* 77: 146-149.
- Ishii, H. and Tsuchai, H. (1987) Spectrophotometric and Analogue Derivative Spectrophotometric Determination of Trace Zinc with 5,10,15,20-Tetrakis(4-sulfophenyl)porphine in Presence of High Concentrations of Cadmium. *Anal Sci.* 3: 229-233.
- IUPAC-IUB Joint Commission on Biochemical Nomenclature, Nomenclature of Tetrapyrroles (1980) *Pure & Appl. Chem.* 51: 2251.
- James, D.A., Swamy, N., Paz, N., Hanson, R.N., and Ray, R. (1999) Synthesis and Esotrogen Receptor Binding Affinity of a Porphyrin-Estradiol Conjugate for Targeted Photodynamic Therapy of Cancer. *Bioinor & Med Chem Lett.* 9: 2379-2384.
- Jang, W.-D., Nishiyama, N., Zhang, G.-D., Harada, A., Jiang, D.-L., Kawauchi, S., Morimoto, Y., Kikuchi, M., Koyama, H., Aida, T., Kataoka, K. (2005) Supramolecular Nanocarrier of Anionic Dendrimer Porphyrins with Cationic Block Copolymers Modified with Polyethylene Glycol to Enhance Intracellular Photodynamic Efficacy. *Angew. Chem. Int. Ed.* 44: 419-423.
- Jeon, S., Lee, H.K., Choi, Y.-K. (1996) Redox Chemistry and Autoreduction of Non- μ -oxo Dimer-Forming [5,10,15,20-Tetrakis(2,6-dichlorophenyl)porphyrinato] Manganese(III) Chloride by Hydroxide Ion. *Bull. Korean Chem. Soc.* 17: 929-934.
- Jeong, E.-Y., Ansari, M.B., Mo, Y.-H., Park, S.-E. (2011) Removal of Cu(II) from Water by Tetrakis(4-carboxyphenyl)porphyrin-functionalized Mesoporous Silica. *J. of Hazard. Mat.* 185:1311-1317.
- Jeong, E.-Y., Mohd Bismillah Ansari, Park, S.E. (2011) Aerobic Baeyer-Villiger Oxidation of Cyclic Ketones over Metalloporphyrins Bridged Periodic Mesoporous Organosilica. *ACS Catal.* 1: 855-863.

- Jerzebinska, R., Korposh, S., James, S., Batty, W., Tatam, R., Lee, S.-W. (2012) Optical Gas Sensor Fabrication based on Porphyrin-Anchored Electrostatic Self-Assembly onto Tapered Optical Fibers. *Anal. Lett.* 45: 1297-1309.
- Jiro, T. (2000) Transition Metal Reagents and Catalysts – Innovation in Organic Synthesis. *England: John Willey & Sons, Ltd.*
- Johannes, K., Nina, E., Eberhard, S., Alfred, L. (2010) Characterization of Escherichia coli Suspensions Using UV/Vis/NIR Absorption Spectroscopy. *Anal. Met.* 2: 123-128.
- Joo, T.Y., Singh, N., Lee, G.W. and Jang, D.O. (2007) Benzimidazole-based Ratiometric Fluorescent Receptor for Selective Recognition of Acetate. *Tetrahedron Lett.* 48: 8846-8850.
- Joseph, R., Zhang, S., Ford, W.T. (1996) Structure and Dynamics of a Colloidal Silica-Poly(methylmethacrylate) Composite by ^{13}C and ^{29}Si MAS NMR Spectroscopy. *Macromol.* 29: 1305-1312.
- Jr, P.E.E and Lyons, J.E. (1989) Halogen Substituent Effects on the Catalytic Activity of Iron Porphyrin Complexes for Selective Air-Oxidation of Alkanes in the Liquid Phase. *Catal. Lett.* 3: 389-398.
- Kainosho, M. (1978) Hydroxylation and Epoxidation Catalyzed by Iron Porphine Complexes. Oxygen Transfer from Iodosylbenzene. *J. Am. Chem. Soc.* 19: 1032-1033.
- Kalný D., Albrecht-Gary, A.-M., Havel, J. (2001) Highly Sensitive Method for Palladium(II) Determination as a Porphyrinato Complex by Capillary Zone Electrophoresis. *Anal. Chim. Acta.* 439: 101-105.
- Kamaya, M., Sugimoto, H., Yanguchi, Y. (2014) A Simple and Rapid Method for the Detection of Non-Ionic Surfactants. *Amer. J. Anal. Chem.* 5: 1121-1128.
- Kamaya, M., Takahashi, J., Nagashima, K. (2004) Rapid and Simple Determination of a Cationic Surfactant by Absorption Induced by Vigorous Shaking. *Microchim Acta.* 144: 35-39.
- Kawamura, K., Igarashi, S., Yotsuyanagi, T. (2011a) Catalytic Activity of Nobel Metal Ions for the Degradation of 5,10,15,20-tetrakis(4-sulfonatophenyl)porphine in the Presence of Oxidizing Agent, and its Application to the Determination of Ultra Trace Amounts of Ruthenium. *Microchim. Acta.* 172: 319-326.
- Kawamura, K., Ikoma, K., Igarashi, S., Hisamoto, H., Yao, T. (2011b) Flow Injection Analysis Combined with a Hydrothermal Flow Reactor: Application to Kinetic

- Determination of Trace Amounts of Iridium Using a Water-Soluble Porphyrin. *Talanta*. 84: 1318-1322.
- Keevil, B.G., Owen, L., Thornton, S., Kavanaqh, J. (2005) Measurement of Citrate in urine using Liquid Chromatography Tandem Mass Spectrometry: Comparison with an Enzymatic Method. *Ann. Clin. Biochem.* 42: 357-363.
- Kervinen, K., Korpi, H., Leskelä, M., Repo, T. (2003) Oxidation of Veratryl Alcohol by Molecular Oxygen in Aqueous Solution Catalyzed by Cobalt salen-type Complexes: The Effect of Reaction Condition. *J Mol. Catal.* 203: 9-19.
- Khade, R.L. and Zhang, Y. (2015) Catalytic and Biocatalytic Iron Porphyrin Carbene Formation: Effects of Binding Mode, Carbene Substituent, Porphyrin Substituent, and Porphyrin Axial Ligand. *J. Am. Chem. Soc.* 137: 7560-7563.
- Korposh, S., Kodaira, S., Batty, W., James, S.W., Lee, S.-W. (2009) Nanoassembled Thin-Film Gas Sensor II. An Intrinsic Highly Sensitive Fibre Optic Sensor for Ammonia Detection. *Sensor & Mater.* 21: 179-189.
- Korposh, S.O., Takahara, N., Ramsden, J.J., Lee, S.-W., Kunitake, T. (2006) Nanoassembled Thin Gas Sensors. I. Ammonia Detection by Porphyrin-based Multilayer Film. *J. Bio. Phys. & Chem.* 6: 125-132.
- Kostas, I.D., Coutsolelos, A.G., Charalambidis, G., Skondra, A., (2007) The First Use of Porphyrin as Catalysts Cross-coupling Reactions: A Water-soluble Palladium Complex with A Porphyrin Ligand as an Efficient Catalyst Precursor for the Suzuki- Miyaura in Aqueous Media under Aerobic Conditions. *Tetrahedron Lett.* 48: 6688-6691.
- Král, V., Králová, J., Kaplánek, R., Bříza, T., Martásek (2006) Qua-vadis Porphyrin Chemistry? *Physiol. Res.* 55: S3-S26.
- Krebs, H.A. (1970) The History of the Tricarboxylic Acid Cycle, *Perspect Biol. Med.* 14: 166-167.
- Krishnamurthy, M. (1977) Kinetics of Anation Reactions of a Water-Soluble Rh(III)-Porphyrin. *Inorg. Chim. Acta.* 25: 215-218.
- Kruk, M. and Jaroniec, M. (1999) Characterization of Highly Ordered MCM-41 Silicas Using X-ray Diffraction and Nitrogen Adsorption. *Langmuir.* 15: 5279-5284.
- Kruk, M. and Jaroniec, M. (2000) Characterization of the Porous Structure of SBA-15. *Chem. Mater.* 12: 1961-1968.

- Kruk, M. and Jaroniec, M. (2015) From Adsorption to Ordered Mesoporous Materials: Jaroniec and Kruk. *Chem Mater.* 13: 1903-1904.
- Labat, G. and Meunier, B. (1989) Factors Controlling the Reactivity of a Ligninase Model Based on the Association of Potassium Monopersulfate to Manganese and Iron. *J. Org. Chem.* 54: 5008-5011.
- Lampman, G.M., Pavia, D.L., Kriz, G.S., Vyvyan, J.R. (2010) Spectroscopy. *Canada: Brooks/cole Cengage Learning.*
- Lee C. H., Dong, H. L. and Hong, J.I. (2001). Colorimetric anion sensing by porphyrin based anion receptor. *Tetrahedron Lett.* **42.** 8665-8668.
- Lee, K.A. and Nam, W. (1997) Determination of Reaction Intermediates in Iron Porphyrin Complex-Catalyzed Oxygenation of Hydrocarbons Using Isotopically Labeled Water: Mechanistic Insights. *J. Am. Chem. Soc.* 119: 1916-1922.
- Leeuwen, P. W. N. M. Van (2004) Homogenous Catalysis – Understanding The Art. *Netherlands: Kluwer Academic Publishers.*
- Levrard, B. and Herrmann. A. (2006) Light-induced Controlled Release of Fragrance Aldehydes from 1-Alkoxy-9,10-anthraquinones for Applications in Functional Perfumery. *Flavour & Fragr. J.* 21: 400-409.
- Li, C.-Y., Zhang, X.-B., Dong, Y.-Y., Ma, Q.-J., Han, Z.-X., Zhao, Y., Shen, G.-L., Yu, R.-Q. (2008) A Porphyrin Derivative Containing 2-(oxymethyl)pyridine Units Showing Unexpected Ratiometric Fluorescent Recognition of Zn²⁺ with High Selectivity. *Anal. Chim. Acta.* 616: 214-221.
- Li, C.Y., Zhou, Y., Li, Y.-F., Kong, X.-F., Zou, C.-X., Weng, C. (2013) Colorimetric and Fluorescent Chemosensor for Citrate Based on A Rhodamine and Pb²⁺ Complex in Aqueous Solution. *Anal. Chim. Acta* 774: 79-84.
- Li, Y., Yan, X., Jiang, G., Liu, Qiang, Song, J., Guo, C. (2007) Toluene Oxyfunctionalization with Air over Metalloporphyrin and Reaction Condition Optimization. *Chin. J. Chem. Eng.* 15: 453-457.
- Lillevtedt, M., Tonnesen, H. H., Hogset, A., Sande, S. A., Kristensen, S. (2011) Evaluation of Physicochemical Properties and Aggregation of the Photosensitizers TPCS2a and TPPS2a in Aqueous Media. *Pharmazie.* 66: 325-333.
- Lindsey, J. S., Scheirman, I.C., Henry C. H., Patrick C. Kearney and Marguerettaz, A.M. (1986). Rothmund and Adler-Longo Reactions Revisited: Synthesis of

- tetraphenylporphyrins under Equilibrium Conditions. *J. Org Chem*, **52**, 827-836.
- Liu, Z.H., Devaraj, S., Yang, C.-R., Yen Y.-P. (2012) A New Selective Chromogenic and Fluorogenic Sensor for Citrate Ion. *Sensor and Actuat B*. 174: 555-562.
- Luca, G.D., Romeo, A., Scolaro, L.M. (2006) Counteranion Dependent Protonation and Aggregation of Tetrakis(4-sulfonatophenyl)porphyrin in Organic Solvents. *J. Phys. Chem.* 110: 7309-7315.
- Luzgina, V.N., Fillipovich, E.I., Evstigneeva, R.P. (1977) Hemetapoprhyrin IX- Physicochemical Properties, Synthesis, Biological Activity and Clinical Use. *Pharmaceu. Chem. J.* 11: 613-620.
- Ma, H.-L. and Jin, W.-J. (2008) Studies on the Effects of Metals Ions and Counter Anions on the Aggregate Behaviours of *meso*-Tetrakis(p-sulfonatophenyl)porphyrin by Absorption and Fluorescence Spectroscopy. *Spectrochim. Acta Mol. Biomol. Spectrosc.* 71: 153-160.
- Ma, J., Liu, L., Li, S., Chen, Y., Zhuo, M., Shao, F., Gong, J., Tong, Z. (2014) Facile Assembly for Fast Construction of Intercalation Hybrids of Layered Double Hydroxides with Anionic Metalloporphyrin. *Dalton Trans.* 43: 9909-9915.
- Ma, S., Yue, Q., Li, Z. (2000) Theoretical Studies on the Structural Change in the N-protonated Tetraphenylporphyrin. *Sci in China.* 43: 253-260.
- MacWilliam, M.P. (2013) Citrate Test Protocol. *America*. ASM Microbel Library.
- Maitani, M.M., Zhan, C., Mochizuki, D., Suzuki, E., Wada, Y. (2013) Influence of Co-Existing Alcohol on Charge Transfer of H₂ Evolution under Visible Light with Dye-Sensitized Nanocrystalline TiO₂. *Applied Catal. B* 140-141: 406-411.
- Maiti, N.C., Mazumdar, S., Periasamy, N. (1998) J- and H- Aggregates of Porphyrin-Surfactant Complexes: Time Resolved Fluorescence and other Spectroscopic Studies. *J. Phys. Chem. B* 102: 1528-1538.
- Manaseen, J. and Bar Ilan, A. (1970) Metal Complexes of Phthalocyanine and α , β , γ , δ – Tetraphenylporphyrin as Heterogeneous Catalysts in Oxidative Dehydrogenation. Correlation between Catalytic Activity and Redox Potential. *J. Catal.* 17: 86-92.
- Manchester, J., Walkup, G., Rivin, O., You, Z. (2010) Evaluation of pKa Estimation Methods on 211 Druglike Compounds *J. Chem. Inf. Model.* 50: 565-571.
- Mansuy, D. (1993) Activation of Alkanes: The Biomimetic Approach. *Coordination Chem. Rev.* 125: 129-142.

- Mansuy, D. (1998) The Great Diversity of Reactions Catalyzed by Cytochromes P450. *Comp. Biochem. Physiol. C: Toxicol. Pharmacol.* 121: 5-14.
- Martinez-Lorente, M.A., Battioni, P., Kleemiss, W., Bartoli, J.F., Mansuy, D. (1996) Manganese Porphyrins Covalently Bound to Silica and Montmorillonite K10 as Efficient Catalysts for Alkene and Alkane Oxidation by Hydrogen Peroxide. *J. Mol. Catal. A.* 113: 343-353.
- Masters, C. (1981) Homogenous Transition Metal Catalysis – A Gentle Art. *London: Chapman & Hall Ltd.*
- Mbaraka, I.K., Radu, D.R., Lin, V.S.Y., Shanks, B.H. (2003) Organosulfonation Acid-functionalized Mesoporous Silica for the Esterification of Fatty Acid. *J. Catal.* 219: 329-336.
- McNall, M., Laurence, R.L., Conner, W.C. (2001) An experimental Approach to Test Sorption Mechanisms in MCM-41. *Micropor & Mesopor Mater.* 44-45: 709-716.
- Megazyme Citric Assay Kit [Data Sheet]. Retrieve from: <https://secure.megazyme.com/Citric-Acid-Assay-Kit>.
- Meleron, J.A., Arsuaga, J.M., Frutos, P.d., Iglesias, J., Sainz, J., Blázquez (2005) Direct Synthesis of Titanium-Substituted Mesostructured Materials Using Non-Ionic Surfactants and Titanocene Dichloride. *Micropor. & Mesopor. Mater.* 86: 364-373.
- Melero, J.A., van Grieken, R. Morales, G., Nuño, V. (2004) Friedal Crafts Acylation of Aromatic Compounds over Arenensulfonic containing Mesostructured SBA-15. *Catal. Commun.* 5: 131-136.
- Meruva, R.K., Chien, J. C.-Y., Young, C.C. *US Patent No: US 6689272 B2*. Retrieved on February 10, 2001, from <http://www.google.com/patents/US6689272>.
- Meunier, B. (1992) Metalloporphyrins as Versatile Catalyst for Oxidation Reactions and Oxidative DNA Cleavage. *Chem. Rev.* 92: 1411-1456.
- Meunier, B., de Visser, S.P., Shaik, S. (2004) Mechanism of Oxidation Reactions Catalyzed by Cytochrome P450 enzymes. *Chem. Rev.* 104: 3947-3980.
- Mifune, M., Odo, J., Iwado, A., Saito, Y. (1991) Uricase-Like Catalytic Activity of Ion-Exchange Resins Modified with Metalloporphyrins. *Talanta* 7: 779-783.
- Milgrom, L.R. (1997) The Colours of Life: An Introduction to Chemistry of Porphyrin and Related Compounds. *U.K. Oxford University Press.*

- Ministry of Natural Resources and Environment Malaysia (2009) Study on the River Water Quality Trends and Indexes in Peninsular Malaysia. *Water Resource Pub.* 21.
- Moghadam, M., Tangestaninejad, S., Mirkhani, V., Baltork, I.M., Kargar, Hadi (2005) Mild and Efficient Oxidation of Alcohols with Sodium Periodate Catalyzed by Polystyrene-bound Mn(III)porphyrin. *Bioinorg. & Med. Chem.* 13: 2001-2005.
- Mori, S., Ishii, K., Hirakawa, Y., Nakamura, R., Hashimoto, K. (2011) In Vivo Participation of Artificial Porphyrins in Electron-Transport Chains: Electrochemical and Spectroscopic Analyses of Microbial Metabolism. *Inorg. Chem.* 50: 2037-2039.
- Moritz, M., and Łoniecki, M. (2012) SBA-15 Mesoporous Material Modified with APTES as the Carrier for 2-(3-benzoylphenyl)propionic Acid. *Applied Surf. Sci.* 258: 7523-7529.
- Morrison, D.J., Cooper, K., Waldron, S., Slater, C., Weaver, L.T., Preston, T. (2004) A Streamlined Approach to The Analysis of Volatile Fatty Acids and Its Application to The Measurement of Whole-Body Flux. *Rapid Commun. Mass Spectrom.* 18: 2953-2600.
- Motulsky, H. and Christopoulos, A. (2003) Fitting Models to Biological Data using Linear and Non-Linear Regression – A Practical Guide to Curve Fitting. *Graph Pad Prism.*
- Nabid, M.R., Shamsinanpouri, M., Sedghi, R., Bayandori, A., Moghaddam, Asadi, S., Osati, S., Safari, N. (2013) Biomimetic Synthesis of a Water-Soluble Conducting Polymer of 3,4-Ethylenedioxythiophene. *Chem. Eng. Technol.* 1: 130-136.
- Nagesh, N., Sharma, V.K., Kumar, G.A. and Lewis, E.A. (2010) Effect of Ionic Strength on Porphyrin Drugs Interaction with Quadruplex DNA Formed by the Promoter Region of C-myc and Bcl2 Oncogenes. *J. of Nucleic Acids* 2010: 1-9.
- Najafian, A., Rabbani, M., Rahimi, R., Deilamkamar, M., Maleki, A. (2015) Synthesis and Characterization of Copper Porphyrin into SBA-16 through “Ship in a Bottle” Method: A Catalyst for Photo Oxidation Reaction under Visible Light. *Solid State Sci.* 46: 7-13.

- Nakagaki, S., Benedito, F.L., Wypych, F. (2004) Anionic Iron (III) Porphyrin Immobilized on Silanized Kaolinite as Catalyst for Oxidation Reactions. *J. Mol. Catal A: Chem.* 217: 121-131.
- Nakagaki, S., Ferreira, G.K.B., Ucoski, G.M., Castro, K.A.D. de F. (2013) Chemical Reactions Catalyzed by Metalloporphyrin-Based Metal-Organic Frameworks. *Mol.* 18: 7279-7308.
- Nakazono, T., Parent, A.R., Sakai, K. (2013) Cobalt Porphyrins as Homogeneous Catalysts for Water Oxidation. *Chem. Commun.* 49: 6325-6327.
- Natali, M., Luisa, A., Iengo, E., Scandola, F. (2014) Efficient Photocatalytic Hydrogen Generation from Water by a Cationic Cobalt(II) Porphyrin. *Chem. Commun.* 50: 1842-1844.
- Neys, P.E.F., Venkelecom, I.F.J., Parton, R.F., Dehaen, W., Lábbé, G., Jacobs, P.A. (1997) The Oxidation of Cyclic Alcohols from an Aqueous Solution by Manganese Porphyrins Embedded in a Polydimethylsiloxane Membrane. *J. Mol. Catal. A.* 126: L9-L12.
- Ng, E.P. (2006) *Synthesis and Characterization of Sulphated ALMCM-41 and its Catalytic Activity in Dibenzoylation of Biphenyl with Benzoyl Chloride*. Master Thesis, Universiti Teknologi Malaysia, Skudai.
- Ogoshi, H., Watanabe, E., Yoshida, Z. (1973) Porphyrin Acids. *Tetrahedron.* 29: 3241-3245.
- Olaya, A.J., S., Delphine, Brevet, P.-F., Nagatani, H., Zimmermann, T., Vanicek, J., Xu, H.-J., Gros, C.P., Barbe, J.-M., Hubert H. Girault (2012) Self-assembled Molecular Rafts at Liquidliquid interfaces for Four-electron Oxygen Reduction. *J. Am. Chem. Soc.* 134: 498.
- Oliveros, G.G.-E., Mozo, A. P.-, Ortega, F.M., Ferronato, C., Chovelon, J.-M. (2009) Degradation of Atrazine using Metalloporphyrins Supported on TiO₂ under Visible Light Irradiation. *App. Cat. B: Environ.* 89: 448-454.
- Orcutt, B.N., LaRowe, D.E., Biddle, J.F., Colwell, F.S., Glazer, B.T., Reese, B.K., Kirkpatrick, J.B., Lapham, L.L., Mills, H.J., Sylvan, J.B., Wankel, S.D., Wheat, G. (2013). Microbial Activity in The Marine Deep Biosphere: Progress and Prospects. *Front. Microbiol.* 4:189.
- Özgün, B. and Pek, A. (1991) Kinetics and Mechanism of the Oxidation of Benzyl Alcohol by Potassium Chlorochromate. *React. Kinet, Catal. Lett.* 43: 589-594.

- Pasternack, R.F., Huber, P.R., Boyd, P., Engasser, G., Francesconi, L., Gibbs, E., Fasella, P., Cerio, V.G., Hinds, L. d. (1972) Aggregation of *meso*-Substituted Water-Soluble Porphyrins. *J. Am. Chem. Soc.* 94: 4511-4517.
- Patel, A. and Pathan, S. (2012) Solvent Free Selective Oxidation of Styrene and Benzyl Alcohol to Benzaldehyde over Eco-Friendly and Reusable Catalyst, Undecamolybdophosphate Supported onto Neutral Alumina. *Ind. Eng. Chem. Res.* 51: 732-740.
- Pepe, E., Abbas, O., Rebufa, C., Simon, M., Lacombe, S., Julliard (2005) Supported Photosensitizers for the Visible Light Activation of Phenols Towards Oxygen. *J. Photochem. & Photobio. A.* 170: 143-149.
- Petrarulo, M., Facchini, P., Cerelli, E., Marangella, M., Linari, F. (1995) Citrate in Urine Determined with a New Citrate Lyaase Method. *Clin. Chem.* 47: 1518-1521.
- Poltowicz, J. and Haber, J. (2004) The Oxyfunctionalization of Cycloalkanes with Dioxygen Catalyzed by Soluble and Supported Metalloporphyrin. *J. Mol. Catal.* 220: 43-51.
- Rashidi, A.M., Mizaeian, M., Jhodabakhshi, S. (2015) Synthesis of Carbon Nanotube-Supported Metalloporphyrin as a Nove; Nanocatalyst for the Mercaptan Removal. *J. Nat. Gas Sci. & Eng.* 25: 103-109.
- Razaeifard, A., Jafarpour, M., Naeimi, A. (2011) A Practical Innovative Method for Highly Selective Oxidation of Alcohols in Neat Water using Water-insoluble Iron and Manganese Porphyrins as Reusable Heterogeneous Catalysts. *Catal. Commum.* 16: 240-244.
- Rebelo, S.L., Melo, A., R. Coimbra, R., Azenha, M.E., Pereira, M.M., Burrows, H.D., Sarakha, M. (2006) Photodegradation of Atrazine and Ametryn with Visible Light using Water Soluble Porphyrins as Sensitizers. *Environ. Chem. Lett.* 5: 29-33.
- Ren, Q.-Z., Yao, Y., Ding, X.-J., Hou, Z.-S., Yan, D.-Y. (2009) Phase-transfer of porphyrins by polypeptide-containing hyperbranched polymers and a novel iron(III) porphyrin biomimetic catalyst. *Chem. Commun.* 4732-4734.
- Ribó, J.M., Crusats, J., Ferrera, J.-A., Valero, M.L. (1994) Aggregation in Water Solution of Tetrasodium Diprotonated *meso*-Tetrakis(4-sulphonatophenyl)porphyrin. *J. Chem. Soc., Chem. Commun.* 681-682.

- Ricchelli, F., Franchi, L., Miotto, G., Borsetto, L., Gobbo, S., Nikolov, P., Bommer, J.C. and Reddi E. (2005) *Meso*-Substituted Tetra-Cationic Porphyrins Photosensitize the Death of Human Fibrosarcoma Cells via Lysosomal Targeting. *The International J. of Biochem. & Cell Biol.* 37: 306-319.
- Ricoux, R., Allad, M., Dubuc, R., Dupont, c., Maréchal, J.-D., Mahy, J.P. (2009) Selective Oxidation of Aromatic Sulfide Catalyzed by an Artificial Metalloenzyme: New Activity of Hemoenzymes. *Org. & Biomol. Chem.* 7: 3208-3211.
- Rocha, I. and Ferreira, E.C. (2002) On-line Simultaneous Monitoring of Glucose and Acetate with FIA during High Cell Density Fermentation of Recombinant *E. Coli*. *Anal. Chim. Acta.* 462: 293-304.
- Rodrigues, J.M.M., Farinha, A.S.F., Muteto, P.V., Barreira, S.M.W.-, Paz, F.A.A., Neves, M.G.P.M.S., Caveleiro, J.A.S., Tomé, A.C., Gomes, M.T.S.R., Sessler, J.L., Tomé, J.P.C. (2014) New Porphyrin Derivatives for Phosphate Anion Sensing in both Organic and Aqueous Media. *Chem. Commun.* 50: 1359-1361.
- Rosa, I.L.V., Manso, C.M.C.P., Serra, O.A. and Iamamoto, Y. (2000) Biomimetical Catalytic Activity of Iron(III) Porphyrins Encapsulated in the Zeolite X. *J. Mol. Catal. A.* 160: 199-208.
- Rothemund, P., Menotti, A.R. (1941) Porphyrin Studies IV. The Synthesis of α , β , γ , δ – Tetraphenylporphine. *J. Am. Chem. Soc.* 63: 267-270.
- Sánchez, M.A.G.-, González, F.R.-E., Compos, C.M.-S.R., Solís, T.-, Segoviano, R. I.Y.Q.-, Alejo, L.A.D.-, Bañales, E.S.-, Campero, A. (2013) Crossed and Linked Histories of Tetrapyrrolic Macrocycles and their Use for Engineering Pores within Sol-Gel Matrices. *Mol.* 18: 588-563.
- Sanderson, R.T. (1983) Polar Covalence. *New York: Academic Press.*
- Satrio, J.A.B. and Doraiswamy (2001) Production of Benzaldehyde: A Case Study in a Possible Industrial Application of Phase-Transfer Catalysis. *Chem. Eng. J.* 82: 41-56.
- Sawant, K.R. (2004). *Imprinting the Surface of Mesoporous Aluminosilicates using Organic Structure-Directing Agents*. Doctor of Philosophy Thesis. University of Delaware.
- Sayari, A. and Yang, Y. (1999) Expanding of Pore Size of MCM-41 Silicas: Use of Amines as Expanders in Direct Synthesis and Postsynthesis Procedures. *J. Phys. Chem. B.* 103: 3651-3658.

- Schell-Feith, E.A., Moerdijk, A., Zwieten, P.H.T. van, Zonderland, H.M., Holscher, H.C., Holthe, J.K.-v., Heijden, B.J. van der (2006) Does citrate prevent nephrocalcinosis in preterm neonates, *Pediatric Nephrol.* 21 1830–1836.
- Selyanchyn, R., Korposh, S., Wakamatsu, Lee, S.-W. (2011) Simultaneous Monitoring of Humidity and Chemical Changes Using Quartz Crystal Microbalance Sensors Modified with Nano-thin Films. *Anal. Sci.* 27: 253-258.
- Serwicka, E.M., Połtowicz, J., Bahranowski, K., Olejniczak, Z., Jones, W. (2004) Cyclohexene Oxidation by Fe-, Co-, and Mn-metalloporphyrins Supported on Aluminated Mesoporous Silica. *Applied Catal. A.* 275: 9-14.
- Sessler, J.L., Cyr, M., Furuta, H., Král, V., Mody, T., Morishima, T., Shionoya, Weghom, Steven. (1993) Anion Binding: A New Direction in Porphyrin-Related Research. *Pure Appl. Chem.* 65: 393-398.
- Sessler, J.L., Karnas E., Sedenberg (2012) Porphyrins and Expanded Porphyrins as Receptors. *Supramol. Chem: From Mol to Nanomater.* Willey-VCH.
- Seybold, P.G. and Gouterman M. (1969) Porphyrins XIII. Fluorescence Spectra and Quantum Yields. *J. Mol. Spec.* 31: 1-13.
- Shah, P., Sridevi, N., Prabhune, A., Ramaswamy, V. (2008) Structural Features of Penicillin Acylase Adsorption on APTES functionalized SBA-15. *Micro & Meso Mater.* 116: 157-165.
- Shao, M., Han, J., Shi, W., Wei, M., Duan, X. (2010) Layer-by-Layer Assembly of Porphyrin/Layered Double Hydroxide Ultrathin Film and its Electrocatalytic Behavior for H₂O₂. *Electrochem. Commun.* 12: 1077-1080.
- Sheldon, R.A., Arends, I.W.C.E., Lempers, H.E.B. (1998) Liquid Phase Oxidation at Metal Ions and Complexes in Constrained Environments. *Catal. Today.* 41: 387-407.
- Shi, L., Hernandez, B., Selke, M. (2006) Singlet Oxygen Generation from Water-Soluble Quantum Dot – Organic Dye Nanocomposites. *J. Am. Chem. Soc. Comm.* 128: 6278-6279.
- Shul'pin, G.B. (2004) Oxidation of C-H Compounds Catalyzed by Metal Complexes in Beller, M. and Bolm, C., Transition Metals for Organic Synthesis. *Germany: Willey-VCH Verlag GmbH & Co. KGaA.*
- Siedlecka, E.M., Kumirska, J., Ossowski, T., Glamowski, P., Gołębiowski, M., Gajdus, J., Kaczyński, Z., Stepnowski, P. (2008) Determination of Volatile Fatty Acids

- in Environmental Aqueous Samples. *Polish J. of Environ. Stud.* 17: No. 3. 351-356.
- Simões, A.V.C., Adamowicz, A., Dąbrowski, J.M., Calverte, M.J.F., Abreu, A.R., Stochel, G., Arnaut, L.G., Pereira, M.M. (2012) Amphiphilic *Meso*(sulfonate ester fluoroaryl)porphyrins: Refining the Substituents of Porphyrin Derivatives for Phototherapy and Diagnostics. *Tetrahedron.* 68: 8767-8772.
- Sing, K.S.W., Everett, D.H., Haul, R., Moscou, L., Pieprotti, A., Rouquérol, J., Siemieniowska, T. (1985) Reporting Physisorption Data for Gas/Solid Systems with Special Reference to the Determination of Surface Area and Porosity. *Pure & Appl. Chem.* 57: 603-619.
- Smith, K.M. (1975) General Features of the Structure and Chemistry of Porphyrin Compounds. in, Buchler, JW., Porphyrin and Metalloporphyrin. *Netherland: Elsevier Scientific.* 187-189.
- Srivastava, S. and Tsuisui, M. (1978) Preparation and Purification of Tetrasodium *meso*-Tetra(p-sulfophenyl)porphine. An Easy Procedure. *J. Org. Chem.* 38: 2103.
- Stephenson, N.A. and Bell, A.T. (2007) Mechanistic Insight into Iron Porphyrin-Catalyzed Olefin Epoxidation by Hydrogen Peroxide: Factors Controlling Activity and Selectivity. *J. Mol. Catal. A.* 275: 54-62.
- Stevens and Atkins (2006) Dye-doped Inorganic/Organic Composite Films as Fluorescence Sensors for Methanol Vapor. *Sensor & Actuat. B.* 123: 59-64.
- Su, H., Li, J., Lin, H., Lin, H. (2010) An Efficient Acetate Anion Receptor based on Isatin. *J. Braz. Chem. Soc.* 21: 541-545.
- Sun, C., Zhao, J., Sun, Y., Zhang, X., Shen, J. (1998) Fabrication of a Multilayer Film Electrode Containing Porphyrin and its Application as a Potentiometric Sensor of Iodide Ion. *Talanta.* 46: 15-21.
- Suslick, K.S. and Watson, R.A. (1997) The Photochemistry of Chromium, Manganese, and Iron Porphyrin Complexes. *New. J. Chem.* 16: 633-642.
- Tabata, M. (1987) Kinetic Method for the Determination of Nanogram Amounts of Lead(II) using its Catalytic Effect on the Reaction of Manganese(II) with 5,10,15,20-tetrakis(4-sulphonatophenyl)porphine. *Analyst* 112: 141-144.
- Tabata, M. and Tanaka (1981) A Kinetic Method for the Determination of Nanogram Amounts of Cadmium(II) by Its Catalytic Effect on the Complex Formation of

- Manganese(II) with α , β , γ , δ -Tetra(p-sulfonatphenyl)porphine. *Microchim Acta*. 2: 149-158.
- Taguchi, A. and Schüth, F. (2005) Ordered Mesoporous Materials in Catalysis. *Micropor & Mesopor Mater.* 77: 1-45.
- Tanimoto, S., Matsumuram S., Toshima, K. (2008) Target-Selective Degradation of Proteins by Porphyrins upon Photo-irradiation. *Chem. Commun.* 3678-3680.
- Tavallali, H., Rad, G.D.-, Parhami, A., Hasanli, N. (2015) An Efficient And Ultrasensitive Rhodamine B-Based Reversible Colorimetric Chemosensor For Naked-Eye Recognition Of Molybdenum And Citrate Ions In Aqueous Solution: Sensing Behaviour And Logic Operation. *Spectrochim. Acta Mol & Biomol Spectrosc* 138: 253-261.
- Tian, J., Liu, S., Liu, Z., Yang, J., Zhu, J., Qiao, M., Hu, X. (2014) Fluorescence Quenching and Spectrophotometric Methods for the Determination of Daunorubicin with *Meso*-tetra(4-sulphophenyl)porphyrin as Probe. *Spectrochim Acta A: Mol. & Biomol. Spec.* 120: 7-13.
- Tojo, G. and Fernandez, M. (2006) Oxidation of Alcohols to Aldehydes and Ketones – A Guide to Current Common Practice. *U.S.A.:* Springer Sci. + Buis. Media, Inc.
- Trytek, M., Fiedurek, J., Polska, K. and Radzki, A. (2005). A Photoexcited Porphyrin System as a Biomimetic Catalyst for D-Limonene Biotransformation. *Catal. Lett.* 105, 119-126.
- Trytek, M., Majdan, M., Fiedureki (2011) Homogeneous and Heterogeneous Free-Based Porphyrins Incorporated to Silica Gel as Fluorescent Materials and Visible Light Catalysts Mimic Monooxygenases in Biomimetic Applications. *Europe: Intech.*
- Tsutsui, M., Ichikawa, M., Vohwinkel, F., Suzuki, K. (1966) Unusual Metalloporphyrins. I. Preparation of Chromium Mesoporphyrin IX Dimethyl Ester. *J Am. Chem. Soc.* 88: 854-855.
- Uemura, T., Kadowaki, Y., Yanai, N., Kitagawa, S. (2009) Template Synthesis of Porous Polypyrrole in 3D Coordination Nanochannels. *Chem. Mater.* 21: 4096-4098.
- Uttamlal, M. and Smith, A.S.H.- (2008) The Excitation Wavelength Dependent Fluorescence of Porphyrin. *Chem. Phys. Lett.* 454: 223-228.

- Valentinas, S. Bruzaite, I., Lendratis (2011) Porphyrin Nanotubes Film for Optical Gas Sensing. *Microelectron. Eng.* 88: 2459-2462.
- Valeur, B. (2012) Molecular Fluorescence – Principles and Applications. *German: Willey-VCH.* 35.
- Vallvey, L.F.C.-, Guerrero, E.A.-, Ramos, M.D.F.-, Gonzalez, F.S. (2005) Development of a One-Shot Optical Citrate Sensor Based on a Guanidinium Synthetic Receptor. *Microchimica Acta* 151: 93-100.
- Vansant, E.F., Voort, P.V.D., Vrancken, K.C. (1995) Characterization and Chemical Modifications on the Silica Surface. *Netherland. Elsevier. Science B.V.*
- Vanzi, F., Madan, B. Sharp, K. (1998) Effect of the Protein Denaturants Urea and Guanidium on Water Structure: A Structural and Thermodynamic Study. *J. Am. Chem. Soc.* 120: 10748-10753.
- Vedachalam, S., Choi, B.-H., Pasunooti, K.K., Ching, K.M., Lee, K., Yoon, H.S., Liu, X.-M. (2011) Glycosylated Porphyrin Derivatives and their Photodynamic Activity in Cancer Cells. *Med. Chem. Commun.* 2: 371-377.
- Watanabe, K., Kitagishi, H., Kano, K. (2011) Supramolecular Ferric Porphyrins as Cyanide Receptors in Aqueous Solution. *ACS Med Chem Lett.* 2: 943-947.
- Wedge, T. J. and Hawthorne, M.F. (2003). Multidendate Carborane-Containing Lewis Acids and Their Chemistry: Mercuracarborands. *Coor. Chem. Rev.* **240**, 111-128.
- Whittaker, J.W. (2003) Free Radical Catalysis by Galactose Oxidase. *Chem. Rev.* 103: 2347-2364.
- Wienkers, M., Ramos, J., Jemal, H., Cardenas, C., Wiget, P., Nelson, A., Free, S., Wu, J., Roach, R., Vulcan, M., Waynant, K., Fort, K., Vladimirova, A., Sun, J., Hunt, S.E., Rudkevich, D.M., Starnes, S.D. (2012) Enhanced Shape-Selective Recognition of Anion Guests through Complexation-Induced Organization of Porphyrin Hosts. *Org. Lett.* 14: 1370-1373.
- Wietzerbin, K., Meunier, B., Bernadou, J. (1997) Oxidation of Tertiary Diaryl Alcohols Catalyzed by a Water-Soluble Metalloporphyrin C_{aliph}-C_{aliph} versus C_{aliph}-C_{Ar} Bond Cleavage. *Chem. Commun.* 2321-2322.
- Wijesekera, T.P. and Dolphin D. (1994) Synthetic Aspects of Porphyrin and Metalloporphyrin Chemistry in Metalloporphyrin in Catalytic Oxidations. Ed. R.A. Sheldon, Marcel Dekker Inc., *New York*, Ch. 7: 193-239.

- Williams, L.D. (2016) Molecular Interactions (Noncovalent Interactions) Biological Systems [Data Sheet]. Retrieved from: http://ww2.chemistry.gatech.edu/~lw26/structure/molecular_interactions/mol_int.html#AD
- Williams, R.C., Boucher, R., Brown, J., Scull, J.R., Walker, J., Paolini, D. (1997) Analysis of Acetate Counter Ion and Inorganic Impurities in Pharmaceutical Drug Substances by Capillary Ion Electrophoresis with Conductivity Detection. *J. Pharm. Biomed. Anal.* 16: 469-479.
- Winkelman, J. (1962) The Distribution of Tetraphenylporphinesulfonate in the Tumor-bearing Rat. *Cancer Res.* 22: 589-596.
- Wolberg, A. and Manassen, J. (1970) Electrochemical and Electron Paramagnetic Resonance Studies of Metalloporphyrins and Their Electrochemical Oxidation Products. *J. Am. Chem. Soc.* 92: 2982-2991.
- Wu, J.J., Li, N., Li, K.-A., Liu, F. (2008) J-Aggregates of Diprotonated Tetrakis(4-sulfonatophenyl)porphyrin Induced by Ionic Liquid 1-Butyl-3-Methylimidazolium Tetrafluoroborate. *J. Phys. Chem. B.* 112: 81334-81338.
- Wu, L., Guo, Q.-S., Liu, Y.-Q., Sun, Q.-J. (2015) Fluorescence Resonance Energy Transfer-Based Ratiometric Fluorescent Probe for Detection of Zn²⁺ Using a Dual-Emission Silica-Coated Quantum Dots Mixture. *Anal. Chem.* 87: 5318-5323.
- Xu, X., Zhang, H., Zhang, C., Cheng, J. (1990) Separation and Determination of Trace Amounts of Copper, Zinc, Iron with *meso*-Tetra-(4-sulfophenyl)porphyrin Complexity High Performance Liquid Chromatography. *Chem. J. Chinese Uni.* 11: 947-951.
- Yabutani, T., Kurokawa, H., Hayashi, Y., Hugughi, H., Iwata, Y., Hashizume, Y., Wada, S., Hayashi, Y., Motonaka, J. (2010) Development of a Compact System for the Determination of Lead using a Liquid Core Waveguide and a Blue Diode as a Light Source. *Anal. Sci.* 26: 407-409.
- Yamada, Y., Matsumoto, S., Yamada, K., Nishino, T., Mihara, N., Sugimoto, K., Tanaka, K. (2014) Crystal Structures of Stacked Ionic Assemblies of Tetracationic and Tetraanionic Porphyrins. *Chem Lett.* 43: 1377-1379.
- Yang, L., Han, J., Liu, W., Li, J., Jiang, L. (2015) Conversion of Inhibition Biosensing to Substrate-Like Biosensing for Quinalphos Selective Detection. *Anal. Chem.* 87: 5270-5277.

- Yao, G.-P., Li, J., Luo, Y., Sun, W.-j. (2012) Efficient Visible Photodegradation of 4-Nitrophenol in The Presence of H₂O₂ By Using A New Copper(II) Porphyrin–TiO₂ Photocatalyst. *J. Mol. Cat A: Chem.* 361-362: 29-35.
- Yokoyama, Y., Kubo, H., Sato, H. (2008) Highly Sensitive Spectrophotometric Determination of Cationic Surfactants in Ground Waters as Their Cu(II)-TPPS Aggregates Proceeded by Solid-Phase Fractionation. *Talanta.* 77: 667-672.
- Yu, Y., Lu, B., Wang, X., Zhao, J., Wang, X., Cai, Q. (2010) Highly Selective Oxidation of Benzyl Alcohol to Benzaldehyde with Hydrogen Peroxide by Biphasic Catalysis. *Chem. Eng. J.* 162: 738-742.
- Yuan, L.-C. and Bruce, T.C. (1984) Oxygen Donation to Manganese(III) Tetraphenylporphyrin Chloride. Low Reactivity of Hydroperoxide as Oxygen Donors to Manganese(III) Porphyrin. *Inorg. Chem.* 24: 986-987.
- Yui, Tatsuto, Kobayashi, Y., Yamada, Y., Yano, K., Fukushima, Y., Torimoto, T., Takagi, K. (2011) Photoinduced Electron Transfer between the Anionic Porphyrins and Viologens in Titania Nanosheets and Monodisperse Mesoporous Silica Hybrid Films. *Appl. Mater. Interfaces.* 9: 931-935.
- Zakavi, S. and Hoseini, S. (2015) The Absorption and Fluorescence Emission Spectra of meso-tetra(aryl)porphyrin Dications with Weak and Strong Carboxylic Acids: A Comparative Study. *RSC Adv.* 5: 106774-106786.
- Zar, J.H. (2010) Biostatistical Analysis. U.S.A: Prentice Hall. 363-371.
- Zhang D. and Li J.H. (2012) Ordered SBA-15 Mesoporous Silica with High Amino-functionalization for Absorption of Heavy Metal Ions. *Chinese Sci. Bull.* 58: 879-883.
- Zhang, J., Zhao G.F., Popović, Z., Lu, Yong, Liu, Y. (2010) Pd-porphyrin Functionalized Ionic Liquid-modified Mesoporous SBA-15: An Efficient and Recyclable Catalyst for Solvent-free Heck Reaction. *Mater. Res. Bull.* 45: 1648-1658.
- Zhang, Y., Li, M.X., Lu, M.Y., Yang, R.H., Liu, F., Li, K.A. (2005) Anion Chelation-Induced Porphyrin Protonation and Its Application for Chloride Anion Sensing. *J. Phys. Chem. A.* 109: 7442-7448.
- Zhang, Y., Wang, H., Yang, R.H. (2007) Colorimetric and Fluorescent Sensing of SCN⁻ Based on meso-Tetraphenylporphyrin/meso-Tetraphenylporphyrin Cobalt(II) System. *Sensor.* 7: 410-419.

- Zhang, Y.R., Zhao, J.Q., He, L.Q., Zhao, D.M., Zhang, S.M. (2006) Manganese (III) Salen Complex Achored onto MCM-41 as Catalyst for the Aerobic Epoxidation of Olefins. *Micropor. Mesopor. Mater.* 94: 159-165.
- Zhao, D., Huo, Q., Feng, J., Chmelka, B.F., Stucky, G.D (1998) Nonionic Triblock and Star Diblock Copolymer and Oligomeric Surfactant Syntheses of Highly Ordered, Hydrothermally Stable Mesoporous Silica Structures. *J. Am. Chem. Soc.* 120: 6024-6036.
- Zhao, D.Y., Wan, Y., Zhou, W. (2013) Ordered Mesoporous Materials. *Germany: Willey-VCH Verlag & Co. KGaA.*
- Zhao, Z.-X., Li X.-Q., Wang X.-Q., Liu G.-F. (2000) Lanthanide Complexes with Acetylacetone and 5,10,15, 20-tetra[para-(4-chlorobenzoloxyl)phenyl]-porphyrin. *Chem. Res. in Chi Uni.* 16: 259-262.
- Zheng, W., Shan, N., Yu, L., Wang, X. (2008) UV-Visible, Fluorescence and EPR Properties of Porphyrins and Metalloporphyrins. *Dyes & Pigments*, 77: 153-157.
- Zheng, X., Qian, J., Tang, F., Wang, Z., Cao, C., Zhong, K. (2015) Microgel-Baesd Thermosensitive MRI Contrat Agent. *ACS Maro. Lett.* 4: 431-435.
- Zhi, F., Lu, X., Yang, J., Wang, X., Shang, H., Zhang, S., Xue, Z. (2009) Selective Anion Sensing through a Self-Assembled Monolayer of Thio-End-Functionalized Porphyrin. *J. Phys. Chem. C.* 113: 13166-13172.
- Zhu, Q., Maeno, S., Nishimoto, R., Miyamoto, T., Fukushima, M. (2014) Oxidative Degradation of Pentabromophenol in the Presence of Humic Substances Catalyzed by a SBA-15 Supported Iron-Porphyrin Catalyst. *J. Mol. Catal. A: Chem.* 385: 31-37.
- Ziólkowski, J.J., Pruchink, F., Szymanska-Buzar, T. (1973) The Structure of Oxotricobalt Acetate. *Inorg. Chim. Acta.* 7: 473.
- Zoltan, T., Vargas, F., López, V., Chávez, C., Rivas, C., Ramírez, A.H. (2015) Influenceof Charge and Metal Coordination of *Meso*-substituted Porphyrins on Bacterial Photoinactivation. *Spectrochim. Acta A: Mol. & Biomol. Spectro.* 135: 747-756.
- Zoltan, T., Vargas, F., López, V., Chávez, V., Rivas, C., Ramírez, Á.H. (2015) Influence of Charge and Metal Coordination of *Meso*-substituted Porphyrins on Photoinactivation. *Spectro. Chim. Acta Part A.* 135: 747-756.

Zucca, P., Neves, C.M.B., Simões, M.M.Q., Neves, M. da G.P.M.S., Cocco, G., Sanjust, E. (2016) Immobilized Lignin Peroxidase-Like Metalloporphyrins as Reusable Catalysts in Oxidative Bleaching of Industrials Dyes. *Mol.* 21: 964-1004.