

ONE STEP POTASSIUM HYDROXIDE ACTIVATED AND CALCIUM OXIDE  
DOPED CARBON CATALYST FOR TRANSESTERIFICATION OF RICE BRAN  
OIL

MUHAMMAD AZAM BIN MUHAMMAD ZAKI

A thesis submitted in fulfilment of the  
requirements for the award of the degree of  
Master of Philosophy

Faculty of Science  
Universiti Teknologi Malaysia

FEBRUARY 2019

## **DEDICATION**

Dedicated to my beloved parents, Muhammad Zaki bin Yacob and Zaidah binti Muhamad, to my siblings and family, to special person, Hawa Aqilah binti Hamuzan, to my friends, thank you so much for their patience, love and support.

## ACKNOWLEDGEMENT

All praise to almighty Allah, the, the most merciful and the most compassionate who blessed me with tolerant attitude, realistic thinking, supportive family and friends, talented supervisor and enabled me to complete this thesis. I could never have done this without the faith I have in you, the Almighty. This thesis is the result of effort on my part along with assistance of many others. Nevertheless, with the help of others, this work has finally come to fruition.

Upon completion of this project, I would like to express my gratitude to many parties. My special thanks and appreciation to my supervisor, Prof. Dr. Abdul Rahim Yacob for his help, suggestions and encouragement throughout my studies. This work would not have been completed without his keen interest. Special thanks to my senior Mohamad Raizul bin Zinalibdin for numerous advice, motivation and help along the completion of the thesis. I would also approach to thank all the lecturers and staff in Department of Chemistry for the diligent advice, suggestions and solutions right the way through this study.

Thanks to my family and friends who always give me their helpful effort. Their cooperation was appreciated and most thankful.

## ABSTRACT

Palm kernel shell are a cheap and abundant biomass from palm oil industries in many tropical countries like Malaysia and Indonesia. This agricultural by-product can be a good source for the production of activated carbon. Activated carbon can be used as catalyst support in transesterification reaction to produce biodiesel. Catalyst support is important to reduce the effects of leaching in heterogeneous catalyst process. Typical preparation of activated carbon catalyst support for transesterification reaction employs a two-step process. In this study, doped activated carbon was prepared in one step using palm kernel shell activated by potassium hydroxide (KOH) and doped with calcium oxide (CaO). The modified carbon was prepared via wet impregnation method using different amount of CaO while maintaining the same percentage concentration of KOH at 25% by weight before calcined at 500°C for 5 hours. The prepared carbon was then used as a heterogeneous base catalyst in transesterification reaction of rice bran oil with methanol. The modified carbon was characterized using thermogravimetric analysis (TGA), Fourier transformed infrared spectroscopy (FTIR), nitrogen adsorption analysis, field emission scanning electron microscope (FESEM), X-ray powder diffraction spectroscopy (XRD) and X-ray fluorescence spectroscopy (XRF). The basic strength of the sample was determined by back titration method. The final product of transesterification was then analysed using gas-chromatography-flame ionization detection (GC-FID) and gas-chromatography-mass spectrometry (GC-MS). XRF was employed to check the possibility of leaching of the metal catalyst into the biodiesel. TGA analysis indicates that complete calcination of palm kernel shells occur at 500°C. Thus, the activation of the modified carbon was done at 500°C. FTIR analysis of raw palm kernel shell shows the presence of various functional groups. However, after activation, most of the functional groups disappeared. BET surface area of 3.62 m<sup>2</sup>/g was obtained from the 25% CaO/KOH/C due to the filling of the metal catalyst into the cavities and pores of the modified carbon. This was confirmed by washing the modified carbon several times with hot water, which later increase the BET surface area to 443.84 m<sup>2</sup>/g. From the basicity analysis, increase in the percentage concentration of CaO increased the basicity of the prepared modified carbon. The performance of prepared modified CaO/KOH/C was identified by measuring the percentage yield of fatty acid methyl esters (FAMES) in the transesterification of rice bran oil with methanol. The percentage yield of FAMES for 0%, 10%, 15%, 20%, 25% and 30% CaO/KOH/C were 80.9%, 86.2%, 90.4%, 92.8%, 93.6% and 94.3%, respectively. Recyclability for the 25% CaO/KOH/C were studied and the catalyst can be reused for three consecutive runs with acceptable yield. Thus, it can be concluded that the preparation of one step KOH activated and CaO modified carbon from palm kernel shell can be used as catalyst in biodiesel production.

## ABSTRAK

Tempurung kelapa sawit adalah sisa pepejal yang murah dan banyak didapati daripada industri kelapa sawit di banyak negara tropika seperti Malaysia dan Indonesia. Hasil sampingan pertanian ini boleh dijadikan sumber yang baik bagi penghasilan karbon teraktif. Karbon teraktif boleh digunakan sebagai penyokong mangkin dalam tindak balas transesterifikasi untuk menghasilkan biodiesel. Penyokong mangkin adalah penting untuk mengurangkan kesan larut resap dalam proses pemangkin heterogen. Penyediaan penyokong mangkin karbon teraktif untuk tindak balas transesterifikasi lazimnya menggunakan proses dua langkah. Dalam kajian ini, karbon aktif terdopkan telah disediakan dalam satu langkah menggunakan tempurung kelapa sawit diaktifkan dengan kalium hidroksida (KOH) dan didop dengan kalsium oksida (CaO). Karbon terubahsuai ini disediakan melalui kaedah pengisitepuan basah menggunakan jumlah CaO yang berbeza manakala peratus kepekatan KOH dikekalkan pada 25% mengikut berat sebelum dikalsin pada 500°C selama 5 jam. Karbon yang disediakan kemudian digunakan sebagai mangkin bes heterogen dalam tindak balas transesterifikasi minyak bran beras dengan metanol. Karbon terubahsuai itu dicirikan menggunakan analisis termogravimetri (TGA), spektroskopi inframerah transformasi Fourier (FTIR), analisis penyerapan nitrogen, mikroskopi elektron pengimbas pemancaran medan (FESEM), spektroskopi pembelauan sinar-X (XRD) dan spektroskopi sinar-X pendarflour (XRF). Kekuatan bes sampel telah ditentukan dengan kaedah pentitratan kembali. Hasil akhir transesterifikasi itu kemudian dianalisis menggunakan kromatografi gas-pengesanan pengionan nyala (GC-FID) dan kromatografi gas-spectrometri jisim (GC-MS). XRF digunakan untuk mengesan kemungkinan logam mangkin larut resap pemangkin ke dalam biodiesel. Analisis TGA menunjukkan pengkalsinan lengkap tempurung kelapa sawit berlaku pada 500°C. Dengan itu, pengaktifan karbon terubahsuai telah dijalankan pada 500°C. Analisis FTIR tempurung kelapa sawit mentah menunjukkan kehadiran pelbagai kumpulan berfungsi. Walau bagaimanapun, selepas pengaktifan, kebanyakan kumpulan berfungsi itu telah hilang. Luas permukaan BET sebanyak 3.62 m<sup>2</sup>/g diperoleh daripada 25% CaO/KOH/C disebabkan pengisian mangkin logam ke dalam rongga dan liang karbon terubahsuai. Ini telah disahkan dengan membasuh karbon terubahsuai beberapa kali dengan air panas yang kemudiannya meningkatkan luas permukaan BET kepada 443.84 m<sup>2</sup>/g. Daripada analisis bes, peningkatan peratus kepekatan CaO telah meningkatkan kekuatan bes karbon terubahsuai yang disediakan. Prestasi karbon terubahsuai CaO/KOH/C yang disediakan telah dikenalpasti dengan mengukur peratus hasil ester metil asid lemak (FAME) dalam transesterifikasi minyak bran beras dengan metanol. Peratus hasil FAME bagi 0%, 10%, 15%, 20%, 25% dan 30% CaO/KOH/C ialah masing-masing 80.9%, 86.2%, 90.4%, 92.8%, 93.6% dan 94.3%. Penggunaan semula bagi 25% CaO/KOH/C telah dikaji dan mangkin itu boleh digunakan semula bagi tiga tindak balas berturut-turut dengan hasil yang boleh diterima. Dengan itu, boleh disimpulkan bahawa penyediaan karbon satu langkah teraktifkan-KOH dan terubahsuai-CaO daripada tempurung kelapa sawit boleh digunakan sebagai mangkin dalam pengeluaran biodiesel.

## TABLE OF CONTENTS

CHAPTER	TITLE	PAGE
	<b>DECLARATION</b>	ii
	<b>DEDICATION</b>	iii
	<b>ACKNOWLEDGEMENT</b>	iv
	<b>ABSTRACT</b>	v
	<b>ABSTRAK</b>	vi
	<b>TABLE OF CONTENTS</b>	vii
	<b>LIST OF TABLES</b>	xi
	<b>LIST OF FIGURES</b>	xii
	<b>ABBREVIATIONS</b>	xiv
	<b>LIST OF APPENDICES</b>	xv
<b>1</b>	<b>INTRODUCTION</b>	<b>2</b>
	1.1 Background of Research	2
	1.2 Problem Statement	8
	1.3 Objective of Research	9
	1.4 Scope of Research	10
	1.5 Significance of the Research	11
	1.6 Organization of Thesis	11
<b>2</b>	<b>LITERATURE REVIEW</b>	<b>12</b>
	2.1 Activated Carbon	12

2.1.1	Precursors for Activated Carbon	14
2.1.2	Palm Kernel Shell	15
2.1.3	Potassium Hydroxide as Chemical Activators and Catalyst	19
2.1.4	Preparation of Activated Carbon	23
2.1.5	Physical Activation	25
2.1.6	Chemical Activation	27
2.1.7	Carbon as Catalyst Support	32
2.2	Biodiesel	38
2.2.1	Rice Bran Oil as Feedstock	44
2.2.2	Homogeneous Catalyst	51
2.2.3	Heterogeneous Catalyst	55
2.2.4	Calcium Oxide as Catalyst	62
<b>3</b>	<b>METHODOLOGY</b>	<b>70</b>
3.1	Introduction	70
3.2	Materials	70
3.3	Method	71
3.3.1	Preparation of Modified Carbon by One Step Activation	71
3.3.2	Biodiesel Production by Transesterification of Rice Bran Oil	72
3.3.3	Reusability of Solid Catalyst	74
3.4	Sample Characterization	74
3.4.1	Thermogravimetric Analysis (TGA)	75
3.4.2	Fourier Transform Infrared Spectroscopy (FTIR)	75
3.4.3	Nitrogen Adsorption Analysis	76

3.4.4	Field Emission Scanning Electron Microscope (FESEM)	77
3.4.5	Energy Dispersive X-ray (EDX)	77
3.4.6	X-ray Powder Diffraction (XRD)	77
3.4.7	Back Titration Analysis	78
3.4.8	Carbon Dioxide – Temperature Program Desorption (CO <sub>2</sub> -TPD)	79
3.4.9	Gas Chromatography	79
3.4.10	X-ray Fluorescence	80
<b>4</b>	<b>RESULTS AND DISCUSSION</b>	<b>82</b>
4.1	Introduction	82
4.2	Characterisation of the Prepared Catalyst	83
4.2.1	Thermogravimetry Analysis of Palm Kernel Shell	83
4.2.2	Fourier Transform Infrared Spectroscopy (FTIR)	86
4.2.3	Back Titration Analysis of CaO/KOH/C	89
4.2.4	Carbon Dioxide Temperature Program Desorption (CO <sub>2</sub> - TPD)	91
4.2.5	Nitrogen Adsorption Analysis	93
4.2.6	Field Emission Scanning Electron Microscope (FESEM)	97
4.2.7	Elemental Analysis of Prepared Catalyst	99
4.2.8	X-ray Diffraction (XRD)	100
4.3	Transesterification Reaction of Rice Bran oil With Methanol to Biodiesel	102
4.3.1	Gas Chromatography Mass Spectrometer	102



4.3.2	Gas Chromatography Flame Ionization Detector	103
4.3.3	Optimisation of the Catalyst Reaction	105
4.3.4	Recyclability of the Prepared Catalyst	111
4.3.5	X-ray Fluorescence (XRF) Analysis of Biodiesel	112
<b>5</b>	<b>CONCLUSION</b>	<b>114</b>
5.1	Conclusion	114
5.2	Recommendations for Future Work	115
	<b>REFERENCES</b>	<b>116</b>
	<b>APPENDICES</b>	<b>137</b>

## LIST OF TABLES

TABLE NO	TITLE	PAGE
2.1	Type and definition of commercial activated carbon	13
2.2	Selected studies on the preparation of activated carbon by chemical activation	30
2.3	Selected studies on biodiesel production from heterogeneous catalyst	58
2.4	Selected studies on CaO as base catalyst in transesterification reaction	67
3.1	Chemicals used throughout this research work	71
3.2	Various reaction conditions for transesterification of rice bran oil	74
3.3	Experimental conditions for GC analysis	79
4.1	FTIR band assignment of raw PKS and the prepared catalyst	89
4.2	CO <sub>2</sub> -TPD desorption peak at different temperature of 25% CaO/KOH/C and washed modified carbon	93
4.3	Single point BET surface area of raw PKS, prepared C/KOH/CaO and washed modified carbon	94
4.4	Textural properties of synthesized 25% CaO/KOH/C and washed modified carbon	95
4.5	EDX analysis of prepared C/KOH/CaO samples	100
4.6	List of fatty acid methyl ester components in biodiesel product	103
4.7	Potassium and calcium content in oil before and after reaction	112

## LIST OF FIGURES

FIGURE NO	TITLE	PAGE
1.1	Overall transesterification of triglycerides with alcohol.	6
2.1	Transesterification of triglycerides with alcohol	42
3.1	Flow diagram for the preparation of modified carbon	72
3.2	Flow chart transesterification reaction to produce biodiesel	73
3.3	Overall methodology for one step KOH activation and CaO modified carbon in transesterification of rice bran oil with methanol	81
4.1	Thermogram of raw PKS	83
4.2	Percentage of weight lost at different temperature regions from TGA	85
4.3	Thermogram of prepared CaO/KOH/C	86
4.4	FTIR spectrum of raw PKS	88
4.5	FTIR spectrum of (a) 0% CaO/KOH/C, (b) 10% CaO/KOH/C, (c) 15%CaO/KOH/C, (d) 20%CaO/KOH/C, (e) 25%CaO/KOH/C and (f) 30%CaO/KOH/C	89
4.6	Amount of basic strength of the prepared CaO/KOH/C catalyst	90
4.7	CO <sub>2</sub> -TPD profile of (a) 25% CaO/KOH/C and (b) washed modified carbon	92
4.8 (a)	N <sub>2</sub> -adsorption-desorption isotherm of 25% CaO/KOH/C	96
4.8 (b)	N <sub>2</sub> -adsorption-desorption of washed modified carbon	96
4.9	FESEM image for raw PKS	97
4.10	FESEM micrograph for (a) 25% C/KOH/CaO catalyst and (b) washed carbon	98

4.11	XRD pattern of (a) 25% CaO/KOH/C and (b) washed modified carbon	101
4.12	Typical GC chromatogram of biodiesel produced from CaO/KOH/C	104
4.13	Percentage yield of rice bran oil using 0%, 10, 15%, 20%, 25% and 30% CaO/KOH/C	105
4.14 (a)	Effect of catalyst loading on transesterification of methanol with rice bran oil	106
4.14 (b)	Effect of methanol to oil molar ratio on the transesterification of rice bran oil with methanol	107
4.14 (c)	Effect of reaction temperature on the transesterification of rice bran oil with methanol	109
4.14 (d)	Effect of reaction time on the transesterification of rice bran oil with methanol	110
4.15	Percentage yield of FAME for 4 consecutive runs	111

## ABBREVIATIONS

AC	-	Activated Carbon
BET	-	Brunauer-Emmett Teller
CaO	-	Calcium Oxide
CaO/KOH/C	-	Potassium hydroxide and calcium oxide modified carbon
CO <sub>2</sub> -TPD	-	Carbon dioxide-Temperature Program Desorption
FAME	-	Fatty acid methyl ester
FESEM	-	Field Emission Scanning Electron Microscope
FID	-	Flame Ionization Detector
FTIR	-	Fourier Transform Infrared
GC-FID	-	Gas Chromatography- Flame Ionization Detector
GC-MS	-	Gas Chromatography Mass Spectrometer
KOH	-	Potassium hydroxide
PKS	-	Palm kernel shell
RBO	-	Rice bran oil
TGA	-	Thermogravimetric Analyzer
XRD	-	X-ray Powder Diffraction
XRF	-	X-ray Fluorescence

## APPENDICES (A-E)

APPENDIX	TITLE	PAGE
A	Calculation of basicity strength of CaO/KOH/C	133
B	Calculation of methanol to oil molar ratio	134
C	Calculation of percentage yield of FAME	135
D	XRD peaks assignments for 25% CaO/KOH/C	138
E	Publication and Conference	136

## CHAPTER 1

### INTRODUCTION

#### 1.1 Background of Research

Activated carbon (AC) is a black solid substance that can be present in granular or powder form. It is a carbonaceous material with a well-developed porosity and high mechanical strength. AC is known as one of the most versatile materials and can be used as a support and a good adsorbent. Moreover, the physical and chemical properties of activated carbon can be easily tailored to meet various specific needs. Its high surface area and well developed porosity make it desirable for several important industrial applications. Many industries including waste water treatment (Ribeiro *et al.*, 2015), chemical recovery process (Kaushik *et al.*, 2017) and separation treatment (Cermakova *et al.*, 2017) are using activated carbon in their process. Activated carbon can also be used as catalyst support (Samad *et al.*, 2017). Moreover, activated carbon can be used in high temperature and high pressure reactions because its adsorptive properties were not affected greatly at high temperature and pressure (Nowicki and Pietrzak, 2017).

As the production and regeneration of commercial AC are still expensive, there are many continuing researches for potential low cost raw material and methods (Acikyildiz *et al.*, 2014; Lounasvuori *et al.*, 2018; Wei *et al.*, 2018) . There is no limitation on the raw material that can be used to produce activated carbon. Almost any carbonaceous material with low organic volatile and high carbon content are desirable and can be converted into AC. The raw material and method used in the production of activated carbon would determine the quality of the activated carbon produced. Usually, the material used for the preparation of AC are fossil fuel generated

hydrocarbon and lignocelluloses from biomass wood or some agricultural waste. However, lignocellulose agricultural wastes are regarded as the most suitable raw materials for the production of AC. The advantage of using agricultural by-product as raw material for manufacturing AC is that these raw materials are potentially less expensive to manufacture and environmentally conscious (El-Sayed *et al.*, 2014). Furthermore, AC produced from this agricultural waste can also facilitate disposal problem of these waste products. Various studies had been proposed regarding the production of activated carbon from agricultural by-products including coconut shell (Sun *et al.*, 2017), pistachio nut shell (Niksiar and Nasernejad, 2017), hazelnut shell (Kwiatkowski and Broniek, 2017) sugar cane bagasse (Kaushik *et al.*, 2017), olive stones (Bohli *et al.*, 2015), macadamia nut shell (Rodrigues *et al.*, 2013) and palm kernel shell (Kundu *et al.*, 2015).

One of the most valuable crops in Malaysia is palm oil. Malaysia is accounted as one of the biggest producers and exporters of palm oil products. Recently, Malaysia had generated a total production of 21.5 million tonnes of palm oil export commodities and it is projected to reach 25.6 million tonnes of crude palm oil per year by 2050 (Umar *et al.*, 2018). In Malaysia, palm oil industries are the main producers of the abundant amount of lignocellulosic biomass. At present, large quantities of palm oil biomass exceeding 50 million tonnes, is produced annually (Liew *et al.*, 2015). The by-product of palm milling process include palm pressed fibre, palm kernel shell and empty fruit bunch (Uemura *et al.*, 2011). Palm kernel shell shows great potential as a precursor for activated carbon production compared to other biomass such as wood, nutshell and coconut shell. The natural characteristics of palm kernel shell make it suitable for AC production since it contains high oxygen and carbon content. These characteristics are known to produce good AC. Although currently some quantity of PKS are normally used as boiler feed to generate steam in the palm oil processing plant, the residue still remain as a surplus which is discarded by open burning or left in mill premises itself (Foo and Hameed, 2012). Therefore, it is profitable if the PKS are also be exploited to produce higher value product such as activated carbons.

With the aim of overcoming the accumulation of agricultural wastes, several attempts have been made to convert these biomasses into value added products such



as pulp and paper, particle boards, pelleted fuels, soil conditioners, animal feedstock, organic acids, activated carbon, plywood and fertilizer (Wahid, 2011; Oviasogie *et al.*, 2013). In addition, converting these agricultural waste into activated carbon is significant due to the increasing market demand on this carbonaceous material that is estimated to reach about 2.1 metric tonnes by year 2018 (Maneerung *et al.*, 2016a). In another point of view, conversion of these agricultural waste can elevate financial income and promote employment opportunities.


Generally, the preparation of AC may either use a physical or chemical activation method. Physical activation is a two-step process which are the carbonization step and activation step. In physical activation process the raw material is first carbonized followed by activation by steam or carbon dioxide. Whereas chemical activation can be done in a single step by thermal decomposition of raw material impregnated with chemical activating reagents such as zinc chloride ( $ZnCl_2$ ), phosphoric acid ( $H_3PO_4$ ), potassium hydroxide (KOH) and sodium hydroxide (NaOH). Chemical activation offers several advantages and disadvantages compared to physical activation. The main advantages are that it can produce a much higher yield at lower activation temperature with less activation time and it can be done in a single step. Moreover, it has a better pore development compared to physical activation process. However, among the disadvantages of chemical activation process is that the chemical activating agents are much more expensive and it is also requires a washing step after activation to remove the chemical activator (Maciá-Agulló *et al.*, 2004).

Currently, the world is facing a vital calamity with regards to energy and fossil fuel. This is because the demand for energy for economic development and population growth is increasing in the last few years. The most important concern is that energy source is typically derived from fossil fuel. This fossil fuel is non-renewable, it has a limited supply and one day it will be depleted. Thus, new source of energy is needed in order to reduce the energy dependence on fossil fuel and also produce less net pollution to the environment. Biodiesel being renewable and environment friendly are considered a feasible route to resolve this problem and has been commercialized as a substitute for petroleum base diesel. In addition, biodiesel is completely miscible with petroleum diesel and can be used as blending stock of petroleum base fuel.

The study of biodiesel as an alternative, nontoxic, biodegradable and renewable fuel is rapidly growing due to the dwindling of fossil fuel resource and the increasing demand for energy. Biodiesel is a non petroleum-based fuel having similar fuel properties as petroleum diesel usually produced from renewable resource such as vegetable oil or animal fat.

Biodiesel consists of mixture of long chain fatty acid alkyl esters mainly fatty acid methyl ester (FAME) or fatty acid ethyl ester (FAEE) (Moser, 2009). The use of biodiesel in conventional diesel engines can reduce the emission of unburnt hydrocarbon, carbon monoxide and particulate because vegetable oil esters contain 10-11% oxygen by weight that can enhance combustion compared to hydrocarbon base diesel (Agarwal, 2007). In general, in terms of power, wear, efficiency and emissions, biodiesel fuels are a viable alternative to petroleum based diesel. There are a few methods for the production of biodiesel including direct use and blending, micro emulsion, thermal cracking (pyrolysis) and transesterification.

The most successful ways of producing biodiesel is by transesterification reaction because it is cost effective and simpler method (Ma and Hanna, 1999). Biodiesel production through transesterification, also known as alcoholysis, involves a reaction between triglyceride with alcohol to produce alkyl ester and glycerol. The alcohol used is usually methanol or ethanol and the reaction usually needs a catalyst to enhance the reaction. The reaction consists of a series of consecutive reversible reactions to produce 3 mol of fatty acid alkyl ester and glycerol as a by-product. The overall reaction equation is shown in Figure 1.1. Generally, excess alcohol is needed to shift the forward reaction (Badday *et al.*, 2014). Triglyceride and the alcohol are not miscible, thus the presence of catalyst is necessary in transesterification reaction in order to achieve high conversion without any harsh reaction condition. Therefore, selection of a right catalyst is very important to get the highest conversion of vegetable oil into biodiesel (Dias *et al.*, 2012).

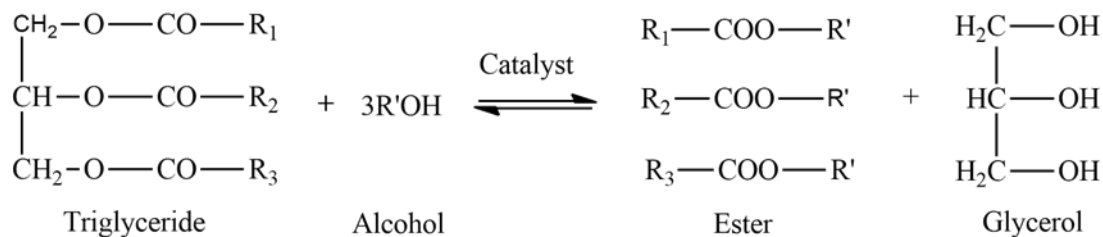

**Figure 1.1:** Overall transesterification reaction of triglyceride with alcohol (Ejikeme *et al.*, 2010)

There exist a wide variety of catalyst for transesterification reactions that can be either acid, base or even mixed oxide that can be present in homogenous or heterogeneous state. Currently, biodiesel is produced industrially by the transesterification of vegetable oil with methanol using a homogeneous base catalyst based on NaOH and KOH to achieve high conversion close to 100% at reaction temperature of around 60°C under less than 3 hours (Alcañiz-Monge *et al.*, 2013). Although the homogeneous catalysis process can produce high yield of biodiesel under mild reaction conditions with fast reaction rate, this process however involves different stages of purification of the biodiesel and the glycerol and it generates large amount of waste water effluents. To minimize the problems associated with this approach, heterogeneous catalytic process has been proposed. The main objective of using heterogeneous catalyst are to simplify the production process as well as to reduce the purification cost and environmental impacts. Heterogeneous catalyst offer several advantages over homogenous catalyst such as elimination of washing step to isolate the product, less corrosive, safer, and environmental friendly, which would reduce the total capital and energy cost (Agarwal *et al.*, 2012). Furthermore, heterogeneous catalyst can be reused and would not have to be continuously added.

A variety of solid bases has been reported to be a good heterogeneous catalyst for biodiesel transesterification. Metal oxides, hydroxides and alkoxides has been developed to catalyse the transesterification reaction of vegetable oil for biodiesel production. In the transesterification of vegetable oil or animal fat into biodiesel process, activated carbon can be used as a heterogeneous support catalyst. The main concern for heterogeneous catalysis is to achieve high surface area to enhance the reactivity and selectivity. This can be achieved by introducing a support to the catalyst

to disperse the catalyst species to obtain optimal performance. Most support can be tailored to meet its specific need either by functionalization or doping process. Support for heterogeneous catalysis can be alumina, zeolite, carbon nanofibre, activated carbon and metal oxide such as  $\text{TiO}_2$ , and  $\text{MnO}_2$  (Bagheri *et al.*, 2014). Occasionally, the preparation of heterogeneous catalyst can contribute to an additional cost. The use of simple, safe and low cost in the preparation of the catalyst can be attractive.

Therefore, in this study, an active and reusable catalyst based on modified carbon from palm kernel shell was produced through one step activation process using potassium hydroxide (KOH) as the activating agent and calcium oxide (CaO) as the catalyst to further increase the basicity of the modified carbon. The prepared modified carbon is then tested as a potential heterogeneous base catalyst in the synthesis of biodiesel from rice bran oil with methanol under a mild reaction conditions. In addition, this study also aimed to investigate the possibility of increasing the strength of basic sites of KOH and CaO mixed in order to improve their performance in the transesterification reaction. These two base catalyst was chosen due to their high basicity which is important for catalysing heterogeneously catalysed transesterification reaction.

## 1.2 Problem Statement

At present, the main industrial biodiesel production method is the alkali catalysed homogenous process between vegetable oil and methanol. According to the National Biofuel Policy report from 2016, the implementation of the 10% biodiesel blend (B10) planned for July 1st 2016 has been postponed to early 2017. This is due to the claim that a higher blend biodiesel above 7% could damage the engines (Zabid *et al.*, 2018). This is due to the contamination of the biodiesel with the catalyst because of poor separation between the biodiesel and the catalyst. Furthermore, a large amount of water is needed in order to remove the homogenous catalyst that is dissolved into the biodiesel and this washing step sometimes may lead to saponification reaction. To overcome the problem connected with the use of homogenous catalyst, attentions was directed toward the development of heterogeneous catalyst for biodiesel production. Heterogeneous catalyst are easy to separate from the reaction mixture, can be reused and will prevent catalyst contamination of the biodiesel (Kaur and Ali, 2014).

Among the different heterogeneous base catalyst, CaO is one of the most active. It is widely used in the transesterification reaction of vegetable oil with methanol to produce biodiesel. However, CaO present limitation in terms of leaching, because some of the  $\text{Ca}^{2+}$  is leached to the alcoholic phase, which would cause an additional process of neutralization and cleaning of the leached species. The leached species can reduce the catalytic property and reusability of the catalyst. Furthermore, the accumulation of these leached species also can harm the mechanical properties of the diesel engine. As a result, mixed oxide or a suitable support are used to increase the interaction between active phase and prevent leaching making the catalyst more stable (Syamsuddin *et al.*, 2015). In this study, CaO catalyst is supported on the modified carbon to reduce the leaching effect.

Generally, preparation of catalyst supported activated carbon involve two-step processes in which the activated carbon was first prepared followed by the impregnated of the catalyst species. Furthermore, in chemical activation process, the activating agent is left as impurities after heat treatment and sometimes may affect the chemical properties of the resulting activated carbon. Therefore, washing steps is

required to remove the remaining chemical activator, which is time consuming and sometimes lead to an environmental issue.

Rice is one of the major staple food in Malaysia making paddy farm agriculture another major industry in Malaysia. Rice bran oil is produced from rice bran which is mostly considered as agricultural waste in paddy farms plantations. As rice is being produced largely in Malaysia, the utilisation of wasted rice bran to obtain oil for biodiesel production will help to increase the value of rice and help to improve local economies. In addition, the use of rice bran oil from agricultural waste can help to reduce the food versus fuel competition which may result in the cost or food shortage (Zhao *et al.*, 2013).

Hence, in this study, palm kernel shell modified carbon was produced by means of chemical activation with KOH and CaO is doped into the activated carbon in a one-step activation process. In addition, instead of washing the activating agent, the impurities left in the activated carbon will be used as a base catalyst.

### **1.3 Objective of Research**

The objective of this study are :

1. To prepare and characterize potassium hydroxide and calcium oxide modified carbon catalyst (CaO/KOH/C) via one step activation process.
2. To apply the prepared catalyst as base heterogeneous catalyst in the transesterification reaction of rice bran oil with methanol.
3. To study the effect of leaching and recyclability of the catalyst.
4. To characterize the composition of biodiesel produce

#### **1.4 Scope of the Research**

The scope of the present study can be divided into 3 major aspects. The first aspect is the preparation of the potassium hydroxide and calcium oxide modified carbon catalyst by one step activation method. The activated carbon catalyst is prepared by impregnating different concentration of CaO at 0%, 10%, 15%, 20% and 25% concentration by weight while maintaining the concentration of potassium hydroxide at 25% concentration by weight into the palm kernel shell. Then, it is calcined at 500°C for 5 hours.

The second aspect is to characterize the prepared catalyst. Thermogravimetry analysis (TGA) for raw palm kernel shell was applied in order to determine the activation temperature. The prepared CaO/KOH/C catalyst were then characterized via Fourier Transform Infrared (FTIR), X-ray Powder Diffraction (XRD), X-ray Fluorescence (XRF) and Nitrogen Adsorption Analysis. Field Emission Scanning Electron Microscope (FESEM) analysed their surface morphology while energy dispersive x-ray (EDX) was used to identify the elemental composition of the prepared catalyst. The basicity and basic strength of the catalyst were analysed by back titration method and Temperature Programmed Desorption (CO<sub>2</sub>-TPD). The possibility of catalyst leaching into biodiesel will be analysed by determining the presence of potassium and calcium in the biodiesel product via X-ray Fluorescence (XRF).

The third scope of this study is to test the prepared CaO/KOH/C catalyst in the transesterification of rice bran oil with methanol. The analysis and yield of biodiesel were performed Gas Chromatography-Flame Ionization Detector (GC-FID) and the confirmation of the methyl esters were identified by Gas Chromatography Mass Spectrometer (GC-MS). The recyclability of the catalyst was done by washing the catalyst with hexane after the transesterification reaction and drying in oven overnight. The catalyst was then used in the next cycle of transesterification reaction and the effect of leaching was also studied.

## REFERENCES

- Abbaszaadeh, A., Ghobadian, B., Omidkhah, M.R., and Najafi, G. (2012) Current biodiesel production technologies: A comparative review. *Energy Conversion and Management*, **63**, 138–148. Elsevier Ltd.
- Abdel-ghani, N.T., El-chaghaby, G.A., Elgammal, M.H., Rawash, E.A., Abdel-ghani, N.T., El-chaghaby, G.A., Elgammal, M.H., and Rawash, E.A. (2016) Optimizing the preparation conditions of activated carbons from olive cake using KOH activation. *New Carbon Materials*, **31**, 2–10. Institute of Coal Chemistry, Chinese Academy of Sciences.
- Abdullah, N. and Sulaiman, F. (2013) The properties of the washed empty fruit bunches of oil palm. *Journal of Physical Science*, **24**, 117–137.
- Abechi, S.E., Gimba, C.E., Uzairu, A., and Dallatu, Y.A. (2013) Preparation and Characterization of Activated Carbon from Palm Kernel Shell by Chemical Activation. **3**, 54–61.
- Acikyildiz, M., Gurses, A., and Karaca, S. (2014) Preparation and characterization of activated carbon from plant wastes with chemical activation. *Microporous and Mesoporous Materials*, **198**, 45–49.
- Acosta, R., Fierro, V., Martinez de Yuso, A., Nabarlantz, D., and Celzard, A. (2016) Tetracycline adsorption onto activated carbons produced by KOH activation of tyre pyrolysis char. *Chemosphere*, **149**, 168–176. Elsevier Ltd.
- Adilla Rashidi, N. and Yusup, S. (2016) A Review on Recent Technological Advancement in the Activated Carbon Production from Oil Palm Wastes. *Chemical Engineering Journal*, **314**, 277–290. Elsevier B.V.
- Aditiya, H.B., Chong, W.T., Mahlia, T.M.I., Sebayang, A.H., Berawi, M.A., and Nur, H. (2016) Second generation bioethanol potential from selected Malaysia's biodiversity biomasses: A review. *Waste Management*, **47**, 46–61. Elsevier Ltd.
- Agarwal, A.K. (2007) Biofuels (alcohols and biodiesel) applications as fuels for internal combustion engines. *Progress in Energy and Combustion Science*, **33**, 233–271.
- Agarwal, M., Chauhan, G., Chaurasia, S.P., and Singh, K. (2012) Study of catalytic behavior of KOH as homogeneous and heterogeneous catalyst for biodiesel production. *Journal of the Taiwan Institute of Chemical Engineers*, **43**, 89–94. Taiwan Institute of Chemical Engineers.
- Al-Lagtah, N.M.A., Al-Muhtaseb, A.H., Ahmad, M.N.M., and Salameh, Y. (2016) Chemical and physical characteristics of optimal synthesised activated carbons from grass-derived sulfonated lignin versus commercial activated carbons. *Microporous and Mesoporous Materials*, **225**, 504–514. Elsevier Ltd.



- Al-Qodah, Z. and Shawabkiah, R. (2009) Production and characterization of granular activated carbon from activated sludge. *Brazilian Journal of Chemical Engineering*, **26**, 127–136.
- Alabadi, A., Razzaque, S., Yang, Y., Chen, S., and Tan, B. (2015) Highly porous activated carbon materials from carbonized biomass with high CO<sub>2</sub> capturing capacity. *Chemical Engineering Journal*, **281**, 606–612. Elsevier B.V.
- Alba-Rubio, A.C., Santamaria-Gonzalez, J., Merida-Robles, J.M., Moreno-Tost, R., Martin-Alonso, D., Jimenez-Lopez, A., and Maireles-Torres, P. (2010) Heterogeneous transesterification processes by using CaO supported on zinc oxide as basic catalysts. *Catalysis Today*, **149**, 281–287.
- Alba-Rubio, A.C., Alonso Castillo, M.L., Albuquerque, M.C.G., Mariscal, R., Cavalcante, C.L., and Granados, M.L. (2012) A new and efficient procedure for removing calcium soaps in biodiesel obtained using CaO as a heterogeneous catalyst. *Fuel*, **95**, 464–470. Elsevier Ltd.
- Albuquerque, M.C.G., Jimenez-Urbistondo, I., Santamaria-Gonzalez, J., Merida-Robles, J.M., Moreno-Tost, R., Rodriguez-Castellon, E., Jimenez-Lopez, A., Azevedo, D.C.S., Cavalcante, C.L., and Maireles-Torres, P. (2008) CaO supported on mesoporous silicas as basic catalysts for transesterification reactions. *Applied Catalysis A: General*, **334**, 35–43.
- Alcañiz-Monge, J., Trautwein, G., and Marco-Lozar, J.P. (2013) Biodiesel production by acid catalysis with heteropolyacids supported on activated carbon fibers. *Applied Catalysis A: General*, **468**, 432–441.
- Alhamed, Y. (2006) Activated Carbon from Dates' Stone by ZnCl<sub>2</sub> Activation. *Engineering Science*, **17**, 75–100.
- Alhassan, Y., Kumar, N., Bugaje, I., and Pali, H.S. (2014) Co-solvents transesterification of cotton seed oil into biodiesel : effects of reaction conditions on quality of fatty acids methyl esters . *Energy Convers Manag. Energy Conversion and Management*, **84**, 640–648.
- Alonso, D.M., Mariscal, R., Granados, M.L., and Maireles-Torres, P. (2009) Biodiesel preparation using Li/CaO catalysts: Activation process and homogeneous contribution. *Catalysis Today*, **143**, 167–171.
- Altintig, E. and Kirkil, S. (2016) Preparation and properties of Ag-coated activated carbon nanocomposites produced from wild chestnut shell by ZnCl<sub>2</sub> activation. *Journal of the Taiwan Institute of Chemical Engineers*, **0**, 1–9. Elsevier B.V.
- Altun, Ş., Yaşar, F., and Öner, C. (2010) The fuel properties of methyl esters produced from canola oil- animal tallow blends by base- catalyzed transesterification. *International Journal of Engineering Research and Development*, **2**, 2–5.
- Amani, H., Asif, M., and Hameed, B.H. (2015) Transesterification of waste cooking palm oil and palm oil to fatty acid methyl ester using cesium-modified silica catalyst. *Journal of the Taiwan Institute of Chemical Engineers*, **000**, 1–9. Elsevier Ltd.
- Angin, D., Altintig, E., and Köse, T.E. (2013) Influence of process parameters on the surface and chemical properties of activated carbon obtained from biochar by

- chemical activation. *Bioresource Technology*, **148**, 542–549. Elsevier Ltd.
- Anuar, M.R. and Abdullah, A.Z. (2016) Challenges in biodiesel industry with regards to feedstock, environmental, social and sustainability issues: A critical review. *Renewable and Sustainable Energy Reviews*, **58**, 208–223. Elsevier.
- Anwar, A. and Garforth, A. (2016) Challenges and opportunities of enhancing cold flow properties of biodiesel via heterogeneous catalysis. *Fuel*, **173**, 189–208. Elsevier Ltd.
- Aracil, J., El Boulifi, N., Bouaid, A., and Martinez, M. (2010) Process optimization for biodiesel production from corn oil and its oxidative stability. *International Journal of Chemical Engineering*, **2010**.
- Arampatzidou, A.C. and Deliyanni, E.A. (2016) Comparison of activation media and pyrolysis temperature for activated carbons development by pyrolysis of potato peels for effective adsorption of endocrine disruptor bisphenol-A. *Journal of Colloid and Interface Science*, **466**, 101–112. Elsevier Inc.
- Atadashi, I.M., Aroua, M.K., and Aziz, A.A. (2010) High quality biodiesel and its diesel engine application: A review. *Renewable and Sustainable Energy Reviews*, **14**, 1999–2008. Elsevier Ltd.
- Athappan, A., Sattler, M.L., and Sethupathi, S. (2015) Selective catalytic reduction of nitric oxide over cerium-doped activated carbons. *Journal of Environmental Chemical Engineering*, **3**, 2502–2513. Elsevier B.V.
- Auer, E., Freund, a., Pietsch, J., and Tacke, T. (1998) Carbons as supports for industrial precious metal catalysts. *Applied Catalysis A: General*, **173**, 259–271.
- Avhad, M.R. and Marchetti, J.M. (2015) A review on recent advancement in catalytic materials for biodiesel production. *Renewable and Sustainable Energy Reviews*, **50**, 696–718. Elsevier.
- Ayeter, G.K., Sunnu, A., and Parbey, J. (2014) Effect of biodiesel production parameters on viscosity and yield of methyl esters: *Jatropha curcas*, *Elaeis guineensis* and *Cocos nucifera*. *Alexandria Engineering Journal*, **54**, 1285–1290. Faculty of Engineering, Alexandria University.
- Azeem, M.W., Hanif, M.A., Al-Sabahi, J.N., Khan, A.A., Naz, S., and Ijaz, A. (2016) Production of biodiesel from low priced, renewable and abundant date seed oil. *Renewable Energy*, **86**, 124–132. Elsevier Ltd.
- Azlina, W., Ab, W., Ghani, K., Ali, S.B., Esfahani, R.M., Amran, M., and Salleh, M. (2012) Hydrogen-Rich Gas Production from Palm Kernel Shell by Applying Air Gasification in Fluidized Bed Reactor Hydrogen-Rich Gas Production from Palm Kernel Shell by Applying Air Gasification in Fluidized Bed Reactor. *Energy & Fuels*, **26**, 1185–1191.
- Badday, A.S., Abdullah, A.Z., and Lee, K.T. (2013) Optimization of biodiesel production process from *Jatropha* oil using supported heteropolyacid catalyst and assisted by ultrasonic energy. *Renewable Energy*, **50**, 427–432. Elsevier Ltd.
- Badday, A.S., Abdullah, A.Z., and Lee, K.T. (2014) Transesterification of crude *Jatropha* oil by activated carbon-supported heteropolyacid catalyst in an ultrasound-assisted reactor system. *Renewable Energy*, **62**, 10–17. Elsevier Ltd.

- Baek, J., Lee, H.M., Roh, J.S., Lee, H.S., Kang, H.S., and Kim, B.J. (2016) Studies on preparation and applications of polymeric precursor-based activated hard carbons: I. Activation mechanism and microstructure analyses. *Microporous and Mesoporous Materials*, **219**, 258–264. Elsevier Ltd.
- Bagheri, S., Julkapli, N.M., Bee, S., and Hamid, A. (2014) Titanium Dioxide as a Catalyst Support in Heterogeneous Catalysis. *The Scientific World Journal*, **2014**, 1–21.
- Bai, H.X., Shen, X.Z., Liu, X.H., and Liu, S.Y. (2009) Synthesis of porous CaO microsphere and its application in catalyzing transesterification reaction for biodiesel. *Transactions of Nonferrous Metals Society of China (English Edition)*, **19**, s674–s677. The Nonferrous Metals Society of China.
- Banerjee, A. and Chakraborty, R. (2009) Resources , Conservation and Recycling Parametric sensitivity in transesterification of waste cooking oil for biodiesel production — A review. *Resources, Conservation and Recycling*, **53**, 490–497.
- Banković–Ilić, I.B., Miladinović, M.R., Stamenković, O.S., and Veljković, V.B. (2017) Application of nano CaO–based catalysts in biodiesel synthesis. *Renewable and Sustainable Energy Reviews*, **72**, 746–760.
- Baroutian, S., Aroua, M.K., Aziz, A., Raman, A., Meriam, N., and Sulaiman, N. (2010) Potassium hydroxide catalyst supported on palm shell activated carbon for transesterification of palm oil. *Fuel Processing Technology*, **91**, 1378–1385. Elsevier B.V.
- Baroutian, S., Aroua, M.K., Raman, A.A.A., and Sulaiman, N.M.N. (2011) Bioresource Technology A packed bed membrane reactor for production of biodiesel using activated carbon supported catalyst. *Bioresource Technology*, **102**, 1095–1102. Elsevier Ltd.
- Baskar, G. and Aiswarya, R. (2016) Trends in catalytic production of biodiesel from various feedstocks. *Renewable and Sustainable Energy Reviews*, **57**, 496–504. Elsevier.
- Bello, A.M., Yacob, A.R., and Kabo, K.S. (2016) Box-Bahken Design Biodiesel Prediction Model from Corn Oil using Na-Modified Alumina Beads. *Indian Journal of Science and Technology*, **9**.
- Benjapornkulaphong, S., Ngamcharussrivichai, C., and Bunyakiat, K. (2009) Al<sub>2</sub>O<sub>3</sub>-supported alkali and alkali earth metal oxides for transesterification of palm kernel oil and coconut oil. *Chemical Engineering Journal*, **145**, 468–474.
- Bet-Moushoul, E., Farhadi, K., Mansourpanah, Y., Nikbakht, A.M., Molaei, R., and Forough, M. (2016) Application of CaO-based/Au nanoparticles as heterogeneous nanocatalysts in biodiesel production. *Fuel*, **164**, 119–127. Elsevier Ltd.
- Bohli, T., Ouederni, A., Fiol, N., and Villaescusa, I. (2015) Evaluation of an activated carbon from olive stones used as an adsorbent for heavy metal removal from aqueous phases. *Comptes Rendus Chimie*, **18**, 88–99. Academie des sciences.
- Bora, B.J. and Saha, U.K. (2015) Comparative assessment of a biogas run dual fuel diesel engine with rice bran oil methyl ester, pongamia oil methyl ester and palm

- oil methyl ester as pilot fuels. *Renewable Energy*, **81**, 490–498. Elsevier Ltd.
- Bora, B.J. and Saha, U.K. (2016) Experimental evaluation of a rice bran biodiesel - biogas run dual fuel diesel engine at varying compression ratios. *Renewable Energy*, **87**, 782–790. Elsevier Ltd.
- Borges, M.E. and Diaz, L. (2012) Recent developments on heterogeneous catalysts for biodiesel production by oil esterification and transesterification reactions: A review. *Renewable and Sustainable Energy Reviews*, **16**, 2839–2849. Elsevier Ltd.
- El Boulifi, N., Bouaid, A., Martinez, M., and Aracil, J. (2013) Optimization and oxidative stability of biodiesel production from rice bran oil. *Renewable Energy*, **53**, 141–147.
- Buasri, A., Chaiyut, N., and Nakweang, C. (2011) Preparing activated carbon from palm shell for biodiesel fuel production. *Chiang Mai Journal of Science*, **38**, 572–578.
- Buasri, A., Ksapabutr, B., Panapoy, M., and Chaiyut, N. (2012a) Biodiesel production from waste cooking palm oil using calcium oxide supported on activated carbon as catalyst in a fixed bed reactor. *Korean Journal of Chemical Engineering*, **29**, 1708–1712.
- Buasri, A., Chaiyut, N., Loryuenyong, V., Rodklum, C., Chaikwan, T., and Kumphan, N. (2012b) Continuous Process for Biodiesel Production in Packed Bed Reactor from Waste Frying Oil Using Potassium Hydroxide Supported on Jatropha curcas Fruit Shell as Solid Catalyst. **2**, 641–653.
- Buasri, A., Chaiyut, N., Loryuenyong, V., and Rodklum, C. (2012c) Transesterification of waste frying oil for synthesizing biodiesel by KOH supported on coconut shell activated carbon in packed bed reactor. *Science Asia*, **38**, 283–288.
- Buasri, A., Chaiyut, N., Loryuenyong, V., Phakdeepataraphan, E., Watpathomsub, S., and Kunakemakorn, V. (2013) Utilization of Biodiesel Wastes as a Bioresource for the Preparation of Activated Carbon. *International Journal of Applied Physics and Mathematics*, **3**, 173–177.
- Calero, J., Luna, D., Sancho, E.D., Luna, C., Bautista, F.M., Romero, A.A., Posadillo, A., and Verdugo, C. (2014) Development of a new biodiesel that integrates glycerol, by using CaO as heterogeneous catalyst, in the partial methanolysis of sunflower oil. *Fuel*, **122**, 94–102. Elsevier Ltd.
- Canakci, M. and Gerpen, J. Van. (2001) Biodiesel production from oils and fats with high free fatty acids. *American society of Agricultural Engineers*, **44**, 1429–1436.
- Canakci, M., Ozsezen, A.N., Arcaklioglu, E., and Erdil, A. (2009) Prediction of performance and exhaust emissions of a diesel engine fueled with biodiesel produced from waste frying palm oil. *Expert Systems with Applications*, **36**, 9268–9280. Elsevier Ltd.
- Cazetta, A.L., Vargas, A.M.M., Nogami, E.M., Kunita, M.H., Guilherme, M.R., Martins, A.C., Silva, T.L., Moraes, J.C.G., and Almeida, V.C. (2011) NaOH-activated carbon of high surface area produced from coconut shell: Kinetics and

- equilibrium studies from the methylene blue adsorption. *Chemical Engineering Journal*, **174**, 117–125.
- Cermakova, L., Kopecka, I., Pivokonsky, M., Pivokonska, L., and Janda, V. (2017) Removal of cyanobacterial amino acids in water treatment by activated carbon adsorption. *Separation and Purification Technology*, **173**, 330–338. Elsevier B.V.
- Chang, G., Huang, Y., Xie, J., Yang, H., Liu, H., Yin, X., and Wu, C. (2016) The lignin pyrolysis composition and pyrolysis products of palm kernel shell, wheat straw, and pine sawdust. *Energy Conversion and Management*, **124**, 587–597. Elsevier Ltd.
- Cho, Y.B., Seo, G., and Chang, D.R. (2009) Transesterification of tributyrin with methanol over calcium oxide catalysts prepared from various precursors. *Fuel Processing Technology*, **90**, 1252–1258.
- Chowdhury, Z.Z., Zain, S.M., Khan, R.A., and Islam, M.S. (2012) Preparation and characterizations of activated carbon from kenaf fiber for equilibrium adsorption studies of copper from wastewater. *Korean Journal of Chemical Engineering*, **29**, 1187–1195.
- Colombo, K. and Ender, L. (2017) The study of biodiesel production using CaO as a heterogeneous catalytic reaction. *Egyptian Journal of Petroleum*, **26**, 341–349.
- Correia, L.M., Saboya, R.M.A., de Sousa Campelo, N., Cecilia, J.A., Rodríguez-Castellón, E., Cavalcante, C.L., and Vieira, R.S. (2014) Characterization of calcium oxide catalysts from natural sources and their application in the transesterification of sunflower oil. *Bioresource Technology*, **151**, 207–213. Elsevier Ltd.
- Cravotto, G., Binello, A., Merizzi, G., and Avogadro, M. (2004) Improving solvent-free extraction of policosanol from rice bran by high-intensity ultrasound treatment. *European Journal of Lipid Science and Technology*, **106**, 147–151.
- Cunha, A., Feddern, V., De Prá, M.C., Higarashi, M.M., De Abreu, P.G., and Coldebella, A. (2013) Synthesis and characterization of ethylic biodiesel from animal fat wastes. *Fuel*, **105**, 228–234. Elsevier Ltd.
- Daud, W.M.A.W., Ali, W.S.W., and Sulaiman, M.Z. (2000) Effects of carbonization temperature on pore development in palm-shell-based activated carbon. *Carbon*, **38**, 1925–1932.
- Degirmenbasi, N., Coskun, S., Boz, N., and Kalyon, D.M. (2015) Biodiesel synthesis from canola oil via heterogeneous catalysis using functionalized CaO nanoparticles. *Fuel*, **153**, 620–627. Elsevier Ltd.
- Deng, H., Li, G., Yang, H., Tang, J., and Tang, J. (2010) Preparation of activated carbons from cotton stalk by microwave assisted KOH and K<sub>2</sub>CO<sub>3</sub> activation. *Chemical Engineering Journal*, **163**, 373–381. Elsevier B.V.
- Dhawane, S.H., Kumar, T., and Halder, G. (2016) Biodiesel synthesis from *Hevea brasiliensis* oil employing carbon supported heterogeneous catalyst: Optimization by Taguchi method. *Renewable Energy*, **89**, 506–514. Elsevier Ltd.
- Dias, J.M., Alvim-Ferraz, M.C.M., Almeida, M.F., Mendez D'az, J.D., Polo, M.S.,

- and Utrilla, J.R. (2012) Selection of heterogeneous catalysts for biodiesel production from animal fat. *Fuel*, **94**, 418–425. Elsevier Ltd.
- Dias, J.M., Alvim-Ferraz, M.C.M., Almeida, M.F., Mendez Diaz, J.D., Sanchez Polo, M., and Rivera Utrilla, J. (2013) Biodiesel production using calcium manganese oxide as catalyst and different raw materials. *Energy Conversion and Management*, **65**, 647–653. Elsevier Ltd.
- Ejikeme, P.M., Anyaogu, I.D., Ejikeme, C.L., Nwafor, N.P., Egbuonu, C.A.C., Ukogu, K., Ibemesi, J.A., Chemistry, I., and Polytechnic, F. (2010) Catalysis in Biodiesel Production by Transesterification Process-An Insight. *E-Journal of Chemistry*, **7**, 1120–1132.
- El-Sayed, G.O., Yehia, M.M., and Asaad, A.A. (2014) Assessment of activated carbon prepared from corncob by chemical activation with phosphoric acid. *Water Resources and Industry*, **7–8**, 66–75. Elsevier.
- Elmouwahidi, A., Zapata-Benabithé, Z., Carrasco-Marín, F., and Moreno-Castilla, C. (2012) Activated carbons from KOH-activation of argan (*Argania spinosa*) seed shells as supercapacitor electrodes. *Bioresource Technology*, **111**, 185–190. Elsevier Ltd.
- Endalew, A.K., Kiros, Y., and Zanzi, R. (2011) Inorganic heterogeneous catalysts for biodiesel production from vegetable oils. *Biomass and Bioenergy*, **35**, 3787–3809. Elsevier Ltd.
- Evangelista, J.P.C., Chellappa, T., Coriolano, A.C.F., Fernandes, V.J., Souza, L.D., and Araujo, A.S. (2012) Synthesis of alumina impregnated with potassium iodide catalyst for biodiesel production from rice bran oil. *Fuel Processing Technology*, **104**, 90–95. Elsevier B.V.
- Fadhil, A.B., Dheyab, M.M., and Abdul-Qader, A.Q.Y. (2012) Purification of biodiesel using activated carbons produced from spent tea waste. *Journal of the Association of Arab Universities for Basic and Applied Sciences*, **11**, 45–49. University of Bahrain.
- Fadhil, A.B., Al-Tikrity, E.T.B., and Albadree, M.A. (2015) Transesterification of a novel feedstock, *Cyprinus carpio* fish oil: Influence of co-solvent and characterization of biodiesel. *Fuel*, **162**, 215–223. Elsevier Ltd.
- Fadhil, A.B., Aziz, A.M., and Altamer, M.H. (2016) Potassium acetate supported on activated carbon for transesterification of new non-edible oil, bitter almond oil. *Fuel*, **170**, 130–140. Elsevier Ltd.
- Farag, H.A., El-Maghraby, A., and Taha, N.A. (2011) Optimization of factors affecting esterification of mixed oil with high percentage of free fatty acid. *Fuel Processing Technology*, **92**, 507–510. Elsevier B.V.
- Ferrera-Lorenzo, N., Fuente, E., Suarez-Ruiz, I., and Ruiz, B. (2014) KOH activated carbon from conventional and microwave heating system of a macroalgae waste from the Agar-Agar industry. *Fuel Processing Technology*, **121**, 25–31. Elsevier B.V.
- Figueiredo, J., Pereira, M.F., Freitas, M.M., and Órfão, J.J. (1999) Modification of the surface chemistry of activated carbons. *Carbon*, **37**, 1379–1389.

- Foo, K.Y. and Hameed, B.H. (2012) Microwave-assisted preparation and adsorption performance of activated carbon from biodiesel industry solid residue: Influence of operational parameters. *Bioresource Technology*, **103**, 398–404. Elsevier Ltd.
- Foo, K.Y. and Hameed, B.H. (2013) Utilization of oil palm biodiesel solid residue as renewable sources for preparation of granular activated carbon by microwave induced KOH activation. *Bioresource Technology*, **130**, 696–702.
- Ganpat, V. and Gbadebo, Y. (2013) Synthesis and kinetics of biodiesel formation via calcium methoxide base catalyzed transesterification reaction in the absence and presence of ultrasound. *Fuel*, **107**, 474–482.
- Gao, Y., Yue, Q., Xu, S., Gao, B., Li, Q., and Yu, H. (2015) Preparation and evaluation of adsorptive properties of micro-mesoporous activated carbon via sodium aluminate activation. *Chemical Engineering Journal*, **274**, 76–83. Elsevier B.V.
- Gao, Y., Xu, S., Yue, Q., Wu, Y., and Gao, B. (2016) Chemical preparation of crab shell-based activated carbon with superior adsorption performance for dye removal from wastewater. *Journal of the Taiwan Institute of Chemical Engineers*, **000**, 1–9. Elsevier B.V.
- Ghani, W.A.W.A.K., Mohd, A., da Silva, G., Bachmann, R.T., Taufiq-Yap, Y.H., Rashid, U., and Al-Muhtaseb, A.H. (2013) Biochar production from waste rubber-wood-sawdust and its potential use in C sequestration: Chemical and physical characterization. *Industrial Crops and Products*, **44**, 18–24. Elsevier B.V.
- Gomez-Serrano, V., Pastor-Villegas, J., Perez-Florindo, A., Duran-Valle, C., and Valenzuela-Calahorra, C. (1996) FT-IR study of rockrose and of char and activated carbon. *Journal of Analytical and Applied Pyrolysis*, **36**, 71–80.
- Guo, J. and Lua, A.C. (2003a) Surface functional groups on oil-palm-shell adsorbents prepared by H<sub>3</sub>PO<sub>4</sub> and KOH activation and their effects on adsorptive capacity. *Chemical Engineering Research & Design*, **81**, 585–590.
- Guo, J. and Lua, A.C. (2003b) Textural and chemical properties of adsorbent prepared from palm shell by phosphoric acid activation. *Materials Chemistry and Physics*, **80**, 114–119.
- Hadi, P., Yeung, K.Y., Guo, J., Wang, H., and McKay, G. (2016) Sustainable development of tyre char-based activated carbons with different textural properties for value-added applications. *Journal of Environmental Management*, **170**, 1–7. Elsevier Ltd.
- Hanapi, S.Z., Masrom, N.I., and Yacob, A.R. (2010) Tungsten Carbide Synthesis by Microwave-Induced Alloying Using Phosphoric Acid Activated Palm Kernel Shell Carbon. *Journal of Materials Science and Engineering*, **4**, 68–73.
- Hayashi, J., Horikawa, T., Takeda, I., Muroyama, K., and Nasir Ani, F. (2002) Preparing activated carbon from various nutshells by chemical activation with K<sub>2</sub>CO<sub>3</sub>. *Carbon*, **40**, 2381–2386.
- Herawan, S.G., Hadi, M.S., Ayob, R., and Putra, A. (2013) Characterization of Activated Carbons from Oil-Palm Shell by CO<sub>2</sub> Activation with No Holding Carbonization Temperature. **2013**.

- Hernandez-Hipolito, P., Juarez-Flores, N., Martinez-Klimova, E., Gomez-Cortes, A., Bokhimi, X., Escobar-Alarcon, L., and Klimova, T.E. (2015) Novel heterogeneous basic catalysts for biodiesel production: Sodium titanate nanotubes doped with potassium. *Catalysis Today*, **250**, 187–196. Elsevier B.V.
- Hidayu, A.R. and Muda, N. (2016) Preparation and Characterization of Impregnated Activated Carbon from Palm Kernel Shell and Coconut Shell for CO<sub>2</sub> Capture. *Procedia Engineering*, **148**, 106–113. Elsevier B.V.
- Ho, W.W.S., Ng, H.K., Gan, S., and Tan, S.H. (2014) Evaluation of palm oil mill fly ash supported calcium oxide as a heterogeneous base catalyst in biodiesel synthesis from crude palm oil. *Energy Conversion and Management*, **88**, 1167–1178. Elsevier Ltd.
- Hoekman, S.K., Broch, A., Robbins, C., Ceniceros, E., and Natarajan, M. (2012) Review of biodiesel composition, properties, and specifications. *Renewable and Sustainable Energy Reviews*, **16**, 143–169.
- Hu, K., Wang, H., Liu, Y., and Yang, C. (2014) KNO<sub>3</sub>/CaO as cost-effective heterogeneous catalyst for the synthesis of glycerol carbonate from glycerol and dimethyl carbonate. *Journal of Industrial and Engineering Chemistry*, **28**, 334–343. The Korean Society of Industrial and Engineering Chemistry.
- Hu, Z., Srinivasan, M.P., and Ni, Y. (2001) Novel activation process for preparing highly microporous and mesoporous activated carbons Novel activation process for preparing highly microporous and mesoporous activated carbons. **39**, 877–886.
- Huang, D.C., Liu, Q.L., Zhang, W., Ding, J., Gu, J.J., Zhu, S.M., Guo, Q.X., and Zhang, D. (2011) Preparation of high-surface-area activated carbon from *Zizania latifolia* leaves by one-step activation with K<sub>2</sub>CO<sub>3</sub>/rarefied air. *Journal of Materials Science*, **46**, 5064–5070.
- Huang, Y., Ma, E., and Zhao, G. (2015) Thermal and structure analysis on reaction mechanisms during the preparation of activated carbon fibers by KOH activation from liquefied wood-based fibers. *Industrial Crops and Products*, **69**, 447–455. Elsevier B.V.
- Hui T.S. & Zaini M.A.A. (2015) Potassium hydroxide activation of activated carbon : a commentary. *Carbon Letters*, **16**, 275–280.
- Hwa, S., Rashid, U., and Taufiq-yap, Y.H. (2014) Biodiesel production from crude *Jatropha Curcas* oil using calcium based mixed oxide catalysts. *FUEL*, **136**, 244–252. Elsevier Ltd.
- Hwa, S., Rashid, U., Choong, S.Y.T., and Taufiq-yap, Y.H. (2017) Heterogeneous calcium-based bimetallic oxide catalyzed transesterification of *Elaeis guineensis* derived triglycerides for biodiesel production. *Energy Conversion and Management*, **141**, 20–27. Elsevier Ltd.
- Intarapong, P., Iangthanarat, S., Phanthong, P., Luengnaruemitchai, A., and Jai-In, S. (2013) Activity and basic properties of KOH/mordenite for transesterification of palm oil. *Journal of Energy Chemistry*, **22**, 690–700. Dalian Institute of Chemical Physics, the Chinese Academy of Sciences. Published by Elsevier B.V.



- Intarapong, P., Iangthanarat, S., and Luengnaruemitchai, A. (2014) Biodiesel Production from Palm Oil Using Potassium Hydroxide Loaded on ZrO<sub>2</sub> Catalyst in a Batch Reactor. *Chiang Mai J. Sci*, **41**, 128–137.
- Irmawati, R., Shafizah, I., Sharina, A.N., and Ahangar, H.A. (2014) Transesterification of Palm Oil by Using Silica Loaded Potassium Carbonate ( K<sub>2</sub>CO<sub>3</sub> / SiO<sub>2</sub> ) Catalysts to Produce Fatty Acid Methyl Esters ( FAME ). *Energy and Power*, **4**, 7–15.
- Islam, A., Taufiq-Yap, Y.H., Chu, C.-M., Chan, E.-S., and Ravindra, P. (2013) Studies on design of heterogeneous catalysts for biodiesel production. *Process Safety and Environmental Protection*, **91**, 131–144. Institution of Chemical Engineers.
- Issariyakul, T. and Dalai, A.K. (2014) Biodiesel from vegetable oils. *Renewable and Sustainable Energy Reviews*, **31**, 446–471. Elsevier.
- Jain, A., Balasubramanian, R., and Srinivasan, M.P. (2015) Production of high surface area mesoporous activated carbons from waste biomass using hydrogen peroxide-mediated hydrothermal treatment for adsorption applications. *Chemical Engineering Journal*, **273**, 622–629. Elsevier B.V.
- Jain, S. and Sharma, M.P. (2010) Kinetics of acid base catalyzed transesterification of Jatropha curcas oil. *Bioresource Technology*, **101**, 7701–7706. Elsevier Ltd.
- Jitputti, J., Kitiyanan, B., Rangsunvigit, P., Bunyakiat, K., Attanatho, L., and Jenvanitpanjakul, P. (2006) Transesterification of crude palm kernel oil and crude coconut oil by different solid catalysts. *Chemical Engineering Journal*, **116**, 61–66.
- Ju, Y. and Vali, S.R. (2005) Rice bran oil as a potential resource for biodiesel : A review. *journal of scientific*, **64**, 866–882.
- Kaewdaeng, S., Sintuya, P., and Nirunsin, R. (2017) Biodiesel production oxide from river snail shell ash as catalyst. *Energy Procedia*, **138**, 937–942. Elsevier B.V.
- Kattimani, V.R., Venkatesha, B.M., and Ananda, S. (2014) Biodiesel Production from Unrefined Rice Bran Oil through Three-Stage Transesterification. *Advance in Chemicals Engineering and Science*, **4**, 361–366.
- Kaur, M. and Ali, A. (2011) Lithium ion impregnated calcium oxide as nano catalyst for the biodiesel production from karanja and jatropha oils. *Renewable Energy*, **36**, 2866–2871. Elsevier Ltd.
- Kaur, N. and Ali, A. (2014) Kinetics and reusability of Zr/CaO as heterogeneous catalyst for the ethanolysis and methanolysis of Jatropha curcas oil. *Fuel Processing Technology*, **119**, 173–184. Elsevier B.V.
- Kaushik, A., Basu, S., Singh, K., Batra, V.S., and Balakrishnan, M. (2017) Activated carbon from sugarcane bagasse ash for melanoidins recovery. *Journal of Environmental Management*, **200**, 29–34. Elsevier Ltd.
- Kawashima, A., Matsubara, K., and Honda, K. (2009) Acceleration of catalytic activity of calcium oxide for biodiesel production. *Bioresource Technology*, **100**, 696–700. Elsevier Ltd.
- Kazemian, H., Turowec, B., Siddiquee, M.N., and Rohani, S. (2013) Biodiesel

production using cesium modified mesoporous ordered silica as heterogeneous base catalyst. *Fuel*, **103**, 719–724. Elsevier Ltd.

- Kazempour, M., Ansari, M., Tajrobehkar, S., Majdzadeh, M., and Kermani, H.R. (2008) Removal of lead, cadmium, zinc, and copper from industrial wastewater by carbon developed from walnut, hazelnut, almond, pistachio shell, and apricot stone. *Journal of Hazardous Materials*, **150**, 322–327.
- Khezami, L., Ould-Dris, A., and Capart, R. (2007) Activated carbon from thermo-compressed wood and other lignocellulosic precursors. *Bioresources*, **2**, 193–209.
- Kim, H., Kang, B., Kim, M., Moo, Y., Kim, D., Lee, J., and Lee, K. (2004) Transesterification of vegetable oil to biodiesel using heterogeneous base catalyst. **95**, 315–320.
- Kouzu, M. and Hidaka, J.S. (2013) Purification to remove leached CaO catalyst from biodiesel with the help of cation-exchange resin. *Fuel*, **105**, 318–324. Elsevier Ltd.
- Kouzu, M., Kasuno, T., Tajika, M., and Sugimoto, Y. (2008) Calcium oxide as a solid base catalyst for transesterification of soybean oil and its application to biodiesel production. *Fuel*, **87**, 2798–2806.
- Król, M., Gryglewicz, G., and MacHnikowski, J. (2011) KOH activation of pitch-derived carbonaceous materials-Effect of carbonization degree. *Fuel Processing Technology*, **92**, 158–165.
- Kundu, A., Sen Gupta, B., Hashim, M.A., and Redzwan, G. (2015) Taguchi optimization approach for production of activated carbon from phosphoric acid impregnated palm kernel shell by microwave heating. *Journal of Cleaner Production*, **105**, 420–427. Elsevier Ltd.
- Kusuma, R.I., Hadinoto, J.P., Ayucitra, A., Soetaredjo, F.E., and Ismadji, S. (2013) Applied Clay Science Natural zeolite from Pacitan Indonesia, as catalyst support for transesterification of palm oil. *Applied Clay Science*, **74**, 121–126. Elsevier B.V.
- Kwiatkowski, M. and Broniek, E. (2017) An analysis of the porous structure of activated carbons obtained from hazelnut shells by various physical and chemical methods of activation. *Colloids and Surfaces*, **529**, 443–453.
- Kwong, T.-L. and Yung, K.-F. (2016) One-step production of biodiesel through simultaneous esterification and transesterification from highly acidic unrefined feedstock over efficient and recyclable ZnO nanostar catalyst. *Renewable Energy*, **90**, 450–457.
- Kyzas, G.Z., Deliyanni, E.A., and Matis, K.A. (2016) Activated carbons produced by pyrolysis of waste potato peels: Cobalt ions removal by adsorption. *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, **490**, 74–83. Elsevier B.V.
- Labeckas, G. and Slavinskas, S. (2006) The effect of rapeseed oil methyl ester on direct injection Diesel engine performance and exhaust emissions. *Energy Conversion and Management*, **47**, 1954–1967.

- Labus, K., Gryglewicz, S., and Machnikowski, J. (2014) Granular KOH-activated carbons from coal-based cokes and their CO<sub>2</sub> adsorption capacity. *Fuel*, **118**, 9–15. Elsevier Ltd.
- Laginhas, C., Nabais, J.M.V., and Titirici, M.M. (2016) Activated carbons with high nitrogen content by a combination of hydrothermal carbonization with activation. *Microporous and Mesoporous Materials*, **226**, 125–132. Elsevier Ltd.
- Largitte, L., Brudey, T., Tant, T., Dumesnil, P.C., and Lodewyckx, P. (2015) Comparison of the adsorption of lead by activated carbons from three lignocellulosic precursors. *Microporous and Mesoporous Materials*, **219**, 265–275. Elsevier Ltd.
- Li, L., Du, W., Liu, D., Wang, L., and Li, Z. (2006) Lipase-catalyzed transesterification of rapeseed oils for biodiesel production with a novel organic solvent as the reaction medium. *Journal of Molecular Catalysis B: Enzymatic*, **43**, 58–62.
- Li, Y., Ye, B., Shen, J., Tian, Z., Wang, L., Zhu, L., Ma, T., Yang, D., and Qiu, F. (2013) Optimization of biodiesel production process from soybean oil using the sodium potassium tartrate doped zirconia catalyst under Microwave Chemical Reactor. *Bioresource Technology*, **137**, 220–225. Elsevier Ltd.
- Li, Y.X., Yang, J.W., Hui, F.L., Fan, W.W., and Yang, Y. (2011) Optimization of biodiesel production from rice bran oil via immobilized lipase catalysis. *African Journal of Biotechnology*, **10**, 16314–16324.
- Liao, C.C. and Chung, T.W. (2013) Optimization of process conditions using response surface methodology for the microwave-assisted transesterification of Jatropha oil with KOH impregnated CaO as catalyst. *Chemical Engineering Research and Design*, **91**, 2457–2464. Institution of Chemical Engineers.
- Liew, L.L., Loh, S.K., Kassim, M.A., and Muda, K. (2015) Efficiency of Nutrients Removal From Palm Oil Mill Effluent Treatment Systems Efficiency of Nutrients Removal From Palm Oil Mill Effluent Treatment Systems. *Journal of Palm Oil Research*, **27**, 433–443.
- Lillo-Rodenas, M.A., Cazorla-Amoros, D., and Linares-Solano, A. (2003) Understanding chemical reactions between carbons and NaOH and KOH: An insight into the chemical activation mechanism. *Carbon*, **41**, 267–275.
- Lillo-Ródenas, M.A., Juan-Juan, J., Cazorla-Amorós, D., and Linares-Solano, A. (2004) About reactions occurring during chemical activation with hydroxides. *Carbon*, **42**, 1365–1369.
- Lin, Y.C., Hsu, K.H., and Lin, J.F. (2014) Rapid palm-biodiesel production assisted by a microwave system and sodium methoxide catalyst. *Fuel*, **115**, 306–311. Elsevier Ltd.
- Lounasvuori, M.M., Kelly, D., and Foord, J.S. (2018) Carbon black as low-cost alternative for electrochemical sensing of phenolic compounds. *Carbon*, **129**, 252–257. Elsevier Ltd.
- Lozano-Castello, D., Lillo-Rodenas, M.A., Cazorla-Amoros, D., and Linares-Solano, A. (2001) Preparation of activated carbons from Spanish anthracite - I. Activation

- by KOH. *Carbon*, **39**, 741–749.
- Lua, A.C. and Yang, T. (2004) Effect of activation temperature on the textural and chemical properties of potassium hydroxide activated carbon prepared from pistachio-nut shell. *Journal of Colloid and Interface Science*, **274**, 594–601.
- Lua, A.C. and Yang, T. (2005) Characteristics of activated carbon prepared from pistachio-nut shell by zinc chloride activation under nitrogen and vacuum conditions. *Journal of Colloid and Interface Science*, **290**, 505–513.
- Luangkiattikhun, P., Tangsathitkulchai, C., and Tangsathitkulchai, M. (2008) Non-isothermal thermogravimetric analysis of oil-palm solid wastes. **99**, 986–997.
- Ma, F. and Hanna, M. a. (1999) Biodiesel production: a review. *Journal Series #12109*, Agricultural Research Division, Institute of Agriculture and Natural Resources, University of Nebraska–Lincoln. *Bioresource Technology*, **70**, 1–15.
- Ma, Z., Chen, D., Gu, J., Bao, B., and Zhang, Q. (2015) Determination of pyrolysis characteristics and kinetics of palm kernel shell using TGA-FTIR and model-free integral methods. *Energy Conversion and Management*, **89**, 251–259. Elsevier Ltd.
- Maciá-Agulló, J.A., Moore, B.C., Cazorla-Amorós, D., and Linares-Solano, A. (2004) Activation of coal tar pitch carbon fibres: Physical activation vs. chemical activation. *Carbon*, **42**, 1361–1364.
- Mahmudul, H.M., Hagos, F.Y., Mamat, R., Adam, A.A., Ishak, W.F.W., and Alenezi, R. (2017) Production, characterization and performance of biodiesel as an alternative fuel in diesel engines – A review. *Renewable and Sustainable Energy Reviews*, **72**, 497–509. Elsevier Ltd.
- Malins, K., Kampars, V., Brinks, J., Neibolte, I., and Murnieks, R. (2015) Synthesis of activated carbon based heterogenous acid catalyst for biodiesel preparation. *Applied Catalysis B: Environmental*, **176–177**, 553–558. Elsevier B.V.
- Maneerung, T., Liew, J., Dai, Y., Kawi, S., Chong, C., and Wang, C.H. (2016a) Activated carbon derived from carbon residue from biomass gasification and its application for dye adsorption: Kinetics, isotherms and thermodynamic studies. *Bioresource Technology*, **200**, 350–359. Elsevier Ltd.
- Maneerung, T., Kawi, S., Dai, Y., and Wang, C.H. (2016b) Sustainable biodiesel production via transesterification of waste cooking oil by using CaO catalysts prepared from chicken manure. *Energy Conversion and Management*, **123**, 487–497. Elsevier Ltd.
- Marchetti, J.M. and Errazu, A.F. (2008) Esterification of free fatty acids using sulfuric acid as catalyst in the presence of triglycerides. *Biomass and Bioenergy*, **32**, 892–895.
- Marinkovic, D.M., Stanković, M. V., Veličković, A. V., Avramović, J.M., Cakic, M.D., and Veljković, V.B. (2015) The Synthesis of CaO Loaded onto Al<sub>2</sub>O<sub>3</sub> from Calcium Acetate and Its Application in Transesterification of the Sunflower Oil. *Advanced Technologies*, **4**, 26–32.
- Marinković, D.M., Stanković, M. V., Veličković, A. V., Avramović, J.M., Miladinović, M.R., Stamenković, O.O., Veljković, V.B., and Jovanović, D.M.

- (2016) Calcium oxide as a promising heterogeneous catalyst for biodiesel production: Current state and perspectives. *Renewable and Sustainable Energy Reviews*, **56**, 1387–1408.
- Martín-González, M.A., González-Díaz, O., Susial, P., Araña, J., Herrera-Melián, J.A., Doña-Rodríguez, J.M., and Pérez-Peña, J. (2014) Reuse of Phoenix canariensis palm frond mulch as biosorbent and as precursor of activated carbons for the adsorption of Imazalil in aqueous phase. *Chemical Engineering Journal*, **245**, 348–358.
- Martins, M.I., Pires, R.F., Alves, M.J., Hori, C.E., Reis, M.H.M., and Cardoso, V.L. (2013) Transesterification of soybean oil for biodiesel production using hydrotalcite as basic catalyst. *Chemical Engineering Transactions*, **32**, 817–822.
- Meloni, D., Perra, D., Monaci, R., Cutrufello, M.G., Rombi, E., and Ferino, I. (2016) Transesterification of Jatropha curcas oil and soybean oil on Al-SBA-15 catalysts. *Applied Catalysis B: Environmental*, **184**, 163–173. Elsevier B.V.
- Meng, Y.L., Wang, B.Y., Li, S.F., Tian, S.J., and Zhang, M.H. (2013) Effect of calcination temperature on the activity of solid Ca/Al composite oxide-based alkaline catalyst for biodiesel production. *Bioresource Technology*, **128**, 305–309. Elsevier Ltd.
- Mison, I.I., Zain, N.K.M., Aziz, R.A., Vidyadharan, B., and Jose, R. (2015) Electrochemical properties of carbon from oil palm kernel shell for high performance supercapacitors. *Electrochimica Acta*, **174**, 78–86. Elsevier Ltd.
- Mofijur, M., Masjuki, H.H., Kalam, M.A., Hazrat, M.A., Liaquat, A.M., Shahabuddin, M., and Varman, M. (2012) Prospects of biodiesel from Jatropha in Malaysia. *Renewable and Sustainable Energy Reviews*, **16**, 5007–5020. Elsevier.
- Mohamad, M., Ngadi, N., Wong, S.L., Jusoh, M., and Yahya, N.Y. (2017) Prediction of biodiesel yield during transesterification process using response surface methodology. *Fuel*, **190**, 104–112. Elsevier Ltd.
- Mohammed, M.A.A., Salmiaton, A., Azlina, W.A.K.G.W., and Amran, M.S.M. (2012) Bioresource Technology Gasification of oil palm empty fruit bunches : A characterization and kinetic study. *Bioresource Technology*, **110**, 628–636. Elsevier Ltd.
- Mohanty, S.K. (2013) A Production of biodiesel from rice bran oil and experimenting on small capacity diesel engine. *International Journal of Modern Engineering Research*, **3**, 920–923.
- Mohd, W., Wan, A., Shabuddin, W., and Ali, W. (2004) Comparison on pore development of activated carbon produced from palm shell and coconut shell. *Bioresource Technology*, **93**, 63–69.
- Molaei Dehkordi, A. and Ghasemi, M. (2012) Transesterification of waste cooking oil to biodiesel using Ca and Zr mixed oxides as heterogeneous base catalysts. *Fuel Processing Technology*, **97**, 45–51. Elsevier B.V.
- Monsalvo, V.M., Mohedano, A.F., and Rodriguez, J.J. (2011) Activated carbons from sewage sludge. Application to aqueous-phase adsorption of 4-chlorophenol. *Desalination*, **277**, 377–382. Elsevier B.V.

- Moser, B.R. (2009) Biodiesel production, properties, and feedstocks. *Vitr. Cell. Dev. Biol. - Plant*, **45**, 229–266.
- Muniandy, L., Adam, F., Mohamed, A.R., and Ng, E.P. (2014) The synthesis and characterization of high purity mixed microporous/mesoporous activated carbon from rice husk using chemical activation with NaOH and KOH. *Microporous and Mesoporous Materials*, **197**, 316–323. Elsevier Inc.
- Mutreja, V., Singh, S., and Ali, A. (2011) Biodiesel from mutton fat using KOH impregnated MgO as heterogeneous catalysts. *Renewable Energy*, **36**, 2253–2258. Elsevier Ltd.
- Nabais, J.M.V., Laginhas, C.E.C., Carrott, P.J.M., and Ribeiro Carrott, M.M.L. (2011) Production of activated carbons from almond shell. *Fuel Processing Technology*, **92**, 234–240. Elsevier B.V.
- Niksiar, A. and Nasernejad, B. (2017) Biomass and Bioenergy Activated carbon preparation from pistachio shell pyrolysis and gasification in a spouted bed reactor. *Biomass and Bioenergy*, **106**, 43–50. Elsevier Ltd.
- Ninduangdee, P., Kuprianov, V.I., Cha, E.Y., Kaewrath, R., Youngyuen, P., and Athhawethworawuth, W. (2015) *Thermogravimetric Studies of Oil Palm Empty Fruit Bunch and Palm Kernel Shell: TG/DTG Analysis and Modeling*. P. in: *Energy Procedia*. Elsevier B.V., 453-458 pp.
- Nowicki, P. and Pietrzak, R. (2017) Thermal and physicochemical properties of phosphorus-containing activated carbons obtained from biomass. *Journal of the Taiwan Institute of Chemical Engineers*, **80**, 1006–1013.
- Nowicki, P., Kazmierczak, J., and Pietrzak, R. (2014) Comparison of physicochemical and sorption properties of activated carbons prepared by physical and chemical activation of cherry stones. *Powder Technology*, **269**, 312–319. Elsevier B.V.
- Okoroigwe, E. C., Ofomatah, A. C., Oparaku, N. F. and Unachukwu, G.O. (2013) Production and evaluation of activated carbon from palm kernel shells (PKS) for economic and environmental sustainability. *International Journal of Physical Sciences*, **8**, 1036–1041.
- van Oss, C.J. (1990) A review of: “Active Carbon.” *Journal of Dispersion Science and Technology*, **11**, 323. Taylor & Francis.
- Al Othman, Z., Habila, M., and Ali, R. (2011) Preparation of Activated Carbon Using the Coprolysis of Agricultural and Municipal Solid Wastes at a Low Carbonization Temperature. *Carbon*, **24**, 67–72.
- Otowa, T., Nojima, Y., and Miyazaki, T. (1997) Development of KOH activated high surface area carbon and its application to drinking water purification. *Carbon*, **35**, 1315–1319.
- Oviasogie, P.O., Odewale, J.O., Aisueni, N.O., Eguagie, E.I., and Brown, G. (2013) Production, utilization and acceptability of organic fertilizers using palms and shea tree as sources of biomass. *African Journal of Agriculture Research*, **8**, 3483–3494.
- Ozdemir, I., Şahin, M., Orhan, R., and Erdem, M. (2014) Preparation and characterization of activated carbon from grape stalk by zinc chloride activation.

*Fuel Processing Technology*, **125**, 200–206.

- Pagketanang, T., Artnaseaw, A., Wongwicha, P., and Thabuot, M. (2015) *Microporous Activated Carbon from KOH-Activation of Rubber Seed-Shells for Application in Capacitor Electrode*. P. in: *Energy Procedia*. Elsevier B.V., 651–656 pp.
- Pasupulety, N., Gunda, K., Liu, Y., Rempel, G.L., and Ng, F.T.T. (2013) Production of biodiesel from soybean oil on CaO/Al<sub>2</sub>O<sub>3</sub> solid base catalysts. *Applied Catalysis A: General*, **452**, 189–202. Elsevier B.V.
- Patil, P.D., Gude, V.G., and Deng, S. (2009) Biodiesel Production from Jatropha Curcas, Waste Cooking, and Camelina Sativa Oils. *Industrial & Engineering Chemistry Research*, **48**, 10850–10856. American Chemical Society.
- Pramanik, K. (2003) Properties and Use of Jatropha Curcas oil and Oiesel Fuel Blends in Compression Ignition Engine. *Renewable Energy*, **28**, 239–248.
- Ramadhas, A.S., Jayaraj, S., and Muraleedharan, C. (2004) Use of vegetable oils as I.C. engine fuels - A review. *Renewable Energy*, **29**, 727–742.
- Ramesh, T., Rajalakshmi, N., and Dhathathreyan, K.S. (2015) Activated carbons derived from tamarind seeds for hydrogen storage. *Journal of Energy Storage*, **4**, 89–95. Elsevier Ltd.
- Reddy, K.S.K., Al Shoaibi, A., and Srinivasakannan, C. (2012) Activated carbon from date palm seed: Process optimization using response surface methodology. *Waste and Biomass Valorization*, **3**, 149–156.
- Reyero, I., Arzamendi, G., and Gandía, L.M. (2014) Heterogenization of the biodiesel synthesis catalysis: CaO and novel calcium compounds as transesterification catalysts. *Chemical Engineering Research and Design*, **92**, 1519–1530. Institution of Chemical Engineers.
- Rezaei, R., Mohadesi, M., and Moradi, G.R. (2013) Optimization of biodiesel production using waste mussel shell catalyst. *Fuel*, **109**, 534–541. Elsevier Ltd.
- Ribeiro, R.F.L., Soares, V.C., Costa, L.M., and Nascentes, C.C. (2015) Production of activated carbon from biodiesel solid residues: An alternative for hazardous metal sorption from aqueous solution. *Journal of Environmental Management*, **162**, 123–131.
- Rodrigues, L.A., De Sousa Ribeiro, L.A., Thim, G.P., Ferreira, R.R., Alvarez-Mendez, M.O., and Coutinho, A.D.R. (2013) Activated carbon derived from macadamia nut shells: An effective adsorbent for phenol removal. *Journal of Porous Materials*, **20**, 619–627.
- Rodríguez-Reinoso, F. (1998) The role of carbon materials in heterogeneous catalysis. *Carbon*, **36**, 159–175.
- Rohman, A. and Man, Y.B.C. (2011) Palm oil analysis in adulterated sesame oil using chromatography and FTIR spectroscopy. *European Journal of Lipid Science and Technology*, **113**, 522–527.
- Roschat, W., Siritanon, T., Yoosuk, B., and Promarak, V. (2016) Biodiesel production from palm oil using hydrated lime-derived CaO as a low-cost basic heterogeneous

- catalyst. *Energy Conversion and Management*, **108**, 459–467. Elsevier Ltd.
- Rovani, S., Rodrigues, A.G., Medeiros, L.F., Cataluña, R., Lima, É.C., and Fernandes, A.N. (2016) Synthesis and characterisation of activated carbon from agroindustrial waste—Preliminary study of 17 $\beta$ -estradiol removal from aqueous solution. *Journal of Environmental Chemical Engineering*, **4**, 2128–2137. Elsevier B.V.
- Rugayah, A.F., Astimar, A.A., and Norzita, N. (2014) Preparation and characterisation of activated carbon from palm kernel shell by physical activation with steam. *Journal of Oil Palm Research*, **26**, 251–264.
- Saba, T., Estephane, J., El, B., El, M., Khazma, M., El, H., and Aouad, S. (2016) Biodiesel production from refined sun flower vegetable oil over KOH / ZSM5 catalysts. *Renewable Energy*, **90**, 301–306.
- Sahira, J., Mandira, A., Prasad, P.B., and Ram, P.R. (2013) Effects of Activating Agents on the Activated Carbons Prepared from Lapsi Seed Stone. *Research Journal of Chemical Science*, **3**, 19–24.
- Samad, S., Shyuan, K., Yin, W., and Khoon, T. (2017) Carbon and non-carbon support materials for platinum-based catalysts in fuel cells. *International Journal of Hydrogen Energy*, **43**, 7823–7854. Elsevier Ltd.
- Santos, R.C.R., Vieira, R.B., and Valentini, A. (2014) Optimization study in biodiesel production via response surface methodology using dolomite as a heterogeneous catalyst Regina C.R. Santos, Rômulo B. Vieira, and Antoninho Valentini. *Journal of Catalyst*, **2014**, 1–11.
- Shafie, S.M., Mahlia, T.M.I., Masjuki, H.H., and Andriyana, A. (2011) Current energy usage and sustainable energy in Malaysia: A review. *Renewable and Sustainable Energy Reviews*, **15**, 4370–4377. Elsevier Ltd.
- Shamsuddin, M.S., Yusoff, N.R.N., and Sulaiman, M.A. (2016) Synthesis and Characterization of Activated Carbon Produced from Kenaf Core Fiber Using H<sub>3</sub>PO<sub>4</sub> Activation. *Procedia Chemistry*, **19**, 558–565. Elsevier Ltd.
- Shoab, M. and Al-Swaidan, H.M. (2015) Optimization and characterization of sliced activated carbon prepared from date palm tree fronds by physical activation. *Biomass and Bioenergy*, **73**, 124–134. Elsevier Ltd.
- Shu, Q., Gao, J., Nawaz, Z., Liao, Y., Wang, D., and Wang, J. (2010) Synthesis of biodiesel from waste vegetable oil with large amounts of free fatty acids using a carbon-based solid acid catalyst. *Applied Energy*, **87**, 2589–2596. Elsevier Ltd.
- Sing, C.Y. and Aris, M.S. (2013) A Study of Biomass Fuel Briquettes from Oil Mill Residues. *Asian Journal of Scientific Research*, **6**, 537–545.
- Singh, A.K. and Fernando, S.D. (2008) Transesterification of Soybean Oil Using Heterogeneous Catalysts. *Energy & Fuels*, **9**, 2067–2069.
- Singh, R.P., Ibrahim, M.H., Esa, N., and Iliyana, M.S. (2010) Composting of waste from palm oil mill: A sustainable waste management practice. *Reviews in Environmental Science and Biotechnology*, **9**, 331–344.
- Sinha, S., Agarwal, A.K., and Garg, S. (2008) Biodiesel development from rice bran



- oil: Transesterification process optimization and fuel characterization. *Energy Conversion and Management*, **49**, 1248–1257.
- Song, C., Wu, S., Cheng, M., Tao, P., Shao, M., and Gao, G. (2014) Adsorption studies of coconut shell carbons prepared by KOH activation for removal of lead(ii) from aqueous solutions. *Sustainability (Switzerland)*, **6**, 86–98.
- Srilatha, K., Sree, R., Prabhavathi Devi, B.L.A., Sai Prasad, P.S., Prasad, R.B.N., and Lingaiah, N. (2012) Preparation of biodiesel from rice bran fatty acids catalyzed by heterogeneous cesium-exchanged 12-tungstophosphoric acids. *Bioresource Technology*, **116**, 53–57. Elsevier Ltd.
- Stamenkovic, O.S., Veljkovic, V.B., Mckay, G., Bazargan, A., and Kostic, M.D. (2015) A calcium oxide-based catalyst derived from palm kernel shell gasification residues for biodiesel production. *Fuel*, **150**, 519–525.
- Sukasem, N. and Manophan, S. (2017) The Development of Biodiesel Production from and Vegetable Oils by Using Different Proportions of Lime Catalyst and Sodium Hydroxide. *Energy Procedia*, **138**, 991–997. Elsevier B.V.
- Sulaiman, F., Abdullah, N., and Rahman, A.A. (2011) Basic Properties of Washed and Unwashed Oil Palm Wastes. Pp. 307–311 in: *Proceedings of the 3rd CUTSE International Conference*.
- Sulihatimarsyila, N.U.R., Wafti, A.B.D., Lik, H., Lau, N., Loh, S.O.H.K., Aziz, A.A., Rahman, Z.A.B., and May, C.Y. (2017) ACTIVATED CARBON FROM OIL PALM BIOMASS AS POTENTIAL ADSORBENT FOR PALM OIL MILL EFFLUENT TREATMENT. *Journal of Oil Palm Research*, **29**, 278–290.
- Sun, K., Leng, C., Jiang, J., Bu, Q., Lin, G., Lu, X., and Zhu, G. (2017) Microporous activated carbons from coconut shells produced by self-activation using the pyrolysis gases produced from them, that have an excellent electric double layer performance. *New Carbon Materials*, **32**, 451–459. Institute of Coal Chemistry, Chinese Academy of Sciences.
- Suryaputra, W., Winata, I., Indraswati, N., and Ismadji, S. (2013) Waste capiz (*Amusium cristatum*) shell as a new heterogeneous catalyst for biodiesel production. *Renewable Energy*, **50**, 795–799. Elsevier Ltd.
- Syamsuddin, Y. and Hameed, B.H. (2016) Synthesis of glycerol free-fatty acid methyl esters from *Jatropha* oil over Ca-La mixed-oxide catalyst. *Journal of the Taiwan Institute of Chemical Engineers*, **58**, 181–188. Elsevier Ltd.
- Syamsuddin, Y., Murat, M.N., and Hameed, B.H. (2015) Transesterification of *Jatropha* oil with dimethyl carbonate to produce fatty acid methyl ester over reusable Ca-La-Al mixed-oxide catalyst. *Energy Conversion and Management*, **106**, 1356–1361. Elsevier Ltd.
- Tang, Z., Claveau, D., Corcuff, R., Belkacemi, K., and Arul, J. (2008) Preparation of nano-CaO using thermal-decomposition method. **62**, 2096–2098.
- Taufiq-yap, Y.H., Hwa, S., Rashid, U., Islam, A., and Zobir, M. (2014) Transesterification of *Jatropha curcas* crude oil to biodiesel on calcium lanthanum mixed oxide catalyst: Effect of stoichiometric composition. *Energy Conversion and Management*, **88**, 1290–1296. Elsevier Ltd.

- Taufiq-Yap, Y.H., Lee, H. V., Hussein, M.Z., and Yunus, R. (2011) Calcium-based mixed oxide catalysts for methanolysis of *Jatropha curcas* oil to biodiesel. *Biomass and Bioenergy*, **35**, 827–834. Elsevier Ltd.
- Thinnakorn, K. and Tscheikuna, J. (2014) Biodiesel production via transesterification of palm olein using sodium phosphate as a heterogeneous catalyst. *Applied Catalysis A: General*, **476**, 26–33. Elsevier B.V.
- Tsyntsarski, B., Stoycheva, I., Tsoncheva, T., Genova, I., Dimitrov, M., Petrova, B., Paneva, D., Cherkezova-Zheleva, Z., Budinova, T., Kolev, H., Gomis-Berenguer, A., Ania, C.O., Mitov, I., and Petrov, N. (2015) Activated carbons from waste biomass and low rank coals as catalyst supports for hydrogen production by methanol decomposition. *Fuel Processing Technology*, **137**, 139–147. Elsevier B.V.
- Uemura, Y., Omar, W.N., Tsutsui, T., and Yusup, S.B. (2011) Torrefaction of oil palm wastes. *Fuel*, **90**, 2585–2591. Elsevier Ltd.
- Umar, M.S., Urme, T., and Jennings, P. (2018) A policy framework and industry roadmap model for sustainable oil palm biomass electricity generation in Malaysia. **128**.
- Üner, O., Geçgel, Ü., and Bayrak, Y. (2015) Preparation and characterization of mesoporous activated carbons from waste watermelon rind by using the chemical activation method with zinc chloride. *Arabian Journal of Chemistry*.
- Uprety, B.K., Chaiwong, W., Ewelike, C., and Rakshit, S.K. (2016) Biodiesel production using heterogeneous catalysts including wood ash and the importance of enhancing byproduct glycerol purity. *Energy Conversion and Management*, **115**, 191–199. Elsevier Ltd.
- Le Van, K. and Luong Thi, T.T. (2014) Activated carbon derived from rice husk by NaOH activation and its application in supercapacitor. *Progress in Natural Science: Materials International*, **24**, 191–198. Elsevier.
- Viriya-empikul, N., Krasae, P., Nualpaeng, W., Yoosuk, B., and Faungnawakij, K. (2012) Biodiesel production over Ca-based solid catalysts derived from industrial wastes. *Fuel*, **92**, 239–244. Elsevier Ltd.
- Wahid, M.B. (2011) Malaysian Palm Oil Board [ MPOB ]. *Malaysian Palm Oil Board [ MPOB ]*, **2011**, 1–59.
- Wang, J. and Kaskel, S. (2012) KOH activation of carbon-based materials for energy storage. *Journal of Materials Chemistry*, **22**, 23710–23725.
- Wang, L., Wang, S., Deng, X., Zhang, Y., and Xiong, C. (2014) Development of Coconut Shell Activated Carbon-Tethered Urease for Degradation of Urea in a Packed Bed. *Sustainable Chemistry and Engineering*, **2**, 433–439.
- Wang, Y.T., Fang, Z., Zhang, F., and Xue, B.J. (2015a) One-step production of biodiesel from oils with high acid value by activated Mg-Al hydrotalcite nanoparticles. *Bioresource Technology*, **193**, 84–89. Elsevier Ltd.
- Wang, Y.X., Ngo, H.H., and Guo, W.S. (2015b) Preparation of a specific bamboo based activated carbon and its application for ciprofloxacin removal. *Science of the Total Environment*, **533**, 32–39.

- Wei, T., Wu, C., Li, F., and Li, J. (2018) Low-cost and environmentally benign selenides as promising thermoelectric materials. **4**, 304–320.
- Wellert, S., Karg, M., Imhof, H., Steppin, A., Altmann, H.J., Dolle, M., Richardt, A., Tiersch, B., Koetz, J., Lapp, A., and Hellweg, T. (2008) Structure of biodiesel based bicontinuous microemulsions for environmentally compatible decontamination: A small angle neutron scattering and freeze fracture electron microscopy study. *Journal of Colloid and Interface Science*, **325**, 250–258.
- Xiao, J., Xu, Q., Xu, Q., Jiang, W., Zhang, J., and Wei, X. (2016) Direct promotion effect of Fe on no reduction by activated carbon loaded with Fe species. *The Journal of Chemical Thermodynamics*, **95**, 216–230. Elsevier Ltd.
- Xie, W. and Zhao, L. (2013) Production of biodiesel by transesterification of soybean oil using calcium supported tin oxides as heterogeneous catalysts. *Energy Conversion and Management*, **76**, 55–62. Elsevier Ltd.
- Xie, W. and Zhao, L. (2014) Heterogeneous CaO-MoO<sub>3</sub>-SBA-15 catalysts for biodiesel production from soybean oil. *Energy Conversion and Management*, **79**, 34–42.
- Xie, W., Peng, H., and Chen, L. (2006) Transesterification of soybean oil catalyzed by potassium loaded on alumina as a solid-base catalyst. *Applied Catalysis A: General*, **300**, 67–74.
- Yacob, A.R., Majid, Z.A., Sari, R., and Dasril, D. (2008) Comparison of Various Sources of High Surface Area Carbon Prepared By Different Types of Activation. *The Malaysian Journal of Analytical Sciences*, **12**, 264–271.
- Yacob, A.R., Noordin, N.P., Sulaiman, N.F., Khairul, M., and Amat, A. (2011) Single Step Transesterification of Palm Oil Using Prepared Calcium Oxide. **1**, 1004–1009.
- Yadav, M. and Sharma, Y.C. (2018) Process optimization and catalyst poisoning study of biodiesel production from kusum oil using potassium aluminum oxide as efficient and reusable heterogeneous catalyst. *Journal of Cleaner Production*, **199**, 593–602.
- Yang, T. and Lua, A.C. (2003) Characteristics of activated carbons prepared from pistachio-nut shells by potassium hydroxide activation. *Microporous and Mesoporous Materials*, **63**, 113–124.
- Yeganeh, M.M., Kaghazchi, T., and Soleimani, M. (2006) Effect of Raw Materials on Properties of Activated Carbons. *Chemical Engineering & Technology*, **29**, 1247–1251.
- Zabid, M.F.M., Abidin, N.Z., and Applanaidu, S. (2018) Implications of Palm-based Biodiesel Blend Mandate on the Biodiesel Industry Growth in Malaysia: Evidence from Causal Loop Diagram. *Institutions and Economies*, **10**, 81–100.
- Zhang, J. and Meng, Q. (2014) Preparation of KOH / CaO / C Supported Biodiesel Catalyst and Application Process. *World Journal of Engineering and Technology*, **2**, 184–191.
- Zhang, J., Chen, S., Yang, R., and Yan, Y. (2010a) Biodiesel production from vegetable oil using heterogenous acid and alkali catalyst. *Fuel*, **89**, 2939–2944.

Elsevier Ltd.

- Zhang, L., Sheng, B., Xin, Z., Liu, Q., and Sun, S. (2010b) Kinetics of transesterification of palm oil and dimethyl carbonate for biodiesel production at the catalysis of heterogeneous base catalyst. *Bioresource Technology*, **101**, 8144–8150. Elsevier Ltd.
- Zhang, Y., Wong, W.T., and Yung, K.F. (2013) One-step production of biodiesel from rice bran oil catalyzed by chlorosulfonic acid modified zirconia via simultaneous esterification and transesterification. *Bioresource Technology*, **147**, 59–64. Elsevier Ltd.
- Zhao, L., Qiu, Z., and Stagg-Williams, S.M. (2013) Transesterification of canola oil catalyzed by nanopowder calcium oxide. *Fuel Processing Technology*, **114**, 154–162. Elsevier B.V.
- Zu, Y., Liu, G., Wang, Z., Shi, J., Zhang, M., Zhang, W., and Jia, M. (2010a) CaO supported on porous carbon as highly efficient heterogeneous catalysts for transesterification of triacetin with methanol. *Energy and Fuels*, **24**, 3810–3816.
- Zu, Y., Liu, G., Wang, Z., Shi, J., Zhang, M., Zhang, W., and Jia, M. (2010b) CaO Supported on Porous Carbon as Highly Efficient Heterogeneous Catalysts for Transesterification of Triacetin with Methanol. 3810–3816.
- Zullaikah, S., Lai, C.-C., Vali, S.R., and Ju, Y.-H. (2005) A two-step acid-catalyzed process for the production of biodiesel from rice bran oil. *Bioresource technology*, **96**, 1889–96.