

Gamma Irradiation-Assisted Synthesis of Silver Nanoparticle and Their Antimicrobial Applications: A Review

Salmah Mossa, Kamyar Shameli *

Department of Environment and Green Technology, Malaysia-Japan International Institute of Technology, Universiti Teknologi Malaysia, Jalan Sultan Yahya Petra, 54100 Kuala Lumpur, Malaysia

* Correspondence: E-mail: kamyarshameli@gmail.com; Tel: +603-22031200

<https://doi.org/10.37934/jrnn.3.1.5375>

ABSTRACT

This review presents an introduction to the synthesis of silver nanoparticles (Ag-NPs) by gamma irradiation method. This method offers some benefits over the conventional methods because it provides fully reduced and highly pure nanoparticles free from by-products or chemical reducing agents, and is capable of controlling the particle size and structure. The nucleation and growth mechanism of metallic nanoparticles are also discussed. The competition between nucleation and growth process in the formation of nanoparticles can determine the size of nanoparticles which is influenced by certain parameters such as the choice of solvents and stabilizer, the precursor to stabilizer ratio, pH during synthesis, and absorbed dose. The present review, summarizes the gamma irradiation synthesis of Ag-NPs procedure, advantages, applications and their antibacterial properties.

Keywords:

Gamma irradiation; Silver nanoparticles;
Antimicrobial, Chemical reduction method.

Received: 28 May 2021

Revised: 22 June 2021

Accepted: 29 June 2021

Published: 7 August 2021

1. Introduction

1 Nanoparticles (NPs) are diversely ultra-structured particles either engineered and manufactured
2 which have one dimension within the nano-scale diameters within the range from 1 to 100 nm [1, 2].
3 NPs stands for the billionth part of a meter, numerically written as 1×10^{-9} meter with unique
4 properties such as size-dependent qualities, high surface-to-volume ratio and unique optical
5 properties at a critical length scale [3, 4]. As the size of NPs decrease, the surface area and energy
6 increase; causing major changes to the physical, chemical and biological properties of from their
7 conventional properties as bulk materials due to quantum effects [5–9]. Wider surface area provides
8 sufficient binding sites for chemical reaction which confers the increase in catalytic activity [10, 11] as
9 well as increases effective interaction with the microorganisms leading to high antimicrobial
10 behavior.
11

1 The unique characteristics of NPs such as size, surface area, shapes, composition, determines their
2 function and applications. such as sensors biomaterials [12], antimicrobial/antiseptic, medical [13–
3 15]. Henceforth, the interest in preparing NPs designed to meet specific needs by surface
4 modifications, controlling of their elementary size, shape and morphologies, have captured the
5 interest of many to explore further [16].


6 Lately, incorporation of inorganic metal NPs into polymer matrix has received widespread
7 attraction as the resulting metal nanocomposites possess superior strength and improved
8 performance to better extent with affordable cost and wider applications. Metals NPs exhibit
9 remarkable physical, chemical, and biological properties and are being explored as a promising
10 approach to combating resistance to antibiotic. Since they effectively bridge bulk materials and atomic
11 or molecular structures, metal NPs are now an important area of scientific research.

12

13 2. Silver Nanoparticles

14 Silver nanoparticles (Ag-NPs) are among the most favored metal NPs due to the multiple
15 functionality as pronounced antimicrobial agent [17–19], combined with antifungal effect of Ag-NPs
16 on dermatophytes [20, 21], anti-cancer [22], anti-inflammatory [23], antiviral [24], anti-angiogenesis
17 [25] and antiplatelet activities [26], has made them the most used NPs to treat various diseases and
18 infections [27] making them significant in the field of medicine and health care. Ag-NPs also
19 demonstrated good catalytic properties in the field of dye detoxification, heavy metal removal and
20 remediation [28, 29]. Ag-NPs has been explored widely and used in various industrial applications
21 and incorporated into a variety of household and consumer products including textiles, cosmetics,
22 paints, coatings, sensor, agricultural and food packaging, with a relatively high usage compared to
23 other metals and alkaline earth metals in NPs applications [30] (Figure 1). The optical properties of
24 metal NPs commonly used in various biochemical applications for food safety monitoring [127] and
25 marine toxin detection [32]. They also have demonstrated excellent catalytic activities [33] and due to
26 their exclusive structures and properties [34], and extensively applied in the field of homo and
27 heterogeneous catalysis [35–37]. Due to the combination of small size with a large surface area, Ag-
28 NPs have strong adsorption reactivity and capacity [38-40], thus Ag-NPs are promising tools for
29 applicability in various wastewater ecosystems.

30

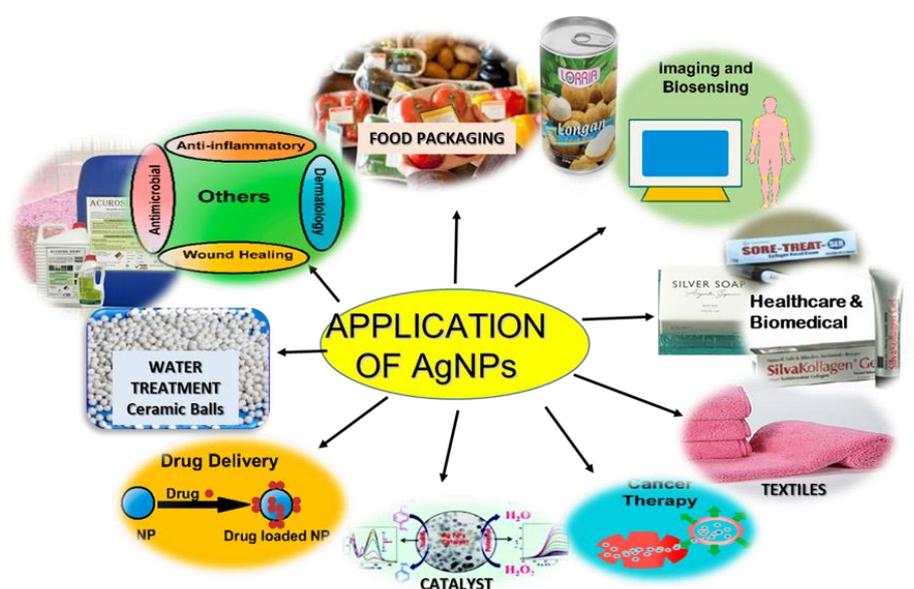

31

32

Figure 1: Various applications of Ag-NPs.

1 The biggest contribution (54%) of Ag-NPs are in the health and fitness, followed by cleaning and
2 disinfecting (11%), food (10%), household equipment (6%), medicine (4%), electronic devices (3%)
3 and others (12%) [41]. Their antimicrobial properties [42–44] are widely used in medicine sector such
4 as antibacterial sprays, medicine, wound dressings [45], respirators, and heart valves [46–50]. Ag-NPs
5 have also exhibited antimalarial [51], antiviral [52], anticancer [53–55], anti-plasmodial [51], larvicidal
6 [56], antifungal [57, 54, 42, 58, 59], biofilm forming bacteria [60, 61], and pupicidal activity [62],
7 disinfections, water and air purification, agriculture [63, 64], etc. These properties of silver encourage
8 its use in, cosmetics, clothing and numerous household products, contraceptives, detergent,
9 dietary supplements, cutting boards, socks, shoes, cell phones, laptop keyboards, and children's toys
10 [65, 66]. Ag-NPs are one of the most promising system to fight the emergence of pathogenic bacterial
11 strains and the increase of resistant microorganisms resulted from the excessive use of antibiotics [67].
12 Nanotechnology products database 2019 reported, Ag-NCs have been used in 278 different types of
13 product in 34 countries and 15 industries with diverse properties and applications [68, 69].

14 The specific properties of NPs such as size, shape, charge, and the composition material of the
15 nanomaterial determine its specific activity [70]. Silver NPs can now be engineered to provide unique
16 functionalities such as larger surface to volume ratio resulting into higher surface exposure and an
17 increased rate of interaction between the test subjects and the ionic silver [71, 45, 50, 72–74].
18

19 3. Polymeric Support

20 The only limitation is small size Ag-NPs tends to agglomerate in solution (Figure 2), which will
21 reduce their surface area hence deteriorate its capability to be used as an adsorbent, catalyst,
22 antibacterial activity [75-77]. This can be resolved by adding a substrate which will promote strong
23 interaction among the substrate and the NPs, reducing agglomeration effectively, thus enhancing
24 their catalytic activity [78-79]. Therefore Ag metals are usually dispersed on a suitable support with
25 large surface area for easy recovery and to enhance the dispersity and stability of Ag-NCs [80-84].
26



27
28 **Figure 2:** Synthesis mechanism of Ag-NPs.

29 The addition of supports is highly recommended to prevent agglomeration and as a stabilizer by
30 providing a barrier and in controlling both the size and shape, and the final distribution of NPs [85–
31 87]. The selection of the support material is critical as it may enhance or reduce the efficiency of Ag-
32 NPs [88, 89]. Many researches focused on the stabilization of Ag on adsorbent materials, including
33 cellulose fiber [90], polyethersulfone microfiltration membranes [91], clay [92], and activated carbon
34 [93]. Clay materials are promising matrices for the preparation of Ag-NPs as they are available
35 abundantly, cheap, good adsorbent, high specific surface area and ion exchange capacity, chemical
36 stability and reusability [94–96]. Anchoring Ag-NPs on the surface of Kaolinite (Kln) is expected to
37 be an economical and efficient catalyst for decomposition of organic contaminants [97]. One of the
38 most effective and promising biomaterials are NCs based on Ag-NPs are Chitosan (Cts) [98] due to

1 their significant antimicrobial activities against Gram-negative and Gram-positive bacteria and low
2 toxicity toward mammalian cells [99-100].


3 **4. Synthesis of Silver Nanocomposites**

4 Synthesis of Ag-NPs such as the choice of the reducing and stabilizing agent play a major role in
5 determining NPs with controlled structures and applications. The characteristic feature of
6 nanomaterials, are continually developed in comparison to other NPs due to its significant
7 antibacterial properties [101, 102]. Ag-NPs can be synthesized by different techniques, such as
8 evaporation-condensation [103], laser ablation [104], gamma irradiation [105], lithography [106],
9 micro-emulsion techniques [107], microwave-assisted technique [108] and biosynthesis using plants
10 [109]. Generally, three different methods of synthesis used are physical, chemical, and biological
11 method [110, 111]. However, the most common method used by the industry for production of Ag-
12 NCs are the chemical methods.

13 **5. Chemical Synthesis of Nanoparticles**

14 Among the existing methods, synthesis by chemical reduction have been enormously employed
15 and preferred for large quantities production of the NPs within short duration, specific size and shape
16 [112–114]. The advantage of the chemical synthesis are pure Ag-NCs can be produced at low cost
17 because of its low instrument requisites, minuscule duration and excessive yield. However, the
18 disadvantage of the chemical method is high consumption of hazardous chemicals which are harmful
19 to living organisms and waste disposal to the environment [115, 116]. Basically, the reduction of silver
20 salts involves three main components, such as metal precursors, reducing agents, and
21 stabilizing/capping agents. The most commonly used reducing agents are sodium borohydride,
22 sodium hydroxide, sodium citrate, hydrazine hydrate, tollens reagents, N, N-dimethylformamide,
23 poly(ethylene glycol)-block copolymers and ammonium formate [117–119].

24 In a chemical reaction, an oxidizing agent gains electrons and is itself reduced whereas a reducing
25 agent loses electrons and is oxidized. Ag-NCs were prepared by mixing AgNO₃ a precursor with
26 sodium borohydride (NaBH₄), a reducing agent. The silver ions (Ag⁺) gain electrons and are reduced
27 to silver atoms (Ag⁰). The atoms will agglomerate into oligomeric clusters, which will eventually lead
28 to the formation of Ag-NCs.






32 A stabilizer is usually added to prevent agglomeration and control the formation and stabilize
33 the NCs. Additionally, the NCs produced by chemical synthesis will be sedimented with chemicals
34 and are not applicable for biomedical application [120].

35 **6. Gamma Irradiation Synthesis of Silver Nanoparticles**

36 Gamma (γ) irradiation is a mature and powerful technology to be considered for the synthesis of
37 Ag-NPs. Irradiation technique is considered a “green technique” as it does not require chemical
38 initiator for reduction unlike the conventional methods [121]. It is a simple, clean process which can
39 be performed using aqueous system, at ambient pressure and room temperature. The reduction of

1 metal NPs by γ -irradiation is controlled by the dose of irradiation while the NPs produced are very
 2 pure, fully reduced without traced of chemical [122]. γ -radiation is a promising green technique for
 3 producing a wide range of materials, particularly polymeric materials and suitable for large-scale
 4 production [123]. Polyvinylpyrrolidone /carboxymethyl cellulose prepared by γ -radiation increases
 5 the swelling and improves the water retention capability which governs the slow release of the
 6 hydrogels bringing release rate of urea 10 times higher than that of phosphate [124]. The reduction of
 7 Ag ions (Ag^+) to Ag atoms (Ag^0) was achieved by the reducing species in the mixture solution.

8 When irradiation is applied to metal ions in an aqueous solution, irradiation energy is absorbed
 9 in water, which causes radiolysis of water and several products are generated, including hydrated
 10 electrons (e_{aq}^-), radical hydrogen atoms ($H\bullet$) and radical hydroxyl ($OH\bullet$) which are dispersed
 11 uniformly in the reaction medium (Eq. 1) [125]. The radiolytic method via γ -radiation is a powerful
 12 technique which can produce the desired morphology and distribution of metal NCs by adjusting the
 13 dose of irradiation [126]. In the aqueous solution, $AgNO_3$ separates to Ag^+ and NO_3^- ions as shown in
 14 Eq. 2. The powerful reductant generated from the radiolytic process, such as active electrons e_{aq}^- and
 15 H atoms ($H\bullet$), will reduce silver ions (Ag^+) to the zerovalent state (Ag^0) (Eqs. 3-4).



16 The reduced neutral silver atom Ag^0 tend to interact with other metal ions to form relatively
 17 stable Ag clusters which combines with neighbouring silver atoms and progressively grew into large
 18 clusters to form spherical Ag-NCs [127, 128] as follows (Eqs. 5-8):



19 Where:

20 $(Ag)_n$ = Silver nanocluster containing "n" silver atom

21 e_{aq}^- = Aqueous electron hydrogen atoms ($H\bullet$)

22 These processes occur simultaneously and the morphology (particle size and shape) and stability
 23 of the resulting Ag-NPs depends highly on the $AgNO_3$ concentration, carrier or stabilizer, irradiation
 24 dose and the synthesis route selected for reduction.

25 7. Advantages of Synthesis by Gamma Irradiation

26 Gamma (γ) irradiation is simple, rapid and environmental friendly strategy to uniformly
 27 penetrate thick layers of materials or organic matters without noticeable decay of the organic matrix
 28 [121]. Irradiation was also demonstrated to be an effective method to increase the kinetics of metal
 29 ion reduction at ambient temperature without excessive reducing agent thus leading to a more

1 environmentally friendly process to generate metal NPs [129]. γ -radiation techniques produce pure
2 Ag-NPs with narrow particle size distribution, homogenous and instantaneous without needing
3 clean up or purification as there are no pollutants, providing a clean alternative over chemical and
4 physicochemical methods [130]. This methodology has therefore been shown to be a powerful
5 approach revolutionary techniques that provides unique advantages over conventional techniques
6 [131].

7 Specifically, gamma radiation is well known to induce gelatin crosslinking and afford a three-
8 dimensional network by forming chemical bonds [5] between molecular backbones [6]. Advantages
9 of radiation-induced polymer degradation include its ability to promote reproducible and
10 quantitative changes without the introduction of chemical reagents and concomitantly occurring
11 product sterilization [7]. In addition to crosslinking, the incorporation of natural fibers (such as
12 cellulose) into gelatin helps to improve the mechanical and thermal properties of the corresponding
13 hydrogels. Generally, radicals are formed from chain scission of the polymer chain in high-energy
14 crosslinking, especially when irradiating dried gelatin or cellulose in the presence of oxygen.

15 **8. Gamma Irradiation-Assisted Synthesis of Cellulose Nanocrystal-Reinforced Gelatine** 16 **Hydrogels**

17 It was observed that for NCs smaller than 100 nm, sphere shape NCs displayed higher cellular
18 uptake than nanorods while for NCs larger than 100 nm nanorods exhibits higher cellular uptake
19 followed by spheres [26]. Spherical Ag-NCs, with size within 10 -15 nm possess antiplatelet
20 properties [26] and are less toxic [132]. Frankova *et al.* reported, spherical Ag-NCs with an average
21 size of 10 nm exhibit biocompatibility for fibroblasts and keratinocytes [133].

22 **9. Effect of Ag Ions Concentration to the Controlling Size of Ag-NPs**


23 The increase in particle size at higher precursor concentration is also observed in many cases. By
24 increasing the concentration of metal ions, final size of Ag-NCs increases due to the rate of ion
25 association that forms larger particles increases. The sizes of NCs are much smaller than those
26 obtained by Hamouda *et al.* [134], which was in the range of 8-17 nm for Ag-NPs from chemical
27 synthesis while 9-21 nm in size for biological synthesis. While Balakarthikeyan *et al.* confirmed the
28 nano size between 68 to 100 nm obtained from synthesis using NaBH_4 [135]. Ag-NPs synthesized
29 chemically using PVP as stabilizer reported NCs of 20.4 nm in size [136]. Green synthesis utilizing
30 *Citrullus lanatus* fruit rind as a reductant and capping agent yields stable, spherical Ag-NPs with an
31 average diameter of 17.96 ± 0.16 nm [110]. Ag-NCs reduced using NaBH_4 showed the formation of
32 cubical NCs with size range from 22-28 nm and 56-72 nm for biological synthesis [60]. Moosa *et al.*
33 also reported an increase in the size of silver kaolinite nanocomposites (Ag/Kln NCs) with the increase
34 in silver nitrate concentration. Similar observation was reported for silver kaolinite NPs synthesized
35 using gamma irradiation. As the

36 **9. Antimicrobial Activity of Ag-NPs**

37 Historically, silver was considered an effective antibacterial substance before the invention of
38 antibiotics and used to prevent inflammation and infections when treating battle wounds during the
39 First World War [45]. Silver compounds displayed strong antibacterial against a wide range of
40 antibacterial spectrum [101], antiviral, antifungal, biocidal and anti-inflammatory activities [137, 138],
41 and are being incorporated into composite for biomedical applications as a better therapeutic
42 strategy. Previous studies have reported the powerful antimicrobial properties of Ag-NPs against

1 various multidrug resistant strains like *Pseudomonas aeruginosa*, ampicillin-resistant *E. coli*,
2 erythromycin-resistant *Streptococcus pyogenes*, methicillin-resistant *S. aureus* (MRSA), vancomycin-
3 resistant *S. aureus* (VRSA) [139, 140] and other eukaryotic microorganisms as compared to other
4 metals. Ag-NPs were being also found to be effective for the inhibition of several viruses including
5 hepatitis B virus, respiratory syncytial virus, herpes simplex virus type, monkey pox virus, [141],
6 HIV-1 virus [142, 143] and a large number of fungi *Aspergillum*, *Candida* and *Saccharomyces*. The
7 intrinsic cytotoxic property of Ag-NPs has been applied against various types of cancer cells, such as
8 hepatocellular carcinoma, lung and breast cancer and cervical carcinoma [144].

9 It is believed, Ag-NPs anchor to the surface of the bacterial cell wall and penetrate it to cause
10 structural changes to the membrane or increase its permeability, all of which trigger cells to die. Once
11 in the cell, silver ions interact with thiol groups in critical bacterial enzymes and proteins, disrupting
12 the respiration and metabolic pathway. This subsequently damage DNA and its production cycle,
13 leading to cell death [142-145]. The antimicrobial process is explained in Figure 3.

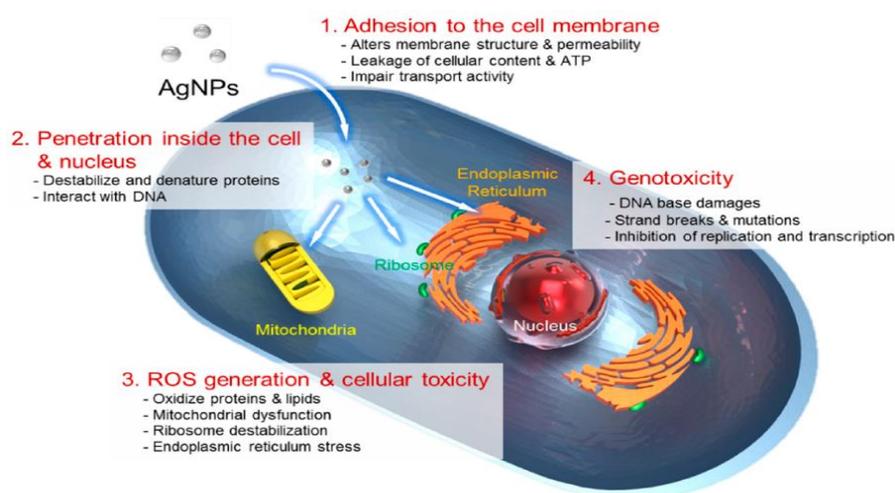


14

15 **Figure 3.** The four most prominent routes of antimicrobial action of Ag-NPs.

16 Some of the factors that influence the antimicrobial properties of Ag-NPs are shape, size, surface
17 charge, capping agent, and synthesis method [146-147]. Size of NPs plays an important role to their
18 antibacterial activity and typically, NPs with size below 50 nm, showed enhanced antimicrobial
19 activity [147]. Smaller NPs, have relatively larger surface area and therefore an enlarged contact area
20 which enhance their biological and chemical activities and increase the release rate of silver ion to
21 enhance antimicrobial activities [148, 149]. Ag-NPs within 1 to 30 nm size are the most commonly
22 used range and were found to be optimal against *S. aureus* and *Klebsiella pneumonia*, while 10–15
23 nm range sizes have highest antimicrobial activity. It was observed that Ag-NPs of size 22.5 nm
24 enhance the antibacterial activity of penicillin G, amoxicillin, erythromycin, clindamycin, and
25 vancomycin [65]. Studies on poly(acrylamide/itaconic acid) as a stabilizer for prepared of Ag-NPs by
26 gamma radiation demonstrated that size were 50 to 42 nm when the irradiation dose is increased
27 from 20 to 50 kGy [150]. While other studies show increase in size with the increase of irradiation
28 dose.

29 Beside the size, electrostatic interaction caused by difference of charge between the negatively
30 charged microorganism cell membrane and the positively charged Ag-NPs, plays an important role
31 [151]. The difference of charge causes the Ag-NPs to be accumulated on the cell membrane, puncture
32 the bacterial cell wall by reacting with the peptidoglycan component, and releasing silver ions into
33 the bacterial cell [152]. The shape of NPs equally accelerates the rate of ion release, studies indicated

1 that spherical and triangular shapes NP seem to have higher antimicrobial activity, while other
2 studies showed truncated triangular Ag-NPs showed the most grounded antibacterial action. The
3 incorporation of silver into a larger number of materials resulted in 95% reduction of antimicrobial
4 activity. Fabrics are now incorporated with engineered Ag-NCs to kill odor-causing bacteria in socks
5 and sports clothing, to prevent microbial spreading as in wound dressing, bedsheets, hospital uniforms,
6 including plastics, coatings, and foams as well as natural and synthetic fibers [153]. Food packaging
7 with coatings of Ag-NPs displayed good inhibition against *L. monocytogenes*, *E. coli*, *P. citrinum*, *S.*
8 *aureus* and *A. niger*, among others resulting in significant reduction of mold and coliforms, increasing
9 shelf life and keeping vegetable, bread and orange juice longer without reducing nutritional values,
10 colour, consistency, flavour and taste the food fresh [154–156]. Ag-NCs deposited into guar gum and
11 on film exhibited improved optical, spectral, thermo-mechanical, oxygen barrier and antimicrobial
12 properties of film for active food packaging applications. In animal husbandry, Ag-NPs are used as
13 a disinfectant to treat against poultry disease caused by yeast from infected cow udders and caused
14 by biological material via eggs, chicken etc. Due to the exceptional antimicrobial properties of Ag-
15 NPs toward a wide range of microorganisms, fungi and viruses, several Ag based medical products
16 have been developed to control microbial proliferation, such as topical creams, antiseptic sprays,
17 cancer therapeutics, pharmaceutical, dentistry, medical devices, bandages, wound healing dressings,
18 disinfectant, bio-imaging and bio-sensing, being efficiently implemented [157]. AgNO₃ and silver
19 sulfadiazine are used to prevent bacterial growth in drinking water, sterilizations and burn care [54].
20 Ag-NCs were found to produce free radicals which will lead to apoptosis resulting in necrobiosis.
21 In low concentrations, Ag has been indicated as non-toxic material to humans, and it has been
22 assessed as a promising material in pharmaceutical and biomedical fields [158], great potential for
23 reducing infections and provides faster healing and better health to the patients [159]. The Ag-NPs
24 with Cts bead hydrogel applied in drug delivery displayed enhanced antibacterial activity against *E.*
25 *coli* and *S. aureus* with controlled and prolonged drug release observed [160].

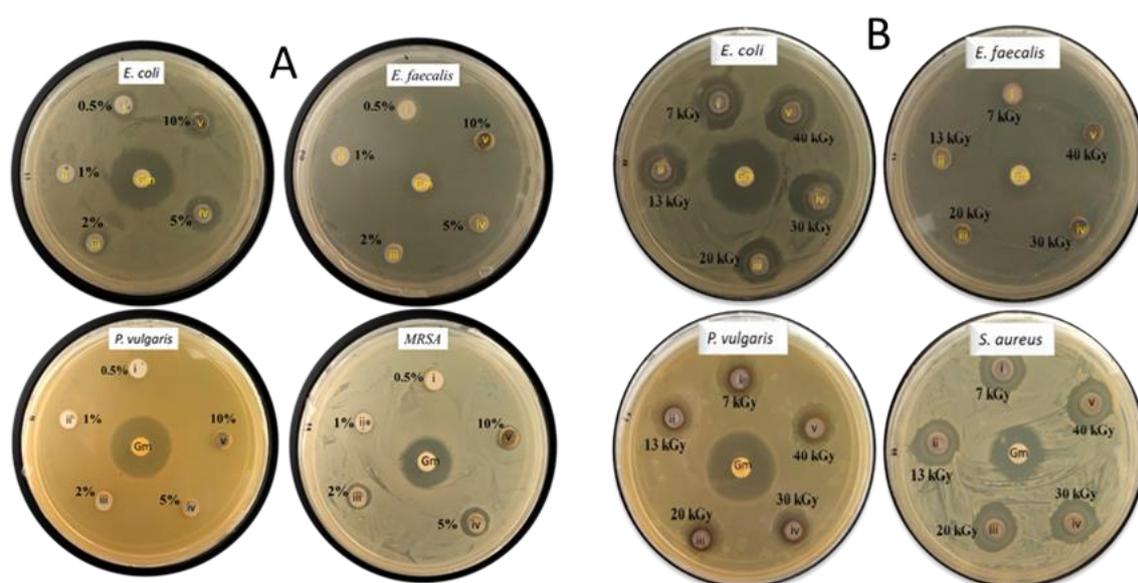

26

27 **Figure 4.** Inhibition zone of Ag/KIn synthesised using **A.** Chemical reduction at 0.5%, 1 %, 2 %, 5 %
28 and 10 % **B.** Gamma reduction at 7, 13, 20, 30, and 40, towards *E. coli*, *E. faecalis*, *P. vulgaris* and MRSA.
29 Gentamicin (Gm, 10 µg/ml) and Nystatin (10 µg/ml) is used as positive control.

30 In a study by S. Moosa *et al* [161], Ag/KIn NCs synthesized using chemical method and gamma
31 irradiation were evaluated against *E. coli*, *S. aureus*, *E. faecalis* and *P. vulgaris* and *C. albicans*. The

1 chemical synthesis Ag/Kln NPs, displayed minimum antimicrobial properties (Figure 4A) compared
2 to the gamma synthesized Ag/Kln NPs (Figure 4B). The strong hydrogen bond network in the Kln
3 matrix prevents the release of Ag⁺ in order to react with bacteria and also hinders any form of
4 intercalation [162, 163]. Meanwhile, the gamma synthesized NPs displayed excellent antimicrobial
5 properties compared to chemically synthesized NPs. Gamma ray irradiation induces the chain
6 scission as well as breaking H bonds and releasing Ag⁺ ions [164]. This suggests that the synthesis
7 method potentially affects the ability of Ag-NCs to release Ag⁺ ions which is also an important factor
8 in determining antimicrobial activity, besides size, shape and structure. From this study, it was
9 observed that the smallest NPs which correspond with Ag/Kln NPs synthesized chemically do not
10 show the best inhibitory effects because of factors preventing Ag⁺ ions release, the main responsible
11 for bacterial inhibition.

12 It was apparent that the gamma synthesized Ag/Kln NCs displayed significantly ($p < 0.05$)
13 highest antibacterial activity than the chemically synthesized Ag/Kln NCs and the gamma
14 synthesized Ag/Kln/Cts BNCs as well towards all the pathogens. The most susceptible bacterial
15 strains were *E. coli*, followed by *P. vulgaris*, *MRSA*, *E. faecalis* and *C. albicans* with zones of inhibition
16 of 17.3, 15.7, 14.7, 11.7 and 15.0 mm, respectively. The remarkably high antimicrobial activity of the
17 gamma synthesized Ag/Kln NCs could be attributed to the release of sufficient silver ions from the
18 Kln surface. γ -irradiation induces the chain scission as well as breaking the strong H bonds tightly
19 interlinking the Kln lamellae and releasing Ag⁺ ions from the tightly bound clay surface [164]. This
20 is evident to conclude that the prepared hybrid Ag/Kln NCs exhibits strong antibacterial activity
21 which can be used as antimicrobial agent for biomedical and food industrial applications. Hence,
22 Ag/Kln-NCs is a promising antimicrobial agent to work with the merits of both advantages of
23 antibacterial and optical enhancing properties, high surface area, strong permeability and low toxicity
24 to the human body and therefore, Ag-NCs constitute a very promising approach for the development
25 of new antimicrobial systems. The literature compiled in Table 1 confirms the potential antimicrobial
26 properties of Ag-NPs synthesis by gamma irradiation with various matrix as support, in a wide range
27 of applications.

28 The polyvinyl alcohol/sodium alginate/Ag-NPs composite films upon exposure to various
29 gamma irradiation doses of 5 to 15 kGy exhibited increased of antibacterial activities against *S. aureus*
30 and *E. coli* [165]. Ag-NPs coating on cotton fabric prohibited *Pseudomonas aeruginosa*,
31 *Staphylococcus aureus*, *Escherichia coli* and *Candida albicans* microbes from proliferating on fabric
32 surface [128]. Study by Gharab *et al* where two types of preparation where the first preparation using
33 silver, chitosan, citrus pectin, sodium alginate were irradiated at 5 kGy and second preparation using
34 *Pleurotus ostreatus* was irradiated at 20 kGy. The synthesized Ag-NPs have potential effect as
35 antioxidant and inhibit cancer cell. Potential Ag-NPs comprising silver chitosan polyethylene oxide
36 synthesized using 20 kGy gamma irradiation have antibacterial activity against gram-negative
37 (*Escherichia coli*) and gram-positive bacterium (*Staphylococcus aureus*) [166].

38 Ag-NPs synthesized with low molecular weight chitosan by gamma irradiation inhibited the
39 growth of Methicillin-resistant *S. aureus* (MRSA) and *Aeromonas hydrophila* bacteria [167]. Silver
40 nanoparticles prepared by γ -ray irradiation at 10–25 kGy using chitosan as a stabilizer formed Ag
41 chitosan NPs exhibited inhibitory activity against *E. coli* and *S. aureus* [168]. γ -irradiation is useful for
42 mass production of Ag-NPs using green techniques, especially in biomedicine. Colloidal Ag chitosan
43 NPs exhibited highly antimicrobial effect against *S. aureus* and *Corticium salmonicolor* [169]. Polyvinyl
44 alcohol/sodium alginate/nano silver (PVA/SA/Ag) composite films by in situ gamma irradiation
45 displayed effective inhibition of *Staphylococcus aureus*, methicillin-resistant *S. aureus* [170].
46 Biosynthesis of Ag-NPs from *Enterococcus sp.* Culture displayed excellent enhanced antimicrobial
47 activity than the commercial antibiotics and potential to inhibit the cell viability of liver cancer cells

1 lines (HepG2) and lung cancer cell lines (A549). Ag-NPs/chitosan synthesized by γ -irradiation
2 showed strong inhibition against *C. cassiicola* and reduce disease incidence of rubber leaves infected
3 by *C. cassiicola*. [171]

4 **Characterization of Silver Nanoparticles**


5 The reduction of silver ions was monitored by visual observation of colour change and was
6 further confirmed by sharp peaks shown by the absorption spectrum recorded by using UV-Vis
7 spectrophotometer. It is well known that Ag-NPs exhibit yellowish-brown color in aqueous solution
8 due to the excitation of surface plasmon resonance (SPR) band in the UV-visible region [173]. This
9 was observed by Moosa *et al.*, in the synthesis of Ag-NPs in kaolinite, upon the addition of NaBH_4 ,
10 the color of the Ag/Kln suspension changed instantly to yellow then to yellowish-brown,
11 subsequently to brown, indicating the formation of Ag-NPs in the kaolinite suspension where Ag^+
12 was reduced to Ag^0 (Figure 5). As the intensities of AgNO_3 increase, so does the intensity of the color
13 of the suspension increases from yellow to brown and darker indicating the formation of Ag/Kln NCs
14 in the kaolinite suspension. Fig 5, shows the colour change of Ag/Kln-NCs suspension from white to
15 yellow, then to yellowish-brown, brown and darker brown upon addition of NaBH_4 .



16

17 **Figure 5.** Photograph of Ag/Kln NCs suspension at different AgNO_3 concentrations synthesized
18 chemically and using gamma irradiation.

19 Similar to the synthesis of Ag/Kln NCs, Aqueous suspensions containing Kln and silver nitrate
20 (1×10^{-2} M AgNO_3), when exposed to different γ -irradiation doses 0, 7, 13, 20, 30, 40, 65 and 80 kGy,
21 displayed a spectrum of greyish to black colors, depending on the absorbed doses. Both chemically
22 synthesized Ag/Kln NCs using NaBH_4 as a reductant agent yielded smaller Ag-NPs than those
23 obtained using gamma irradiation. Beside the synthesis method, the concentration of silver and the
24 irradiation dose also affect the size of NCs. It was revealed that as the concentration of silver or the
25 irradiation dose is increased, the size of the NCs increased as well due to an increase in the reduction
26 of Ag^+ and formation of NCs.

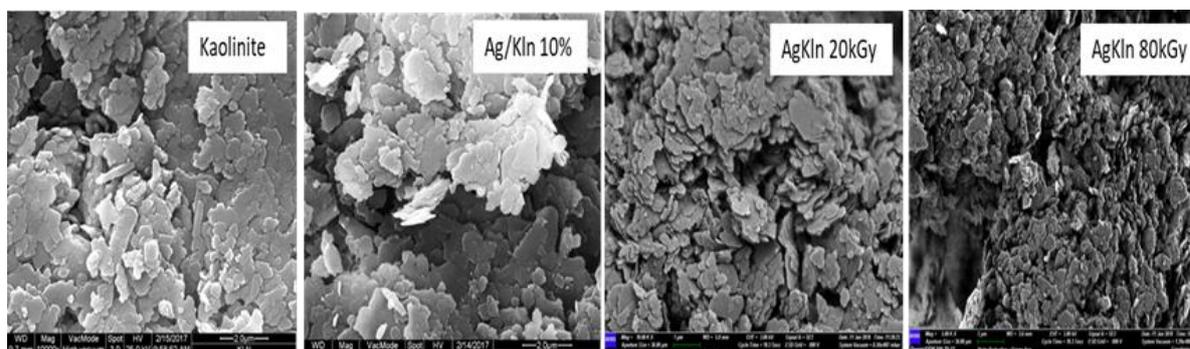

27

28 **Figure 6.** FESEM image of Kln, Ag/Kln 10% synthesized using NaBH_4 , Ag/Kln 20 kGy and Ag/Kln
29 80kGy.

1 **Table 1.** Antimicrobial of Ag-NPs synthesized by gamma irradiation and their applications.

| Ag-NCs of different matrix | Size | Antimicrobial properties and application | References |
|--------------------------------------------------------------------------------------------------------|--------------------------------------------------------------------------------------|------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|------------|
| Polyvinyl alcohol/sodium alginate/nano silver (PVA/SA/Ag) composite films by in situ gamma irradiation | <ul style="list-style-type: none"> ▪ 80 and 100nm | <ul style="list-style-type: none"> ▪ The composite films exhibited increased of antibacterial activities against <i>S. aureus</i> and <i>E. coli</i> upon exposure to various doses of gamma irradiation. ▪ The size of the NPs is reduced from 100 to 80 nm when the irradiation dose increases from 5 kGy to 15 kGy. | [165] |
| Poly(Acrylamide/Itaconic Acid)-Ag-NPs | <ul style="list-style-type: none"> ▪ Spherical ▪ 42 to 50 nm | <ul style="list-style-type: none"> ▪ Excellent antibacterial property against strains of <i>Pseudomonas aeruginosa</i> and slightly active against <i>Escherichia coli</i>, <i>methicillin-resistant Staphylococcus aureus</i>, and <i>Klebsiella pneumoniae</i>. and 20, 30, 40, 50 and 70 kGy | [150] |
| Colloidal Ag-NPs in a water isopropanol polyvinylalcohol system | <ul style="list-style-type: none"> • Spherical • 30 nm | <ul style="list-style-type: none"> ▪ Ag-NPs prepared using 60 Co-gamma radiation at total dose of 35 kGy on cotton fabric prohibited <i>Pseudomonas aeruginosa</i>, <i>Staphylococcus aureus</i>, <i>Escherichia coli</i> and <i>Candida albicans</i> microbes from proliferating on fabric surface. | [128] |
| Ag-NPs synthesized using i. Chitosan, citrus pectin and sodium alginate ii Pleurotus ostreatus. | <ul style="list-style-type: none"> • 26 nm - 5 nm | <ul style="list-style-type: none"> • Synthesized Ag-NPs citrus pectin at 5.0 kGy and fermented fenugreek powder at 20.0 kGy have potential effect as antioxidant and inhibit cancer cell. | [122] |
| Ag chitosan polyethylene oxide nanocomposites prepared using gamma irradiation at 20 kGy | NA | <ul style="list-style-type: none"> ▪ Ag/Cts and Ag/Cts/PEO nanocomposites have antibacterial activity against gram-negative (<i>Escherichia coli</i>) and gram-positive bacterium (<i>Staphylococcus aureus</i>). | [166] |
| Synthesis of Ag-NPs with low molecular weight chitosan by gamma irradiation at 16 and 40 kGy | <ul style="list-style-type: none"> ▪ Spherical ▪ 5–30 nm | <ul style="list-style-type: none"> ▪ The resulting Ag/Cts NPs inhibited the growth of <i>Methicillin-resistant S. aureus</i> (MRSA) and <i>Aeromonas hydrophila</i> bacteria. | [167] |
| Ag chitosan NPs were prepared by 25 kGy γ -ray irradiation | spherical 7–30 nm | Ag chitosan NPs exhibited inhibitory activity against <i>E. coli</i> and <i>S. aureus</i> . The γ -ray doses of | [168] |
| Colloidal Ag-NPs using chitosan as a stabiliser and free radical scavenger | 7 nm | Colloidal Ag chitosan NPs exhibited highly antimicrobial effect against <i>S. aureus</i> . and <i>Corticium salmonicolor</i> | [169] |

| | | | |
|------------------------------------------------------------------------------------------|---------------------------------------------------------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-------|
| Ag/poly(vinyl alcohol) hydrogels prepared using gamma irradiation at 25 kGy dose. | | Remarkable antibacterial activity Ag/PVA hydrogel against <i>Escherichia coli</i> and <i>S. aureus</i> bacteria. | [172] |
| Ag-NP/gelatin/PVA irradiated at 30, 40, or 50 kGy | <ul style="list-style-type: none"> ▪ 8 nm | Effective inhibition of <i>Staphylococcus aureus</i> , methicillin-resistant <i>S. aureus</i> . The degree of crosslink of the hydrogels increased with the increase in the irradiation dose and decrease with an increase in the amount of AgNO ₃ . | [170] |
| biosynthesis of eco-friendly Ag-NPs using culture supernatant of <i>Enterococcus</i> sp. | <ul style="list-style-type: none"> ▪ Spherical ▪ 10 – 80nm | <ul style="list-style-type: none"> ▪ Excellent enhanced antimicrobial activity than the commercial antibiotics ▪ Ag-NPs have the great potential to inhibit the cell viability of liver cancer cells lines (HepG2) and lung cancer cell lines (A549). | [53] |
| Ag kaolinite matrices synthesized: i. using chemical and γ - irradiation | <ul style="list-style-type: none"> ▪ Spherical ▪ 0.95 – 16 nm | Excelleny microbial properties against the gram-positive strains (<i>S. aureus</i> and <i>E. faecalis</i>) and gram-negative bacterial strains (<i>P. vulgaris</i> and <i>E. coli</i>), and yeast <i>C. Albicans</i> | [161] |
| Synthesis of Ag-NPs/Chitosan by γ - Irradiation from 8 to 28 kGy | <ul style="list-style-type: none"> ▪ 15 to 5 nm | <ul style="list-style-type: none"> ▪ Ag-NPs inhibited the growth of <i>Corynespora cassicola</i> on rubber-leaf extract media | [171] |

FESEM was employed to determine the surface morphology of the developed Ag/KIn NCs. The energies of the emitted x-rays identify the element providing qualitative and quantitative information regarding the elemental ingredient of the NCs. The intensity of silver signal was intensified with the increased AgNO₃ concentration, and the dose of gamma irradiation, suggesting the formation of enhanced growth of Ag-NPs. No obvious peak belong to impurity is detected. The result indicates that the as synthesized Ag-NPs synthesized using gamma irradiation is composed of high purity Ag-NPs (Figure 6).

Conclusion

Chemical synthesis is commonly favoured due to their simplicity and production of enormous quantity of monodispersed NCs possessing controlled size, shapes and morphologies. However, synthesis using gamma irradiation technology is simple, safe and can be manufactured at a larger scale at room condition and under ambient pressure. Gamma synthesis is considered a green technology and environmentally benign without using harsh chemical as reducing agents making it a suitable candidate for medical, drug delivery antimicrobial and fungicidal agents in the future and dental applications. Beside the synthesis method, the concentration of silver and the irradiation dose also affect the size of NPs. It was revealed that as the concentration of silver or the irradiation dose is increased, the size of the NCs increased as well due to an increase in the reduction of Ag⁺ and formation of NPs. The antimicrobial evaluation indicate that the Ag-NPs prepared by gamma irradiation displayed excellent antimicrobial activity compared to those obtained by chemical synthesis. This is evident to conclude that the Ag-NPs prepared by gamma irradiation exhibits pure and strong antibacterial activity which can be used as antimicrobial agent for biomedical and food industrial applications.

Acknowledgement

This research was funded by Takasago Thermal Engineering Co. Ltd. grant (R.K.130000.7343.4B422) from the research management center (RMC) of Universiti Teknologi Malaysia (UTM) and Malaysia Japan International Institute of Technology (MJIIIT).

References

- [1] I. Bibi *et al.*, "Green synthesis of iron oxide nanoparticles using pomegranate seeds extract and photocatalytic activity evaluation for the degradation of textile dye," *J. Mater. Res. Technol.*, vol. 8, no. 6, pp. 6115–6124, 2019, doi: 10.1016/j.jmrt.2019.10.006.
- [2] O. P. Bolade, A. B. Williams, and N. U. Benson, "Environmental Nanotechnology , Monitoring & Management Green synthesis of iron-based nanomaterials for environmental remediation: A review," *Environ. Nanotechnology, Monit. Manag.*, vol. 13, no. December 2019, p. 100279, 2020, doi: 10.1016/j.enmm.2019.100279.
- [3] K. Simeonidis *et al.*, "Optimizing magnetic nanoparticles for drinking water technology: The case of Cr(VI)," 2015, doi: 10.1016/j.scitotenv.2015.04.033.
- [4] Y. Kalachyova, D. Mares, V. Jerabek, R. Elashnikov, V. Švorčík, and O. Lyutakov, "Longtime stability of silver-based SERS substrate in the environment and (bio)environment with variable temperature and humidity," *Sensors Actuators A*, vol. 285, pp. 566–572, 2019, doi: 10.1016/j.sna.2018.11.037.
- [5] P. G. Jamkhande, N. W. Ghule, A. H. Bamer, and M. G. Kalaskar, "Metal nanoparticles synthesis: An overview on methods of preparation, advantages and disadvantages, and applications," *J. Drug Deliv. Sci. Technol.*, vol. 53, no. June, p. 101174, 2019, doi: 10.1016/j.jddst.2019.101174.

- [6] R. Kumar, K. Ram, S. Ranjan, and V. Bhooshan, "Journal of Drug Delivery Science and Technology Advances in nanotechnology and nanomaterials based strategies for neural tissue engineering," *J. Drug Deliv. Sci. Technol.*, vol. 57, no. December 2019, p. 101617, 2020, doi: 10.1016/j.jddst.2020.101617.
- [7] S. Kumar, M. Nehra, D. Kedia, N. Dilbaghi, K. Tankeshwar, and K. H. Kim, "Nanotechnology-based biomaterials for orthopaedic applications: Recent advances and future prospects," *Mater. Sci. Eng. C*, vol. 106, no. September 2019, p. 110154, 2020, doi: 10.1016/j.msec.2019.110154.
- [8] J. Pulit-Prociak and M. Banach, "Silver nanoparticles - A material of the future...?," *Open Chem.*, vol. 14, no. 1, pp. 76–91, 2016, doi: 10.1515/chem-2016-0005.
- [9] G. Kania *et al.*, "Uptake and bioreactivity of charged chitosan-coated superparamagnetic nanoparticles as promising contrast agents for magnetic resonance imaging," *Nanomedicine Nanotechnology, Biol. Med.*, vol. 14, no. 1, pp. 131–140, 2018, doi: 10.1016/j.nano.2017.09.004.
- [10] and J. S. Simranjeet Singh, Vijay Kumar, Romina Romero, Kankan Sharma, "Applications of Nanoparticles in Wastewater Treatment," *Nanobiotechnology Bioformulations, Nanotechnol. Life Sci.*, no. July, p. 395 = 418, 2019, doi: 10.1007/978-3-030-17061-5.
- [11] L. Shi, J. Du, Z. Chen, M. Megharaj, and R. Naidu, "Functional kaolinite supported Fe/Ni nanoparticles for simultaneous catalytic remediation of mixed contaminants (lead and nitrate) from wastewater," *J. Colloid Interface Sci.*, vol. 428, pp. 302–307, 2014, doi: 10.1016/j.jcis.2014.04.059.
- [12] E. C. Ahn, H. S. P. Wong, and E. Pop, "Carbon nanomaterials for non-volatile memories," *Nat. Rev. Mater.*, vol. 3, no. 3, 2018, doi: 10.1038/natrevmats.2018.9.
- [13] S. Kameswara Srikar, D. D. Giri, D. B. Pal, P. K. Mishra, and S. N. Upadhyay, "Green Synthesis of Silver Nanoparticles: A Review," *Green Sustain. Chem.*, vol. 6, no. 6, pp. 34–56, 2016, doi: 10.4236/gsc.2016.61004.
- [14] J. Stergar, I. Ban, and U. Maver, "The Potential Biomedical Application of NiCu Magnetic Nanoparticles," *Magnetochemistry*, vol. 5, no. 4, p. 66, 2019, doi: 10.3390/magnetochemistry5040066.
- [15] P. Sathishkumar, F. L. Gu, Q. Zhan, T. Palvannan, and A. R. Mohd Yusoff, "Flavonoids mediated 'Green' nanomaterials: A novel nanomedicine system to treat various diseases – Current trends and future perspective," *Mater. Lett.*, vol. 210, pp. 26–30, 2018, doi: 10.1016/j.matlet.2017.08.078.
- [16] A. M. Díez-Pascual, M. A. Gómez-Fatou, F. Ania, and A. Flores, "Nanoindentation in polymer nanocomposites," *Prog. Mater. Sci.*, vol. 67, pp. 1–94, 2015, doi: 10.1016/j.pmatsci.2014.06.002.
- [17] B. Perito, E. Giorgetti, P. Marsili, and M. Muniz-Miranda, "Antibacterial activity of silver nanoparticles obtained by pulsed laser ablation in pure water and in chloride solution," *Beilstein J. Nanotechnol.*, vol. 7, no. 1, pp. 465–473, 2016, doi: 10.3762/bjnano.7.40.
- [18] M. Ratti *et al.*, "Irradiation with visible light enhances the antibacterial toxicity of silver nanoparticles produced by laser ablation," *Appl. Phys. A Mater. Sci. Process.*, vol. 122, no. 4, pp. 1–7, 2016, doi: 10.1007/s00339-016-9935-8.
- [19] Y. G. Yuan, Q. L. Peng, and S. Gurunathan, "Effects of silver nanoparticles on multiple drug-resistant strains of Staphylococcus aureus and Pseudomonas aeruginosa from mastitis-infected goats: An alternative approach for antimicrobial therapy," *Int. J. Mol. Sci.*, vol. 18, no. 3, 2017, doi: 10.3390/ijms18030569.
- [20] & R. Abdehgah, I. B., Khodavandi, A., Shamsazar, A., Negahdary, M., Jafarzadeh, M., "in-vitro-antifungal-effects-of-biosynthesized-silver-nanoparticle-by-candida-albicans-against-candida-glabrata." 2017.
- [21] K. J. Kim, W. S. Sung, S. K. Moon, J. S. Choi, J. G. Kim, and D. G. Lee, "Antifungal effect of silver nanoparticles on dermatophytes," *J. Microbiol. Biotechnol.*, vol. 18, no. 8, pp. 1482–1484, 2008.
- [22] A. Ebrahiminezhad, M. Bagheri, S. M. Taghizadeh, A. Berenjjan, and Y. Ghasemi, "Biomimetic synthesis of silver nanoparticles using microalgal secretory carbohydrates as a novel anticancer and antimicrobial," *Adv. Nat. Sci. Nanosci. Nanotechnol.*, vol. 7, no. 1, 2016, doi: 10.1088/2043-6262/7/1/015018.
- [23] X. Zhang, Z. Liu, W. Shen, and S. Gurunathan, "Silver Nanoparticles : Synthesis , Characterization , Properties , Applications , and Therapeutic Approaches," 2016, doi: 10.3390/ijms17091534.

- [24] T. Thi Ngoc Dung *et al.*, “Silver nanoparticles as potential antiviral agents against African swine fever virus,” *Mater. Res. Express*, vol. 6, no. 12, p. 1250g9, Jan. 2020, doi: 10.1088/2053-1591/ab6ad8.
- [25] A. Mukherjee, V. S. Madamsetty, M. K. Paul, and S. Mukherjee, “Recent advancements of nanomedicine towards antiangiogenic therapy in cancer,” *Int. J. Mol. Sci.*, vol. 21, no. 2, 2020, doi: 10.3390/ijms21020455.
- [26] N. K. Hante, C. Medina, and M. J. Santos-Martinez, “Effect on Platelet Function of Metal-Based Nanoparticles Developed for Medical Applications,” *Front. Cardiovasc. Med.*, vol. 6, no. September, 2019, doi: 10.3389/fcvm.2019.00139.
- [27] M. E. Awad, A. López-Galindo, M. Setti, M. M. El-Rahmany, and C. V. Iborra, “Kaolinite in pharmaceuticals and biomedicine,” *Int. J. Pharm.*, vol. 533, no. 1, pp. 34–48, 2017, doi: 10.1016/j.ijpharm.2017.09.056.
- [28] K. N and S. M, “Efficient Removal of Toxic Textile Dyes using Silver Nanocomposites,” *J. Nanosci. Curr. Res.*, vol. 02, no. 03, pp. 2–6, 2018, doi: 10.4172/2572-0813.1000113.
- [29] T. Ngulube, J. R. Gumbo, V. Masindi, and A. Maity, “An update on synthetic dyes adsorption onto clay based minerals: A state-of-art review,” *Journal of Environmental Management*. 2017, doi: 10.1016/j.jenvman.2016.12.031.
- [30] P. Laux *et al.*, “Nanomaterials: certain aspects of application, risk assessment and risk communication,” *Arch. Toxicol.*, vol. 92, no. 1, pp. 121–141, 2018, doi: 10.1007/s00204-017-2144-1.
- [31] Khan, Rehman, Hayat, and Andreescu, “Magnetic Particles-Based Analytical Platforms for Food Safety Monitoring,” *Magnetochemistry*, vol. 5, no. 4, p. 63, 2019, doi: 10.3390/magnetochemistry5040063.
- [32] G. Gaiani, C. K. O’Sullivan, and M. Campàs, “Magnetic Beads in Marine Toxin Detection: A Review,” *Magnetochemistry*, vol. 5, no. 4, p. 62, 2019, doi: 10.3390/magnetochemistry5040062.
- [33] J. Isaad and A. El Achari, “Synthesis and spectroscopic characterization of azoic dyes based on pyrazolone derivatives catalyzed by an acidic ionic liquid supported on silica-coated magnetite nanoparticle,” *J. Mol. Struct.*, vol. 1154, pp. 557–564, 2018, doi: 10.1016/j.molstruc.2017.10.091.
- [34] M. Ismail *et al.*, “Pollution, Toxicity and Carcinogenicity of Organic Dyes and their Catalytic Bio-Remediation,” *Curr. Pharm. Des.*, vol. 25, no. 34, pp. 3645–3663, 2019, doi: 10.2174/1381612825666191021142026.
- [35] Y. Jiang and J. Wu, “Recent development in chitosan nanocomposites for surface-based biosensor applications,” *Electrophoresis*, vol. 40, no. 16, pp. 2084–2097, 2019, doi: 10.1002/elps.201900066.
- [36] S. C. Dey, M. Al-amin, and T. U. Rashid, “pH Induced Fabrication of Kaolinite-Chitosan Biocomposite pH Induced Fabrication of Kaolinite-Chitosan Biocomposite Shaikat Chandra Dey a , Mohammad Al-Amin b , Taslim Ur Rashid c ,” no. July, 2016, doi: 10.18052/www.scipress.com/ILCPA.68.1.
- [37] B. P. L. Angel *et al.*, “Biochemistry & Pharmacology : Open Access The Chemistry of Chitin and Chitosan Justifying their Nanomedical Utilities,” vol. 7, no. 1, pp. 1–6, 2018, doi: 10.4172/2167-0501.1000241.
- [38] L. Y. Ozer *et al.*, “Water microbial disinfection via supported nAg/Kaolin in a fixed-bed reactor configuration,” *Appl. Clay Sci.*, vol. 184, no. August 2019, 2020, doi: 10.1016/j.clay.2019.105387.
- [39] M. S. Mauter, I. Zucker, F. Perreault, J. R. Werber, J. H. Kim, and M. Elimelech, “The role of nanotechnology in tackling global water challenges,” *Nat. Sustain.*, vol. 1, no. 4, pp. 166–175, 2018, doi: 10.1038/s41893-018-0046-8.
- [40] A. H. Jabbar, M. Q. Hamzah, S. O. Mezan, A. S. Binti Ameruddin, and M. A. Agam, “Green Synthesis of Silver/ Polystyrene Nano composite (Ag/PS NCs) Via Plant Extracts Beginning a New Era in Drug Delivery,” *Indian J. Sci. Technol.*, vol. 11, no. 22, pp. 1–9, 2018, doi: 10.17485/ijst/2018/v11i22/121154.
- [41] S. P. Deshmukh, S. M. Patil, S. B. Mullani, and S. D. Delekar, “Silver nanoparticles as an effective disinfectant : A review,” vol. 97, no. July 2018, pp. 954–965, 2019, doi: 10.1016/j.msec.2018.12.102.
- [42] W. Huang *et al.*, “Synergistic antifungal effect of biosynthesized silver nanoparticles combined with fungicides,” *Int. J. Agric. Biol.*, vol. 20, no. 5, pp. 1225–1229, 2018, doi: 10.17957/IJAB/15.0595.
- [43] A. C. Burdușel, O. Gherasim, A. M. Grumezescu, L. Mogoantă, A. Ficai, and E. Andronescu, “Biomedical

- applications of silver nanoparticles: An up-to-date overview,” *Nanomaterials*, vol. 8, no. 9, pp. 1–25, 2018, doi: 10.3390/nano8090681.
- [44] K. Midha, G. Singh, M. Nagpal, and S. Arora, “Potential Application of Silver Nanoparticles in Medicine,” *Nanosci. Nanotechnology-Asia*, vol. 6, no. 2, pp. 82–91, 2016, doi: 10.2174/2210681205666150818230319.
- [45] G. Nam, S. Rangasamy, B. Purushothaman, and J. M. Song, “The application of bactericidal silver nanoparticles in wound treatment,” *Nanomater. Nanotechnol.*, vol. 5, no. 1, 2015, doi: 10.5772/60918.
- [46] C. Gao *et al.*, “Antibacterial activity and osseointegration of silver-coated poly(ether ether ketone) prepared using the polydopamine-assisted deposition technique,” *J. Mater. Chem. B*, vol. 5, no. 47, pp. 9326–9336, 2017, doi: 10.1039/c7tb02436c.
- [47] E. Ertem *et al.*, “Core-Shell Silver Nanoparticles in Endodontic Disinfection Solutions Enable Long-Term Antimicrobial Effect on Oral Biofilms,” *ACS Appl. Mater. Interfaces*, vol. 9, no. 40, pp. 34762–34772, 2017, doi: 10.1021/acsami.7b13929.
- [48] B. Le Ouay and F. Stellacci, “Antibacterial activity of silver nanoparticles: A surface science insight,” *Nano Today*, vol. 10, no. 3, pp. 339–354, 2015, doi: 10.1016/j.nantod.2015.04.002.
- [49] L. Mei *et al.*, “Silver Nanocluster-Embedded Zein Films as Antimicrobial Coating Materials for Food Packaging,” *ACS Appl. Mater. Interfaces*, vol. 9, no. 40, pp. 35297–35304, 2017, doi: 10.1021/acsami.7b08152.
- [50] B. Journal, D. Hotza, and J. B. R. Neto, “BACTERICIDAL EFFECTIVENESS OF FREEZE-CAST CERAMIC FILTERS IMPREGNATED WITH SILVER NANOPARTICLES,” vol. 35, no. 04, pp. 1267–1274, 2018.
- [51] L. P. Kojom Foko *et al.*, “A systematic review on anti-malarial drug discovery and antiplasmodial potential of green synthesis mediated metal nanoparticles: Overview, challenges and future perspectives,” *Malar. J.*, vol. 18, no. 1, pp. 1–14, 2019, doi: 10.1186/s12936-019-2974-9.
- [52] Y.-L. Lin, J.-C. Wei, J.-J. Lin, S. -h. Hsu, Y.-L. Lee, and J.-J. Liang, “Surfactant-Modified Nanoclay Exhibits an Antiviral Activity with High Potency and Broad Spectrum,” *J. Virol.*, vol. 88, no. 8, pp. 4218–4228, 2014, doi: 10.1128/jvi.03256-13.
- [53] S. Rajeshkumar, C. Malarkodi, M. Vanaja, and G. Annadurai, “Anticancer and enhanced antimicrobial activity of biosynthesized silver nanoparticles against clinical pathogens,” *J. Mol. Struct.*, vol. 1116, pp. 165–173, Jul. 2016, doi: 10.1016/j.molstruc.2016.03.044.
- [54] M. Khatami, I. Sharifi, M. A. L. Nobre, N. Zafarnia, and M. R. Aflatoonian, “Waste-grass-mediated green synthesis of silver nanoparticles and evaluation of their anticancer, antifungal and antibacterial activity,” *Green Chem. Lett. Rev.*, vol. 11, no. 2, pp. 125–134, 2018, doi: 10.1080/17518253.2018.1444797.
- [55] A. Hussain *et al.*, “Biosynthesized silver nanoparticle (AgNP) from pandanus odorifer leaf extract exhibits anti-metastasis and anti-biofilm potentials,” *Front. Microbiol.*, vol. 10, no. FEB, pp. 1–19, 2019, doi: 10.3389/fmicb.2019.00008.
- [56] S. S. Rec, “Synthesis of silver and gold nanoparticles using Jasminum nervosum leaf extract and its larvicidal activity against filarial and arboviral vector Culex quinquefasciatus Say (Dipter ... Synthesis of silver and gold nanoparticles using Jasminum nervosum le,” no. November, 2015, doi: 10.1007/s11356-015-5001-x.
- [57] W. Huang, M. Yan, H. Duan, Y. Bi, X. Cheng, and H. Yu, “Synergistic Antifungal Activity of Green Synthesized Silver Nanoparticles and Epoxiconazole against Setosphaeria turcica,” vol. 2020, 2020.
- [58] W. Lin, Y. Fang, and L. Xue, “Forest Biomass Allocation vary with Temperature in Five Forest Types of China,” no. May, pp. 1043–1048, 2019, doi: 10.17957/IJAB/15.0.
- [59] W. Lin, Y. Fang, and L. Xue, “Antifungal Effect of Buxus sinica Leaf Extract-mediated Silver Nanoparticles against Curvularia lunata,” no. July, pp. 1043–1048, 2019, doi: 10.17957/IJAB/15.0.
- [60] S. O. Hasson, M. J. Al-Awady, A. H. Al-Hamadani, and I. H. Al-Azawi, “Boosting Antimicrobial Activity of Imipenem in Combination with Silver Nanoparticles towards S. fonticola and Pantoea sp.,” *Nano*

- Biomed. Eng.*, vol. 11, no. 2, 2019, doi: 10.5101/nbe.v11i2.p200-214.
- [61] G. Franci *et al.*, “Silver nanoparticles as potential antibacterial agents,” *Molecules*, vol. 20, no. 5, pp. 8856–8874, 2015, doi: 10.3390/molecules20058856.
- [62] M. Saravanan, S. Arokiyaraj, T. Lakshmi, and A. Pugazhendhi, “Synthesis of silver nanoparticles from *Phenerochaete chrysosporium* (MTCC-787) and their antibacterial activity against human pathogenic bacteria,” *Microb. Pathog.*, vol. 117, no. February, pp. 68–72, 2018, doi: 10.1016/j.micpath.2018.02.008.
- [63] S. Das *et al.*, “Disinfection of the water borne pathogens *Escherichia coli* and *Staphylococcus aureus* by solar photocatalysis using sonochemically synthesized reusable Ag@ZnO core-shell nanoparticles,” *Int. J. Environ. Res. Public Health*, vol. 14, no. 7, 2017, doi: 10.3390/ijerph14070747.
- [64] S. Wanjale *et al.*, “Surface tailored PS/TiO₂ composite nanofiber membrane for copper removal from water,” *J. Colloid Interface Sci.*, 2016, doi: 10.1016/j.jcis.2016.01.054.
- [65] S. P. Deshmukh, S. M. Patil, S. B. Mullani, and S. D. Delekar, “Materials Science & Engineering C Silver nanoparticles as an effective disinfectant: A review,” vol. 97, no. July 2018, pp. 954–965, 2019, doi: 10.1016/j.msec.2018.12.102.
- [66] A. Barkat, S. Beg, F. H. Pottoo, and A. Garg, “Silver Nanoparticles and their Antimicrobial Applications,” pp. 1–10, 2018, doi: 10.2174/2405461503666180806113924.
- [67] L. C. S. Belusso *et al.*, “Applied Surface Science Synthesis of silver nanoparticles from bottom up approach on borophosphate glass and their applications as SERS, antibacterial and glass-based catalyst,” *Appl. Surf. Sci.*, vol. 473, no. November 2018, pp. 303–312, 2019, doi: 10.1016/j.apsusc.2018.12.155.
- [68] M. Abbas, N. Naeem, H. Iftikhar, and U. Latif, “Synthesis, Characterization and Antimicrobial Properties of Silver Nanocomposites,” *Silver Nanoparticles - Fabr. Charact. Appl.*, 2018, doi: 10.5772/intechopen.74623.
- [69] S. Temizel-Sekeryan and A. L. Hicks, “Global environmental impacts of silver nanoparticle production methods supported by life cycle assessment,” *Resour. Conserv. Recycl.*, vol. 156, no. January, p. 104676, 2020, doi: 10.1016/j.resconrec.2019.104676.
- [70] J. Jeevanandam, A. Barhoum, Y. S. Chan, A. Dufresne, and M. K. Danquah, “Review on nanoparticles and nanostructured materials: History, sources, toxicity and regulations,” *Beilstein J. Nanotechnol.*, vol. 9, no. 1, pp. 1050–1074, 2018, doi: 10.3762/bjnano.9.98.
- [71] B. Calderón-Jiménez, M. E. Johnson, A. R. Montoro Bustos, K. E. Murphy, M. R. Winchester, and J. R. V. Baudrit, “Silver nanoparticles: Technological advances, societal impacts, and metrological challenges,” *Front. Chem.*, vol. 5, no. Feb, pp. 1–26, 2017, doi: 10.3389/fchem.2017.00006.
- [72] A. Bal, F. E. Çepni, Çakir, I. Acar, and G. Güçlü, “Synthesis and characterization of copolymeric and terpolymeric hydrogel-silver nanocomposites based on acrylic acid, acrylamide and itaconic acid: Investigation of their antibacterial activity against gram-negative bacteria,” *Brazilian J. Chem. Eng.*, vol. 32, no. 2, pp. 509–518, 2015, doi: 10.1590/0104-6632.20150322s00003066.
- [73] F. Dong, E. Valsami-Jones, and J. U. Kreft, “New, rapid method to measure dissolved silver concentration in silver nanoparticle suspensions by aggregation combined with centrifugation,” *J. Nanoparticle Res.*, vol. 18, no. 9, pp. 1–12, 2016, doi: 10.1007/s11051-016-3565-0.
- [74] A. Mackevica, M. E. Olsson, and S. F. Hansen, “Silver nanoparticle release from commercially available plastic food containers into food simulants,” *J. Nanoparticle Res.*, vol. 18, no. 1, pp. 1–11, 2016, doi: 10.1007/s11051-015-3313-x.
- [75] B. Ganguly, “Short Review on Green Silver Nanoparticles and its Bioactivities,” *Mater. Sci. Res. India*, vol. 16, no. 3, pp. 225–229, 2019, doi: 10.13005/msri/160304.
- [76] X. Y. Dong, Z. W. Gao, K. F. Yang, W. Q. Zhang, and L. W. Xu, “Nanosilver as a new generation of silver catalysts in organic transformations for efficient synthesis of fine chemicals,” *Catal. Sci. Technol.*, vol. 5, no. 5, pp. 2554–2574, 2015, doi: 10.1039/c5cy00285k.
- [77] G. Liao, W. Zhao, Q. Li, Q. Pang, and Z. Xu, “Novel poly (acrylic acid)-modified tourmaline/silver composites for adsorption removal of Cu(II) ions and catalytic reduction of methylene blue in water,”

- Chem. Lett.*, vol. 46, no. 11, pp. 1631–1634, 2017, doi: 10.1246/cl.170785.
- [78] N. Arora, A. Mehta, A. Mishra, and S. Basu, “4-Nitrophenol reduction catalysed by Au-Ag bimetallic nanoparticles supported on LDH: Homogeneous vs. heterogeneous catalysis,” *Appl. Clay Sci.*, vol. 151, no. June 2017, pp. 1–9, 2018, doi: 10.1016/j.clay.2017.10.015.
- [79] M. Gondwal and G. Joshi Nee Pant, “Synthesis and Catalytic and Biological Activities of Silver and Copper Nanoparticles Using *Cassia occidentalis*,” *Int. J. Biomater.*, vol. 2018, 2018, doi: 10.1155/2018/6735426.
- [80] P. SAGITHA, K. SARADA, and K. MURALEEDHARAN, “One-pot synthesis of poly vinyl alcohol (PVA) supported silver nanoparticles and its efficiency in catalytic reduction of methylene blue,” *Trans. Nonferrous Met. Soc. China (English Ed.)*, vol. 26, no. 10, pp. 2693–2700, 2016, doi: 10.1016/S1003-6326(16)64397-2.
- [81] K. Jyoti and A. Singh, “Green synthesis of nanostructured silver particles and their catalytic application in dye degradation,” *J. Genet. Eng. Biotechnol.*, vol. 14, no. 2, pp. 311–317, 2016, doi: 10.1016/j.jgeb.2016.09.005.
- [82] M. A. Mudassir *et al.*, “Development of Silver-Nanoparticle-Decorated Emulsion-Templated Hierarchically Porous Poly(1-vinylimidazole) Beads for Water Treatment,” *ACS Appl. Mater. Interfaces*, vol. 9, no. 28, pp. 24190–24197, 2017, doi: 10.1021/acsami.7b05311.
- [83] N. Khatri, S. Tyagi, and D. Rawtani, “Removal of basic dyes auramine yellow and auramine O by halloysite nanotubes,” *Int. J. Environ. Waste Manag.*, vol. 17, no. 1, pp. 44–59, 2016, doi: 10.1504/IJEW.2016.076427.
- [84] B. Szczepanik, “Photocatalytic degradation of organic contaminants over clay-TiO₂ nanocomposites: A review,” *Appl. Clay Sci.*, vol. 141, pp. 227–239, 2017, doi: 10.1016/j.clay.2017.02.029.
- [85] M. Bin Ahmad, K. Shameli, W. Md Zin Wan Yunus, N. Azowa Ibrahim, and M. Darroudi, “Synthesis and Characterization of Silver/Clay/Starch Bionanocomposites by Green Method,” *Aust. J. Basic Appl. Sci.*, vol. 4, no. 7, pp. 2158–2165, 2010.
- [86] Q. Yuan and T. D. Golden, “A novel method for synthesis of clay/polymer stabilized silver nanoparticles,” *Surfaces and Interfaces*, vol. 20, no. March, p. 100620, 2020, doi: 10.1016/j.surfin.2020.100620.
- [87] S. Kumar-Krishnan *et al.*, “Chitosan/silver nanocomposites: Synergistic antibacterial action of silver nanoparticles and silver ions,” *Eur. Polym. J.*, 2015, doi: 10.1016/j.eurpolymj.2015.03.066.
- [88] N. Wang, Y. Hu, and Z. Zhang, “Sustainable catalytic properties of silver nanoparticles supported montmorillonite for highly efficient recyclable reduction of methylene blue,” *Appl. Clay Sci.*, vol. 150, no. September, pp. 47–55, 2017, doi: 10.1016/j.clay.2017.08.024.
- [89] K. Bijalwan, A. Kainthola, H. Sharma, and C. Dwivedi, “Materials Today : Proceedings Catalytic reduction of 4-nitrophenol using gold-silver alloy nanoparticles coated on alkali activated sand,” *Mater. Today Proc.*, no. xxxx, pp. 2–5, 2020, doi: 10.1016/j.matpr.2020.01.089.
- [90] A. Jamshaid *et al.*, “Cellulose-based Materials for the Removal of Heavy Metals from Wastewater - An Overview,” *ChemBioEng Rev.*, vol. 4, no. 4, pp. 240–256, 2017, doi: 10.1002/cben.201700002.
- [91] A. M. Ferreira, É. B. Roque, F. V. da Fonseca, and C. P. Borges, “High flux microfiltration membranes with silver nanoparticles for water disinfection,” *Desalin. Water Treat.*, vol. 56, no. 13, pp. 3590–3598, 2015, doi: 10.1080/19443994.2014.1000977.
- [92] N. M. Alandis, W. Mekhamer, O. Aldayel, J. A. A. Hefne, and M. Alam, “Adsorptive Applications of Montmorillonite Clay for the Removal of Ag(I) and Cu(II) from Aqueous Medium,” *J. Chem.*, vol. 2019, 2019, doi: 10.1155/2019/7129014.
- [93] S. P. C. Gonçalves, M. Strauss, F. S. Delite, Z. Clemente, V. L. Castro, and D. S. T. Martinez, “Activated carbon from pyrolysed sugarcane bagasse: Silver nanoparticle modification and ecotoxicity assessment,” *Sci. Total Environ.*, vol. 565, pp. 833–840, 2015, doi: 10.1016/j.scitotenv.2016.03.041.
- [94] C. Li, Z. Sun, A. Song, X. Dong, S. Zheng, and D. D. Dionysiou, “Flowing nitrogen atmosphere induced rich oxygen vacancies overspread the surface of TiO₂/kaolinite composite for enhanced photocatalytic activity within broad radiation spectrum,” *Appl. Catal. B Environ.*, vol. 236, pp. 76–87, 2018, doi:

- 10.1016/j.apcatb.2018.04.083.
- [95] C. Li, Z. Sun, W. Zhang, C. Yu, and S. Zheng, “Highly efficient g-C₃N₄/TiO₂/kaolinite composite with novel three-dimensional structure and enhanced visible light responding ability towards ciprofloxacin and *S. aureus*,” *Appl. Catal. B Environ.*, vol. 220, pp. 272–282, 2018, doi: 10.1016/j.apcatb.2017.08.044.
- [96] A. Mishra, A. Mehta, M. Sharma, and S. Basu, “Enhanced heterogeneous photodegradation of VOC and dye using microwave synthesized TiO₂/Clay nanocomposites: A comparison study of different type of clays,” *J. Alloys Compd.*, vol. 694, pp. 574–580, 2017, doi: 10.1016/j.jallcom.2016.10.036.
- [97] Z. Cao, Q. Wang, and H. Cheng, “Recent advances in kaolinite-based material for photocatalysts,” *Chinese Chem. Lett.*, 2021, doi: 10.1016/j.ccllet.2021.01.009.
- [98] R. R. Palem, N. Saha, G. D. Shimoga, and Z. Kronekova, “Chitosan-Silver Nanocomposites: New Functional Biomaterial for Healthcare Applications,” pp. 1–36.
- [99] U. Latif, K. Al-Rubeaan, and A. T. M. Saeb, “A Review on Antimicrobial Chitosan-Silver Nanocomposites: A Roadmap Toward Pathogen Targeted Synthesis,” *Int. J. Polym. Mater. Polym. Biomater.*, vol. 64, no. 9, pp. 448–458, 2015, doi: 10.1080/00914037.2014.958834.
- [100] S. Lima *et al.*, “Chitosan-based silver nanoparticles : A study of the antibacterial , antileishmanial and cytotoxic effects,” 2016, doi: 10.1177/0883911516681329.
- [101] M. Rahimi *et al.*, “Carbohydrate polymer-based silver nanocomposites: Recent progress in the antimicrobial wound dressings,” *Carbohydr. Polym.*, vol. 231, no. September 2019, 2020, doi: 10.1016/j.carbpol.2019.115696.
- [102] Q. B. Xu *et al.*, “Antibacterial cotton fabric with enhanced durability prepared using silver nanoparticles and carboxymethyl chitosan,” *Carbohydr. Polym.*, vol. 177, no. September, pp. 187–193, 2017, doi: 10.1016/j.carbpol.2017.08.129.
- [103] J. Natsuki, T. Natsuki, and Y. Hashimoto, “A Review of Silver Nanoparticles: Synthesis Methods, Properties and Applications,” *Int. J. Mater. Sci. Appl.*, vol. 4, no. 5, p. 325, 2015, doi: 10.11648/j.ijmsa.20150405.17.
- [104] R. A. Ismail, G. M. Sulaiman, M. H. Mohsin, and A. H. Saadon, “Preparation of silver iodide nanoparticles using laser ablation in liquid for antibacterial applications,” *IET Nanobiotechnology*, vol. 12, no. 6, pp. 781–786, 2018, doi: 10.1049/iet-nbt.2017.0231.
- [105] R. M. Kumar, B. L. Rao, S. Asha, B. Narayana, K. Byrappa, and Y. Wang, “Gamma radiation assisted biosynthesis of silver nanoparticles and their characterization,” no. January, 2015, doi: 10.5185/amlett.2015.6002.
- [106] M. Scuderi *et al.*, “Nanoscale Study of the Tarnishing Process in Electron Beam Lithography-Fabricated Silver Nanoparticles for Plasmonic Applications,” *J. Phys. Chem. C*, vol. 120, no. 42, pp. 24314–24323, 2016, doi: 10.1021/acs.jpcc.6b03963.
- [107] R. D. Rivera-Rangel, M. P. González-Muñoz, M. Avila-Rodriguez, T. A. Razo-Lazcano, and C. Solans, “Green synthesis of silver nanoparticles in oil-in-water microemulsion and nano-emulsion using geranium leaf aqueous extract as a reducing agent,” *Colloids Surfaces A Physicochem. Eng. Asp.*, vol. 536, no. July 2017, pp. 60–67, 2018, doi: 10.1016/j.colsurfa.2017.07.051.
- [108] M. Parveen, F. Ahmad, A. M. Malla, and S. Azaz, “Microwave-assisted green synthesis of silver nanoparticles from *Fraxinus excelsior* leaf extract and its antioxidant assay,” *Appl. Nanosci.*, vol. 6, no. 2, pp. 267–276, 2016, doi: 10.1007/s13204-015-0433-7.
- [109] E. M. Halawani, “Rapid Biosynthesis Method and Characterization of Silver Nanoparticles Using <i>Zizyphus spina christi</i> Leaf Extract and Their Antibacterial Efficacy in Therapeutic Application,” *J. Biomater. Nanobiotechnol.*, vol. 08, no. 01, pp. 22–35, 2017, doi: 10.4236/jbnb.2017.81002.
- [110] M. Ndikau, N. M. Noah, D. M. Andala, and E. Masika, “Green Synthesis and Characterization of Silver Nanoparticles Using *Citrullus lanatus* Fruit Rind Extract ,” *Int. J. Anal. Chem.*, vol. 2017, pp. 1–9, 2017, doi: 10.1155/2017/8108504.

- [111] J. K. Patra and K. H. Baek, "Green Nanobiotechnology: Factors Affecting Synthesis and Characterization Techniques," *J. Nanomater.*, vol. 2014, 2014, doi: 10.1155/2014/417305.
- [112] A. R. Allafchian, S. Z. Mirahmadi-Zare, S. A. H. Jalali, S. S. Hashemi, and M. R. Vahabi, "Green synthesis of silver nanoparticles using phlomis leaf extract and investigation of their antibacterial activity," *J. Nanostructure Chem.*, vol. 6, no. 2, pp. 129–135, 2016, doi: 10.1007/s40097-016-0187-0.
- [113] S. Irvani, H. Korbekandi, and B. Zolfaghari, "Synthesis of silver nanoparticles : chemical , physical and biological methods Synthesis of silver NPs," vol. 9, no. 6, pp. 1–17, 2016, doi: 10.1111/j.1551-2916.2006.01044.x.
- [114] A. Islam, M. V Jacob, and E. Antunes, "A critical review on silver nanoparticles : From synthesis and applications to its mitigation through low-cost adsorption by biochar," *J. Environ. Manage.*, vol. 281, no. July 2020, p. 111918, 2021, doi: 10.1016/j.jenvman.2020.111918.
- [115] V. R. Remya, V. K. Abitha, P. Singh Rajput, A. Vasudeo Rane, and A. Dutta, "Silver nanoparticles green synthesis: A mini review," *Chem. Int. Chem. Int. Chem. Int.*, vol. 3, no. 32, pp. 165–171, 2017, [Online]. Available: www.bosaljournals/chemint/.
- [116] B. D. Altinsoy, G. Şeker Karatoprak, and I. Ocoy, "Extracellular directed ag NPs formation and investigation of their antimicrobial and cytotoxic properties," *Saudi Pharm. J.*, vol. 27, no. 1, pp. 9–16, 2019, doi: 10.1016/j.jsps.2018.07.013.
- [117] A. P. Reverberi, M. Vocciante, E. Lunghi, L. Pietrelli, and B. Fabiano, "New trends in the synthesis of nanoparticles by green methods," *Chem. Eng. Trans.*, vol. 61, no. October, pp. 667–672, 2017, doi: 10.3303/CET1761109.
- [118] S. M. Landage, "SYNTHESIS OF NANOSILVER USING CHEMICAL REDUCTION METHODS," *Int. J. Adv. Res. Eng. Appl. Sci.*, vol. 3, no. 5, pp. 14–22, 2014.
- [119] S. Zhang, Y. Tang, and B. Vlahovic, "A Review on Preparation and Applications of Silver-Containing Nanofibers," *Nanoscale Res. Lett.*, vol. 11, no. 1, pp. 1–8, 2016, doi: 10.1186/s11671-016-1286-z.
- [120] K. Jyoti, M. Baunthiyal, and A. Singh, "Characterization of silver nanoparticles synthesized using *Urtica dioica* Linn. leaves and their synergistic effects with antibiotics," *J. Radiat. Res. Appl. Sci.*, vol. 9, no. 3, pp. 217–227, 2016, doi: 10.1016/j.jrras.2015.10.002.
- [121] D. M. Clifford, C. E. Castano, and J. V. Rojas, "Supported transition metal nanomaterials: Nanocomposites synthesized by ionizing radiation," *Radiat. Phys. Chem.*, vol. 132, no. October 2016, pp. 52–64, 2017, doi: 10.1016/j.radphyschem.2016.12.001.
- [122] M. Ghorab, A. El-Batal, A. Hanora, and F. Mosalam, "Incorporation of Silver Nanoparticles with Natural Polymers Using Biotechnological and Gamma Irradiation Processes," *Br. Biotechnol. J.*, vol. 16, no. 1, pp. 1–25, 2016, doi: 10.9734/bbj/2016/25642.
- [123] M. M. Ghobashy, A. Awad, M. A. Elhady, and A. M. Elbarbary, "Silver rubber-hydrogel nanocomposite as pH-sensitive prepared by gamma radiation : Part I," *Cogent Chem.*, vol. 17, no. 1, pp. 1–12, 2017, doi: 10.1080/23312009.2017.1328770.
- [124] A. M. Elbarbary and M. M. Ghobashy, "Controlled release fertilizers using superabsorbent hydrogel prepared by gamma radiation," *Radiochim. Acta*, vol. 105, no. 10, pp. 865–876, 2017, doi: 10.1515/ract-2016-2679.
- [125] N. Misra, J. Biswal, V. P. Dhamgaye, G. S. Lodha, and S. Sabharwal, "A comparative study of gamma, electron beam, and synchrotron X-ray irradiation method for synthesis of silver nanoparticles in PVP," *Adv. Mater. Lett.*, vol. 4, no. 6, pp. 458–463, 2013, doi: 10.5185/amlett.2012.ib.114.
- [126] A. Abedini, A. A. A. Bakar, F. Larki, P. S. Menon, M. S. Islam, and S. Shaari, "Recent Advances in Shape-Controlled Synthesis of Noble Metal Nanoparticles by Radiolysis Route," *Nanoscale Res. Lett.*, vol. 11, no. 1, 2016, doi: 10.1186/s11671-016-1500-z.
- [127] J. V. Garcia-Ramos, S. Sanchez-Cortes, A. Torreggiani, M. Tamba, Z. Jurasekova, and M. D'Angelantonio, "Fabrication of Ag nanoparticles by γ -irradiation: Application to surface-enhanced Raman spectroscopy of fungicides," *Colloids Surfaces A Physicochem. Eng. Asp.*, vol. 339, no. 1–3, pp.

- 60–67, 2009, doi: 10.1016/j.colsurfa.2009.01.018.
- [128] A. Bera *et al.*, “Gamma radiation synthesis of colloidal AgNPs for its potential application in antimicrobial fabrics,” *Radiat. Phys. Chem.*, vol. 115, pp. 62–67, 2015, doi: 10.1016/j.radphyschem.2015.05.041.
- [129] K. Hareesh, R. P. Joshi, S. S. Dahiwal, V. N. Bhoraskar, and S. D. Dhole, “Synthesis of Ag-reduced graphene oxide nanocomposite by gamma radiation assisted method and its photocatalytic activity,” *Vacuum*, vol. 124, no. December, pp. 40–45, 2016, doi: 10.1016/j.vacuum.2015.11.011.
- [130] G. G. Flores-Rojas, F. López-Saucedo, and E. Bucio, “Gamma-irradiation applied in the synthesis of metallic and organic nanoparticles: A short review,” *Radiat. Phys. Chem.*, vol. 169, no. December 2017, p. 107962, 2020, doi: 10.1016/j.radphyschem.2018.08.011.
- [131] S. M. Ghoreishian *et al.*, “ γ -Radiolysis as a highly efficient green approach to the synthesis of metal nanoclusters: A review of mechanisms and applications,” *Chem. Eng. J.*, vol. 360, no. October 2018, pp. 1390–1406, 2019, doi: 10.1016/j.cej.2018.10.164.
- [132] C. Auría-Soro *et al.*, “Interactions of nanoparticles and biosystems: Microenvironment of nanoparticles and biomolecules in nanomedicine,” *Nanomaterials*, vol. 9, no. 10, 2019, doi: 10.3390/nano9101365.
- [133] X. F. Zhang, W. Shen, and S. Gurunathan, “Silver nanoparticle-mediated cellular responses in various cell lines: An in vitro model,” *Int. J. Mol. Sci.*, vol. 17, no. 10, pp. 1–26, 2016, doi: 10.3390/ijms17101603.
- [134] R. A. Hamouda, W. E. Yousuf, E. E. Abdeen, and A. Mohamed, “Biological and Chemical Synthesis of Silver Nanoparticles : Characterization , MIC and Antibacterial Activity against Pathogenic Bacteria,” vol. 11, no. 7, pp. 1–12, 2019.
- [135] C. R. R. Balakarthekeyan, “Photocatalytic Degradation of Methylene Blue Dye Using Synthesized Silver Nanoparticles,” pp. 14–19, 2019.
- [136] J. Y. Cheon, S. J. Kim, and W. H. Park, “Facile interpretation of catalytic reaction between organic dye pollutants and silver nanoparticles with different shapes,” *J. Nanomater.*, vol. 2019, 2019, doi: 10.1155/2019/3257892.
- [137] C. M. Ramakritinan *et al.*, “Synthesis of chitosan mediated silver nanoparticles (Ag NPs) for potential antimicrobial applications,” *Front. Lab. Med.*, vol. 2, no. 1, pp. 30–35, 2018, doi: 10.1016/j.flm.2018.04.002.
- [138] S. Zaidi, L. Misba, and A. U. Khan, “Nano-therapeutics: A revolution in infection control in post antibiotic era,” *Nanomedicine Nanotechnology, Biol. Med.*, vol. 13, no. 7, pp. 2281–2301, 2017, doi: 10.1016/j.nano.2017.06.015.
- [139] A. Roy, O. Bulut, S. Some, A. K. Mandal, and M. D. Yilmaz, “Green synthesis of silver nanoparticles: Biomolecule-nanoparticle organizations targeting antimicrobial activity,” *RSC Adv.*, vol. 9, no. 5, pp. 2673–2702, 2019, doi: 10.1039/c8ra08982e.
- [140] C. G. Anjali Das *et al.*, “Antibacterial activity of silver nanoparticles (biosynthesis): A short review on recent advances,” *Biocatal. Agric. Biotechnol.*, p. 101593, 2020, doi: 10.1016/j.bcab.2020.101593.
- [141] L. Wei, J. Lu, H. Xu, A. Patel, Z. S. Chen, and G. Chen, “Silver nanoparticles: Synthesis, properties, and therapeutic applications,” *Drug Discov. Today*, vol. 20, no. 5, pp. 595–601, 2015, doi: 10.1016/j.drudis.2014.11.014.
- [142] S. K. Kailasa, T. J. Park, J. V. Rohit, and J. R. Koduru, *Antimicrobial activity of silver nanoparticles*. Elsevier Inc., 2019.
- [143] S. Sengupta and R. Sasisekharan, “Exploiting nanotechnology to target cancer,” *Br. J. Cancer*, vol. 96, no. 9, pp. 1315–1319, 2007, doi: 10.1038/sj.bjc.6603707.
- [144] S. H. Lee and B. H. Jun, “Silver nanoparticles: Synthesis and application for nanomedicine,” *Int. J. Mol. Sci.*, vol. 20, no. 4, 2019, doi: 10.3390/ijms20040865.
- [145] S. H. Lee and B. H. Jun, “Silver nanoparticles: Synthesis and application for nanomedicine,” *Int. J. Mol. Sci.*, vol. 20, no. 4, pp. 1–23, 2019, doi: 10.3390/ijms20040865.
- [146] K. Zheng, M. I. Setyawati, D. T. Leong, and J. Xie, “Antimicrobial silver nanomaterials,” *Coord. Chem.*

- Rev., vol. 357, pp. 1–17, 2018, doi: 10.1016/j.ccr.2017.11.019.
- [147] I. Zorraquín-Peña, C. Cueva, B. Bartolomé, and M. V. Moreno-Arribas, “Silver nanoparticles against foodborne bacteria. Effects at intestinal level and health limitations,” *Microorganisms*, vol. 8, no. 1, 2020, doi: 10.3390/microorganisms8010132.
- [148] Y. Y. Zhang, Q. B. Xu, F. Y. Fu, and X. D. Liu, “Durable antimicrobial cotton textiles modified with inorganic nanoparticles,” *Cellulose*, vol. 23, no. 5, pp. 2791–2808, 2016, doi: 10.1007/s10570-016-1012-0.
- [149] K. Anna, M. Speruda, and E. Krzy, “Similarities and Differences between Silver Ions and Silver in Nanoforms as Antibacterial Agents,” doi: 10.3390/ijms19020444.
- [150] M. Eid and E. Araby, “Bactericidal effect of poly(acrylamide/itaconic acid)-silver nanoparticles synthesized by gamma irradiation against pseudomonas aeruginosa,” *Appl. Biochem. Biotechnol.*, vol. 171, no. 2, pp. 469–487, 2013, doi: 10.1007/s12010-013-0357-1.
- [151] M. R. Bindhu and M. Umadevi, “Antibacterial and catalytic activities of green synthesized silver nanoparticles,” *Spectrochim. Acta - Part A Mol. Biomol. Spectrosc.*, vol. 135, no. April, pp. 373–378, 2015, doi: 10.1016/j.saa.2014.07.045.
- [152] W. Sim, R. T. Barnard, and Z. M. Ziora, “Antimicrobial Silver in Medicinal and Consumer Applications: A Patent Review of the Past Decade,” no. Figure 1, pp. 1–15, 2018, doi: 10.3390/antibiotics7040093.
- [153] D. Ballottin *et al.*, “Antimicrobial textiles: Biogenic silver nanoparticles against *Candida* and *Xanthomonas*,” *Mater. Sci. Eng. C*, vol. 75, pp. 582–589, 2017, doi: 10.1016/j.msec.2017.02.110.
- [154] P. V. Baptista *et al.*, “Nano-strategies to fight multidrug resistant bacteria-"A Battle of the Titans",” *Front. Microbiol.*, vol. 9, no. JUL, pp. 1–26, 2018, doi: 10.3389/fmicb.2018.01441.
- [155] M. Singh and T. Sahareen, “Investigation of cellulosic packets impregnated with silver nanoparticles for enhancing shelf-life of vegetables,” *LWT - Food Sci. Technol.*, vol. 86, pp. 116–122, 2017, doi: 10.1016/j.lwt.2017.07.056.
- [156] B. R. A. Hurley, A. Ouzts, J. Fischer, and T. Gomes, “PAPER PRESENTED AT IAPRI WORLD CONFERENCE 2012 Effects of Private and Public Label Packaging on Consumer Purchase Patterns,” *Packag. Technol. Sci.*, vol. 28, Issue, no. January, pp. 271–284, 2015, doi: 10.1002/pts.
- [157] A. Regiel-Futyra *et al.*, “Development of noncytotoxic silver-chitosan nanocomposites for efficient control of biofilm forming microbes,” *RSC Adv.*, vol. 7, no. 83, pp. 52398–52413, 2017, doi: 10.1039/c7ra08359a.
- [158] F. Paladini and M. Pollini, “Antimicrobial silver nanoparticles for wound healing application: Progress and future trends,” *Materials (Basel)*, vol. 12, no. 16, 2019, doi: 10.3390/ma12162540.
- [159] K. K. Sadasivuni *et al.*, *Silver Nanoparticles and Its Polymer Nanocomposites—Synthesis, Optimization, Biomedical Usage, and Its Various Applications*, no. January. 2019.
- [160] P. Singh, H. Singh, Y. J. Kim, R. Mathiyalagan, C. Wang, and D. C. Yang, “Extracellular synthesis of silver and gold nanoparticles by *Sporosarcina koreensis* DC4 and their biological applications,” *Enzyme Microb. Technol.*, vol. 86, pp. 75–83, 2016, doi: 10.1016/j.enzmictec.2016.02.005.
- [161] S. Moosa, A. N. Mohd Faisal Mahadeven, and K. Shameli, “Physiochemical synthesis of Silver/Kaolinite nanocomposites and study their antibacterial properties,” *J. Res. Nanosci. Nanotechnol.*, vol. 1, no. 1, pp. 1–11, 2021, doi: 10.37934/jrnn.1.1.111.
- [162] G. Liao, J. Fang, Q. Li, S. Li, Z. Xu, and B. Fang, “Ag-Based nanocomposites: Synthesis and applications in catalysis,” *Nanoscale*, vol. 11, no. 15, pp. 7062–7096, 2019, doi: 10.1039/c9nr01408j.
- [163] J. Madejová *et al.*, “Antibacterial kaolinite/urea/chlorhexidine nanocomposites: Experiment and molecular modelling,” *Appl. Surf. Sci.*, vol. 305, pp. 783–791, 2014, doi: 10.1016/j.apsusc.2014.04.008.
- [164] S. Ahmad *et al.*, “Green nanotechnology: A review on green synthesis of silver nanoparticles — An ecofriendly approach,” *Int. J. Nanomedicine*, vol. 14, pp. 5087–5107, 2019, doi: 10.2147/IJN.S200254.
- [165] N. Eghbalifam and S. FrounEghbalifam, N., Frounchi, M., & Dadbin, “Antibacterial silver

- nanoparticles in polyvinyl alcohol/sodium alginate blend produced by gamma irradiation,” *Int. J. Biol. Macromol.*, vol. 80, pp. 170–176, 2015, doi: 10.1016/j.ijbiomac.2015.06.042.
- [166] D. E. Hegazy and G. A. Mahmoud, “Radiation Synthesis and Characterization of Polyethylene Oxide / Chitosan- Silver Nanocomposite for Biomedical Applications,” vol. 47, 2014.
- [167] N. M. Huang *et al.*, “ γ -Ray assisted synthesis of silver nanoparticles in chitosan solution and the antibacterial properties,” *Chem. Eng. J.*, vol. 155, no. 1–2, pp. 499–507, 2009, doi: 10.1016/j.cej.2009.07.040.
- [168] R. Yoksan and S. Chirachanchai, “Silver nanoparticles dispersing in chitosan solution: Preparation by γ -ray irradiation and their antimicrobial activities,” *Mater. Chem. Phys.*, vol. 115, no. 1, pp. 296–302, 2009, doi: 10.1016/j.matchemphys.2008.12.001.
- [169] D. van Phu *et al.*, “Synthesis and antimicrobial effects of colloidal silver nanoparticles in chitosan by γ -irradiation,” *J. Exp. Nanosci.*, vol. 5, no. 2, pp. 169–179, 2010, doi: 10.1080/17458080903383324.
- [170] N. Leawhiran, P. Pavasant, K. Soontornvipart, and P. Supaphol, “Gamma Irradiation Synthesis and Characterization of AgNP / Gelatin / PVA Hydrogels for Antibacterial Wound Dressings,” vol. 41138, pp. 1–11, 2014, doi: 10.1002/app.41138.
- [171] L. T. A. Nhien, N. D. Luong, L. T. T. Tien, and L. Q. Luan, “Radiation Synthesis of Silver Nanoparticles/Chitosan for Controlling Leaf Fall Disease on Rubber Trees Causing by *Corynespora cassiicola*,” *J. Nanomater.*, vol. 2018, 2018, doi: 10.1155/2018/7121549.
- [172] T. Jurkin, M. Gotić, G. Štefanić, and I. Pucić, “Gamma-irradiation synthesis of iron oxide nanoparticles in the presence of PEO, PVP or CTAB,” *Radiat. Phys. Chem.*, vol. 124, pp. 75–83, 2016, doi: 10.1016/j.radphyschem.2015.11.019.
- [173] M. Bin Ahmad, J. J. Lim, K. Shameli, N. A. Ibrahim, M. Y. Tay, and B. W. Chieng, “Antibacterial activity of silver bionanocomposites synthesized by chemical reduction route,” *Chem. Cent. J.*, vol. 6, no. 1, pp. 1–9, 2012, doi: 10.1186/1752-153X-6-101.